

## Effect of ionizing radiation on mechanical and electric properties of polymer composites

Deawha Soh<sup>\*</sup>, V.A. Kovtunets<sup>\*\*</sup>, A.I. Kupchishin<sup>\*\*</sup>, G.A. Mun<sup>\*\*</sup>,  
Z.S. Nurkeeva<sup>\*\*</sup>, G.T. Akhmetkalieva<sup>\*\*</sup>, V.V. Khutoryanskiy<sup>\*\*</sup>  
Myongji University, Korea<sup>\*</sup>; Kazakh National University, Kazakhstan<sup>\*\*</sup>

### Abstract

Radiation technology is an effective way for regulating polymeric materials to physicochemical and mechanical properties. The effect of radiation on mechanical and electrochemical properties of new rubber-like polymeric composite materials based on poly(vinyl ether of ethyleneglycol : PVEEG) have been studied for investigating mechanical and electric property of polymer composites applications.

**Keywords** : Radiation, Polymeric materials, physicochemical and mechanical properties, Electrochemical properties, Poly(vinyl ether of ethyleneglycol)

### 1. INTRODUCTION

Radiation treatment of polymeric materials is one of the effective ways for regulation of their physicochemical and mechanical properties. It is well known that the treatment of polymeric materials by high-energy radiation can induce two kinds of processes. The first one is a degradation, which is accompanied by decrease of polymeric molecular weight. The second process is a cross-linking, which leads to the formation of three-dimensional polymeric network. Usually both processes proceed simultaneously upon irradiation of polymers with domination of one of them. The nature of polymer affects significantly the processes, which occur in course of irradiation treatment [1]. At present the polymers of vinyl ethers attract considerable attention of researchers because of their unique physico-chemical and mechanical properties [2]. Recently [3] it was shown that the polymeric films containing poly(vinyl ether of ethyleneglycol) show the behavior typical for polymers in rubbery state at

room temperature. Very high elongations were observed at very low stress applied. The elongation at breakdown for these samples was about 400~500 %. On removing the stress the films underwent a partial contraction, which is typical for rubbery state. In the present work we have studied the effect of radiation on mechanical and electrochemical properties of new rubber-like polymeric composite materials based on poly(vinyl ether of ethyleneglycol).

### 2. EXPERIMENTAL

The hydrogel of polyvinyl ether of ethyleneglycol (PVEEG) was synthesized by gamma-irradiation polymerization of vinyl ether of ethyleneglycol with a help of <sup>60</sup>Co MRX- $\gamma$ -25M at irradiation dose rate 1 Gy/s and absorbed dose 10 kGy as described in Refs [5]. Divinyl ether of diethyleneglycol (4 mol.%) was used as a cross-linking agent. After synthesis the hydrogel was washed by distilled water during 2 weeks to remove unreacted monomers. The equilibrium-swollen hydrogel was dispersed

using the blender CONCEPT 7200 (Bosch, Germany) to obtain a microgel. Two kinds of samples were prepared. The first one was pure poly(vinyl ether of ethyleneglycol) microgel dried on air during several weeks. The second kind was prepared by mixing the microgel with aqueous solution of silver nitrate (20 mL of 0.005 M AgNO<sub>3</sub> was mixed with 250 mL of microgel) and subsequent drying. In course of drying the samples containing silver ions gained a dark color because of partial reduction of AgNO<sub>3</sub> into metallic Ag<sup>0</sup>. The obtained dry samples were cut into pieces of 10 × 20 mm with a thickness 3-5 mm. Irradiation of compositions was conducted using the linear electron accelerator ELU-6 (Russia) with a medium energy of electrons 2 MeV. The absorbed dose was calculated according to the following empirical formula:

$$D = dE/dx \cdot 10^3 \tau j,$$

where  $dE/dx$  is a coefficient of energy absorption by the substance,  $\tau$  - irradiation time (s),  $j$  - electric current density (A/cm<sup>2</sup>). The dose rate was 1.56 kGy/s. The absorbed dose was varied within 10~100 kGy. Mechanical properties of the composites were studied using the facility 2167 P-50 (Russia) in a compression mode. The rigidity index was calculated according to the following formula:

$$k = F/\Delta h S$$

where  $F$  is a force applied (N),  $h$  is a contraction of the sample thickness under stress (m) and  $S$  is a surface of the sample (mm<sup>2</sup>). The dynamic compression was evaluated using the following formula:

$$\varepsilon = (\Delta h/h_0 \Delta \tau) 100 \%,$$


where  $h_0$  is a starting thickness of the sample

and  $\Delta \tau$  is a time of compression. The electric resistance of the materials was measured with the universal voltmeter V-73-42 (Russia).


### 3. RESULTS AND DISCUSSION

The unique mechanical properties of polymers of vinyl ethers in dry state are due to very low glass transition point, which is below than -30°C [3,4]. Therefore at normal conditions the rubbery state is typical for these polymers with a possibility of very high elongations at very low stress applied. The main effect of radiation treatment of polymers of vinyl ethers is a cross-linking, which leads to the formation of polymeric networks [6]. The microgels obtained by pulverization of a macrogel of PVEEG using a blender after drying represent solid substances with rubber-like properties. We have studied the compressibility of the samples as a function of absorbed dose. The dependences of rigidity index of the pure polymer and the samples saturated by silver ions on absorbed dose is plotted in Fig. 1 (a, b, c). It is seen that an increase of absorbed dose leads to a decrease of the samples compressibility, which is caused by cross-linking of polymeric materials. The samples, which were preliminary saturated by AgNO<sub>3</sub> show higher rigidity than the samples based on pure PVEEG due to additional structure formation processes occurring in the materials.


The data on dynamics of compression are plotted in Fig 2. It is seen that depending the absorbed dose the samples reduce their thickness considerably in the first few seconds of the stress and then their compression comes to a plateau. The maximal compression of the sample is about 35~37 %, which is observed for unirradiated samples.

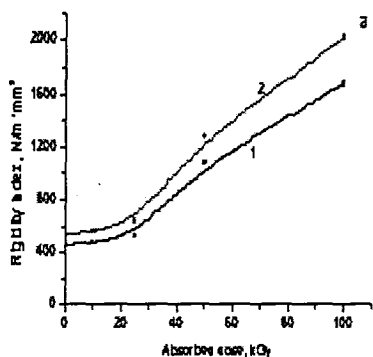

(a)

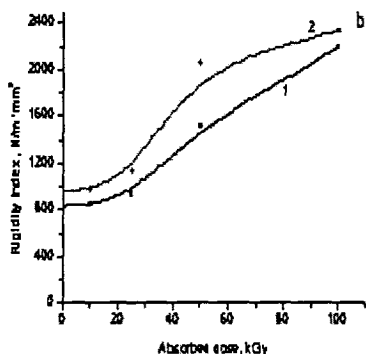

(b)

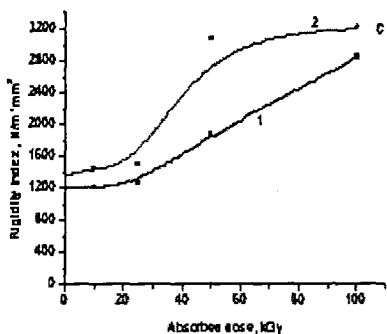


(c)


Fig 1. Dependence of rigidity index of pure PVEEG (1) and PVEEG+AgNO<sub>3</sub> samples (2) on absorbed dose. Applied force: 100 (a), 200 (b), 300 N (c)

It should be noted that the deformation of samples is reversible, which is typical for rubbery state. The samples saturated by AgNO<sub>3</sub> are characterized by lower compression values.

The dependence of electric resistance of obtained polymeric materials on absorbed dose is shown in fig 3. It is seen that the material saturated by AgNO<sub>3</sub> is characterized by lower electric resistance than the pure polymer, which is caused by appearance of ionic conductivity in the presence of Ag<sup>+</sup>, NO<sub>3</sub><sup>-</sup> and water traces.

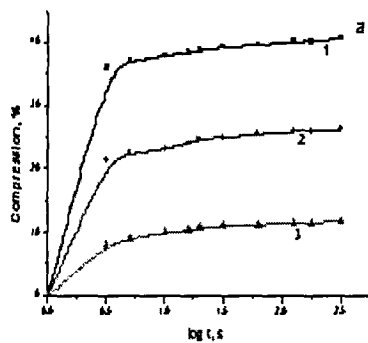

(a)

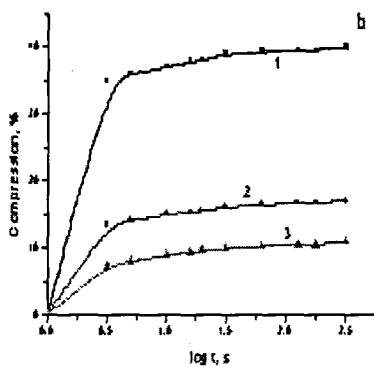

(b)

Fig 2. Dependence of compression of pure PVEEG (a), PVEEG+AgNO<sub>3</sub> samples (b) on time. Absorbed dose: 0 (1), 50 (2), 100 kGy (3). Applied force: 100 N

In both cases an increase of absorbed dose decreases the electric conductivity of the materials, which is probably connected with a cross-linking process and some loss of charge carriers mobility.

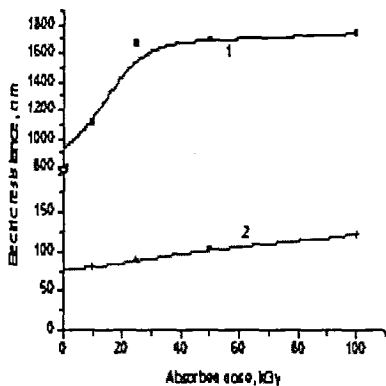


Fig 3. Dependence of electric resistance of pure PVEEG (1), PVEEG + AgNO<sub>3</sub> samples (2) on absorbed dose

#### 4. CONCLUSION

The polymeric materials prepared based on poly(vinyl ether of ethyleneglycol) show the mechanical properties typical for rubbery-state. An irradiation treatment of the polymers results in additional cross-linking, which strengthens the mechanical properties. A saturation of obtained materials by AgNO<sub>3</sub> leads to a considerable decrease of electric resistance and increase in rigidity of polymers.

#### Acknowledgements

This work was supported by the KISTEP grant of M6-0011-00-0043 for int'l. JRP.

#### REFERENCES

- [1] Polymers, Utrecht", The Netherlands, 1992.
- [2] Reyntjens W.G.S., Goethals E. "New materials from poly(vinyl ethers) , Polym.

Adv. Technol". p.107, 2001.

- [3] Khutoryanskiy V.V., Cascone M.G., Lazzeri L., Barbani N., Nurkeeva Z.S., Mun G.A., Bitekenova A.B., and Dzhusupbekova A.B., "Hydrophilic films based on blends of poly(acrylic acid) and poly(2-hydroxyethyl vinyl ether) . I. Thermal, mechanical and morphological characterization", J. Mater. Chem., submitted
- [4] Molyneux P., "Water-soluble synthetic polymers: Properties and behavior", CRC Press. Vol.1, 1983.
- [5] Nurkeeva Z.S., Shaikhutdinov E.M., Seitov A.Z., and Saikieva C.Kh., "On radiation polymerization of vinyl ethers of glycols and aminoalcohols", p.932, 1987.
- [6] Sabharwal S., Mohan H., Bhardwaj Y.K., and Majali A.B., "Radiation induced crosslinking of poly(vinyl methyl ether) in aqueous solutions", Radiat. Phys. Chem., p.643, 1999.