

DA01

Multiferroics under strong magnetic fields

Kee Hoon Kim

¹ Frontier Physics Research Division and CSCMR, Department of Physics and Astronomy, Seoul National University, Seoul 151-747, South Korea

*Corresponding author: kikkim@phya.snu.ac.kr, Phone: +82 2 880 9068, Fax: +82 2 888 0769

We have systematically investigated electric/magnetic phase diagram of a series of multiferroic crystals $R\text{Mn}_2\text{O}_5$ ($R=\text{Tb}$, Dy , Bi , and Y) through the magnetization (M), dielectric constant (ϵ), electrical polarization (P) and specific heat (C_p) measurements down to 0.6 K and under static and pulsed magnetic field (H) up to 45 tesla (T) at NHMFL. Comparative studies of the phase diagram reveal several unprecedented findings: (1) phase evolution of the incommensurate antiferromagnetic $Mn\ d$ spin ordering and related magneto-dielectric effects up to 33 T, (2) a new high field phase coupled to an incommensurate $Mn\ d$ spin ordering appearing around 20 T, (3) phase evolution coupled to rare earth f -spin ordering and resultant polarization changes, and (4) significant modification of phase boundaries due to strong d - f spin interaction. Based on the determined electric/magnetic phase diagram, we explain how the exchange striction mechanism can induce large polarization at high field region above 20 T in these series of $R\text{Mn}_2\text{O}_5$ compounds. In the second part, we particularly discuss the intriguing electric/magnetic signals of BiMn_2O_5 . At low temperatures below 5 K, BiMn_2O_5 exhibits a single magnetic-field-induced transition near $H_c \sim 18$ T as evidenced by a sharp increase in magnetization. Interestingly, ϵ vs H curves show a sharp peak at H_c , of which magnitude systematically increases as temperature approaches proximity to a zero temperature. Furthermore, P changes its sign with increasing H from positive to negative at H_c without any hysteresis in H so that H_c coincides with the magnetic field at which $P=0$. The trajectory of which above three transitions occur follows the scaling relation $T_c(H) \sim (H-H_c)^\alpha$ with $\alpha=1/2$. The shape of C_p versus H curve indicates that a magnetic-field-induced transition is close to the 2nd order down to ~ 0.6 K which is consistent with the absence of hysteresis in M , ϵ , and P measurements. Temperature dependent ϵ measurements under fixed magnetic field (Fig. 1) near H_c reveal that ϵ increases systematically as T decreases to ~ 4 K and slightly decreases down to 0.6 K, as similarly observed in quantum paraelectric SrTiO_3 . All of these observations suggest an interesting possibility that BiMn_2O_5 can be a unique system to exhibit quantum fluctuation of ferroelectricity tuned by magnetic field.

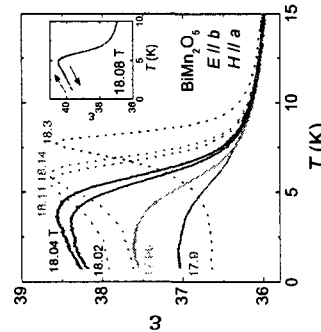


Fig. 1. ϵ vs T curve near $H_c=18$ T.

In close collaboration with : J. W. Kim, S. Y. Haam, Y. S. Oh, T. H. Kim, N. Hur, S. Park, S.-W. Cheong, J. H. Han, P. A. Sharma, N. Harrison, and A. Migliori

DA02

Magnetic properties in RTiO_3 thin filmsC. U. Jung*¹

¹ Department of Physics, Hankyuk University of Foreign Studies, Yongin, Gyeonggi-do 449-791, Korea

*Corresponding author: cu-jung@hufs.ac.kr, Phone: +82 31 330 4952, Fax: +82 31 330 4566

RTiO_3 ($R = \text{Eu}, \text{Y}$) thin films were grown by using a pulsed laser deposition. The suitable choice of substrate as well as reducing growth condition allowed us to grow the epitaxial YTiO_3 thin films. The YTiO_3 film exhibited a clear ferromagnetic transition around 30 K with a saturation magnetization of about $0.7 \mu\text{B}/\text{Ti}$. [1] Recently, novel magnetic and electric phase control in epitaxial EuTiO_3 thin films was predicted from first principles calculation. [2] To verify this prediction, EuTiO_3 thin films were grown on various kinds of substrates with different lattice mismatch and their structural and magnetic properties were investigated.

REFERENCES

- [1] S. C. Chae, Y. J. Chang, S. S. A. Seo, T. W. Noh, D.-W. Kim, and C. U. Jung, Appl. Phys. Lett. **89**, 182512 (2006).
 [2] Craig J. Fennie and Karim M. Rabe, Phys. Rev. Lett., **97**, 267602 (2006).