

# 무윤활 압연한 알루미늄 판재의 기계적 특성과 성형성

사이드무로드 아크라모프<sup>1</sup> · 김인수<sup>1#</sup>

## Mechanical properties and formability of asymmetrically rolled aluminum alloy sheet

S. Akramov<sup>1</sup>, Insoo Kim<sup>1#</sup>

### Abstract

Drawability and other mechanical properties of sheet metals are strongly dependent on their crystallographic orientations. In this paper the formability of the AA 5052 Al alloy sheets was investigated after asymmetric rolling and subsequent heat treatment. In most cases, after asymmetric rolling specimens showed a fine grain size and subsequent heat treated specimens showed that the ND // <111> texture component were observed. The anisotropy of formability is often described by the plastic strain ratios (r-value) as a function of the angle to the rolling direction in sheet metal. For a good formability, a high r-value is required in sheet metals. In the asymmetry rolled and subsequent heat treated Al alloy sheet, the variation of the plastic strain ratios have been investigated in this study. The plastic strain ratios of the asymmetry rolled and subsequent heat treated AA 5052 Al alloy sheets were higher than those of the original Al sheets. These could be related to the formation of ND // <111> texture components through asymmetric rolling in Al sheet.

**Key Words** : Aluminum sheet, Shear Deformation, Texture, Plastic strain ratio, Formability, r-value

### 1. 서 론

In the past decade, many researchers are interested in optimization of the formability of the aluminum alloys in order to increase their application range. Using shear deformation processes can be obtained very fine grained materials with high strength but limited formability properties.

It has been found that the deformation in metals sheets of <111> plane parallel to the sheet surface helps to increase the r-value and variation of the textures decreasing  $\Delta r$ -values. However, due to the high energy stored in the deformed state and the existence of structural heterogeneities, annealing conditions are critical and unwanted structures may form. [1-5]. In the

present paper investigation of the AA 5052 Al alloy sheet was asymmetrically rolled with high reduction ratio without lubricant to investigate the effects of the severe shear deformation on plastic strain ratio of subsequent heat treated AA 5052 Al alloy sheet.

### 2. 제 목

Sheet of commercial AA 5052 aluminum alloy was used to obtain a severe deformation by asymmetrical rolling process with rolls diameter ratios 1.5. The sheet samples, with dimensions of 60mm x 40mm x 3mm, were prepared from a sheet along the rolling direction. Then these plates were annealed at 500 ° C for 1 hour to homogenize the initial grain size through thickness (named initial Al sheet). The annealed Al sheets were then asymmetrically rolled to different reductions

1. 금오공과대학교 신소재시스템공학부  
# 교신저자: 금오공과대학교 신소재시스템공학부,  
E-mail: iskim@kumoh.ac.kr

ranging from 0 to 80% on a laboratory asymmetrical rolling mill with roll ratio 1.5. Hence we will observe 60% asymmetrically rolled samples in 2 passes. To obtain high friction ratio no lubricant was used during rolling process. To obtain the information of the texture change in the frictionally rolled and heat treated samples, the incomplete pole figures of (111), (200), and (220) for each sample were measured by using X-ray goniometer [5]. After the asymmetrical rolling, to study the formability of the asymmetrical rolled Al sheets, samples were annealed at the temperature of 300 ° C for 20 min in salt bath. The average r-value ( $r_{\text{avg}}$ -value), and  $\Delta r$ -value was obtained from calculated r-value data.

### 3. 제 목

Texture measurements were performed at one tenth thickness close to surface (S=0.9) and half thickness (S=0) of the asymmetrically rolled sheets. (111), (200), and (220) pole figures were obtained by using the Cu-K $\alpha$  radiation with the Schultz reflection method. Using this data inverse pole figures were calculated. Fig. 1 shows (111) pole figures of initial, 60% asymmetrically rolled and subsequent heat treated AA5052 aluminum alloy sheets. As the result of full recrystallisation at 500C heat treatment for 2 hours initial specimen on center (S=0) and one tenth thickness layers (S=0.9) layers have

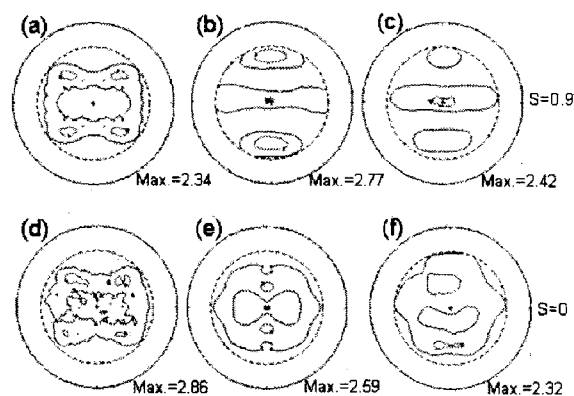


Fig.1 (111) Pole figures from one tenth surface layer S=0.9 (a) initial Al sheet, (b) 80% asymmetric rolled, (c) 80% asymmetric rolled and subsequent heat treated at 300C for 20min. From center layer S=0 (d) initial Al sheet, (e) 80% asymmetric rolled, (f) 80% asymmetric rolled and subsequent heat treated at 300C for 20min.

highest cube texture components intensity. After 60% thickness reduction with asymmetric rolling process, main texture components rotated, and rotated Cube texture components observed on one tenth thickness layer. On the center layer typical rolling texture components observed with minor remained recrystallisation textures. With subsequent heat treatment at 300C for 20min rotated Cube texture decreased and  $\langle 111 \rangle // ND$  texture components observed on S=0.9 layer.

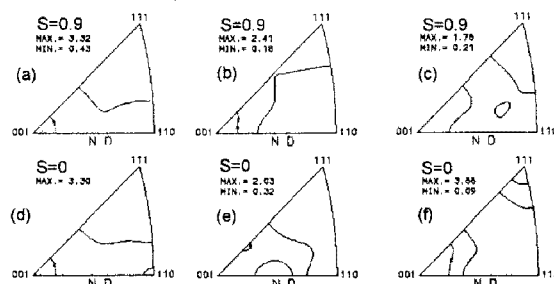


Fig. 2 ND direction inverse pole figures from one tenth surface layer S=0.9 and center layer S=0 where is, (a) initial Al sheet, (b) 80% asymmetric rolled, (c) 80% asymmetric rolled and subsequent heat treated at 300C for 20min.

Fig. 2 shows (111) inverse pole figures, where is the change in texture of the AA 5052 aluminum alloy sheet after heat treatment at 300°C for 20min. compared to the texture without heat treatment and initial Al sample. Strong cube component is observed in initial Al sheet Fig. 1(a, d). At one tenth of thickness layer Fig. 1 (a, b and c) after 90% asymmetric rolling the strong cube component is distorted and  $\gamma$ -fiber ND// $\langle 111 \rangle$ ,  $\{001\} \langle 110 \rangle$  were observed. In case of subsequent heat treatment for 20min at 300°C intensity of the  $\langle 111 \rangle$  pole and rotated cube texture component slightly increased on the center layer data.

### 4. 결 론

In the present study the plastic properties of AA 5052 Aluminum sheet during asymmetric cold rolling was investigated using X-ray diffractometer measurements the following conclusions are summarized from this research work:

- (1) The average r-values of the asymmetric cold rolled with measured Al sheet is higher than that of the initial one.

## 참 고 문 헌

- [1] M. Hatherly, W.B. Hutchinson, An Introduction to Textures in Metals, Institution of Metallurgists, London, 1979.
- [2] J. Hirsch, K. Lucke, Mechanism of deformation and development of rolling textures in polycrystalline F.C.C. metals—simulation and interpretation of experiments on the basis of Taylor-tape theories, Acta Metall. 36 (1988) 2883–2904.
- [3] A.K. Vasudevan, R.D. Doherty, Aluminum Alloys—Contemporary Research and Applications, Treatise on Materials Science and Technology, vol. 31, Academic Press, 1989.
- [4] J. L. Bassani, 1977, Yield characterization of metals with transversely isotropic plastic properties, Int. J. Mech. Sci., Vol. 19, pp. 651 ~ 156.
- [5] M. G. Lee, 2000, Influence of rolling variation and heat treatment process on texture development of cubic metals, Master thesis of Kumoh national institute of technology
- [6] H.J. Bunge: Texture Analysis in Materials Science, translated by P.R. Morris (Butterworths, London 1982, p. 337)
- [7] P.H. Lequeu and J.J. Jonas, Metall. Trans. Vol. 19A (1988), p. 105
- [8] J.J. Park, Predictions of texture and plastic anisotropy developed by mechanical deformation in aluminum sheet, J. Mater. Process. Technol. 87 (1999) 146–153. J. L. Bassani, 1977, Yield characterization of metals with transversely isotropic plastic properties, Int. J. Mech. Sci., Vol. 19, pp. 651 ~ 156.