Preliminary Study of Annular Fuel Fabrication Using Hot Extrusion Method

Sang-Gyu Park*, Kiho Kim, and Jeong-Yong Park Korea Atomic Energy Research Institute, 111, Daedeok-daero 989beon-gil, Yuseong-gu, Daejeon, Republic of Korea *sgpark82@kaeri.re.kr

1. Introduction

The innovative fuel fabrication development is the development of the advanced ultra-high burnup sodium-cooled fast reactor metallic fuel concepts. The fabrication experiment seeks to investigate advanced fuel designs with the following features: decreased fuel smeared density (SD), venting of the fission gas to the sodium coolant, reduce the FCCI (Fuel Cladding Chemical Interaction), advanced fabrication method that includes consideration of annular fuel and extrusion method. The one of most attractive advantage of extrusion method is save the process waste by omitting the sodium process. From the previous study, annular fuel shows the possibility of the reduction of swelling effect and then prevention of the FCMI (Fuel Cladding Mechanical Interaction) [1]. However, the fabrication technology of the annular fuel has not been developed yet. Hence, KAERI has started to study the annular fuel fabrication method by using hot extrusion method. In this study, the prototype of annular fuel has been fabricated by using Cu billet. The design of billet and annular fuel has been determined, and then and design and material for the mold has been determined by using Deform 3D program. After the mold fabrication, the prototype annular fuel has been fabricated and its texture were examined by us EBSD (Electron Back Scatter Diffraction).

2. Result & Discussion

2.1 Design of Billet & Annular Fuel

The size of the billet and the fuel core specimens for the production of the annular simulated fuel shims were determined. In the case of the fuel padding, the annular shape having a diameter of 5 mm and a smear density of 75% was selected as a ring 10 mm in diameter. In the case of a billet, a diameter of 40 mm was selected by extrusion. The inside of the billet was designed to be easily manufactured into an annular shape by extruding holes of the same size as annular fuel.

2.2 Preliminary Fabrication of Annular Fuel

Based on the analysis results, the jig design was designed, and the mold was manufactured based on the design. In the simulated fuel core extrusion, a press machine capable of extruding a maximum of 200 tons was used, and the extrusion was performed by inserting the billet before extrusion into a mold set at 450°C after heating at 600°C. As a result of the extrusion, it was possible to successfully fabricate the annular fuel. The microstructure distribution of Cu annular fuel after extrusion was analyzed using Electro Back-Scattered Diffraction (EBSD). Cu has a phase centered cubic crystal structure (face centered cubic (FCC)) at room temperature. Cu has a fine grain size of several um to several tens of µm after extrusion. This tendency is different from that of an

general extruded structure exhibiting anisotropy along the machining direction. This is attributed to the fact that the microstructure of the billet formed in the initial machining already has a fine grain size.



Fig. 1. Extrusion equipment.

Fig. 1 shows the result of analyzing the temperature at each part during actual extrusion. The extrusion conditions were selected based on the extrusion of the annular simulated fuel core with Cu at a maximum temperature of 726°C.

2.3 Microstructure Analysis of Billet

In order to analyze the cause of the fine grains of the Cu annular fuel, the microstructure of the billet produced by the conventional machining is analyzed by EBSD. The texture of the treated billet was similar to that of the microstructure after extrusion, but it showed a tendency to have a grain size of at most 100 um or more, which is relatively coarser than that of the extruded fuel core. Therefore, it is considered that the non-anisotropic crystal tendency analyzed after extrusion production is attributed to the fact that the crystal grains used in the processing billet are already small in size. In order to study the anisotropy control in the extrusion process, it is judged to be appropriate. Therefore, in the future extrusion process research, the test will be carried out

using the directly melt-cast billets.

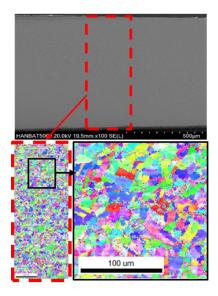


Fig. 2. Texture analysis annular fuel (L direction).

3. Conclusion

In this study, the prototype of annular fuel has been fabricated by using hot extrusion method. The mold for annular fuel was designed using Deform 3D, and the fabrication was successfully done by press extrusion method.

ACKNOWLEDGEMENT

This work was supported by the National Research Foundation of Korea funded by the Ministry of Science and ICT (2017M2A8A5014888).

REFERENCES

[1] K. Marsden, "Report on Development of Concepts for the Advanced casting System in Support of the Deployment of a remotely Operable Research Scale Fuel Fabrication Faculty for Metal Fuel", INL/EXT-07-12469