

A New Choice for the Polymerization Inhibitor in 2-Hydroxyethyl Methacrylate Synthesis

Byeong-Deog Park, Heon-Seung Chae, Heung Chang[†],
Seung-Mo Oh, and Yoon-Sik Lee^{*}

Chemical Technology

Seoul National University, Seoul 151-742

[†]Samsung General Chemicals Co., Ltd., Daesan-Eup,
Seosan-Gun, Chung-Nam 352-870

Received May 24, 1993

2-Hydroxyethyl methacrylate (2-HEMA) is one of the most important chemicals produced in large amounts nowadays. It is widely used as a monomer for the production of various resins, varnishes, adhesives, and hydrogels for contact lenses, drug carriers and etc.¹ Generally, it has been synthesized by adding ethylene oxide (EO) to methacrylic acid (MA). The reaction should be carefully controlled by using proper catalysts and inhibitors since the reactants and products can easily be polymerized. So far many catalysts such as tertiary amines,² quaternary ammonium salts,³ metal salts,⁴ ion exchange resins,⁵ and polymer supported iron catalysts⁶ have been reported. As metallic catalysts, Fe(III) salts such as FeCl₃, FeBr₃, Fe₂(SO₄)₃, and Fe(NO₃)₃ have been widely used.

Since 2-HEMA contains a viny group which is vulnerable to the polymerization reaction, inhibitors must be added during the synthesis and purification processes. So far, an extensive search for a more effective synthesis process has been focused on the development of the proper polymerization inhibitors.⁷ Among them, some phenol derivatives such as *p*-methoxyphenol (PMP), hydroquinone, and 2,6-di-*t*-butyl-4-methylphenol have been widely used as polymerization retarders, aq. nitrite or nitrate salts have been employed as inorganic inhibitors. But, the inhibition mechanisms for the above mentioned have not been systematically studied so far. We now wish to report some important results about the effect of inhibitors on the 2-HEMA synthesis.

2-HEMA was synthesized from MA and EO by using catalysts such as FeCl₃·6H₂O, Na₂Cr₂O₇, and triethylamine (TEA) (Table 1). The reactions were carried out in an autoclave (Parr model, 4561, SUS 316) at 3.5-5.0 atm. The synthesis procedure was as follows. MA, catalysts and inhibitors were added in an autoclave, followed by a N₂ purge, and the N₂ pressure was adjusted to 2.5-3.0 atm. After the reactor temperature was raised to 85°C, EO was slowly and continuously added for about 30 min. After the completion of the reaction which took about 75-300 minutes, the residual EO was vented out by N₂ stripping, and the products were analyzed by GC⁸ and acid-number titration. The results are summarized in Table 1.

As illustrated in the table, when PMP was used as an inhibitor, the reactions were generally sluggish and the polymerization had occurred even with TEA. On the other hand, when aq. NaNO₃ was used as an inhibitor, the reactions were fast with high conversion yields.

The inhibition mechanism of PMP is known to be related to the resonance-stabilizing effect of the corresponding phenol radical after losing hydrogen atom to propagating radical.

Table 1. The Catalytic Activities and the Effects of Inhibitors on 2-HEMA Synthesis^a

| Catalyst ^b | Inhibitor | Reaction time ^c (min) | Conversion _v of MA |
|--|-------------------|----------------------------------|-------------------------------|
| FeCl ₃ ·6H ₂ O | NaNO ₃ | 160 | 98% |
| Na ₂ Cr ₂ O ₇ | NaNO ₃ | 180 | >98.8% |
| TEA | NaNO ₃ | 75 | 97% |
| FeCl ₃ ·6H ₂ O | PMP | >300 | 89% |
| Na ₂ Cr ₂ O ₇ | PMP | 150 | 95% |
| TEA | PMP | 180 | |

^aConditions: reaction temperature; 85°C, MA (580 mmol), EO (1.1 eq to MA). Inhibitor; 30% NaNO₃ aqueous solution (2.0 mmol), PMP (2.0 mmol). Initial pressure; 3.5 atm under N₂ atmosphere. ^bThe amount of catalyst: FeCl₃·6H₂O (3.7 mmol), Na₂Cr₂O₇ (3.8 mmol), TEA (22 mmol). ^cDetermined by the pressure drop to the original one. ^dDetermined by acid-number. ^ePolymers were formed.

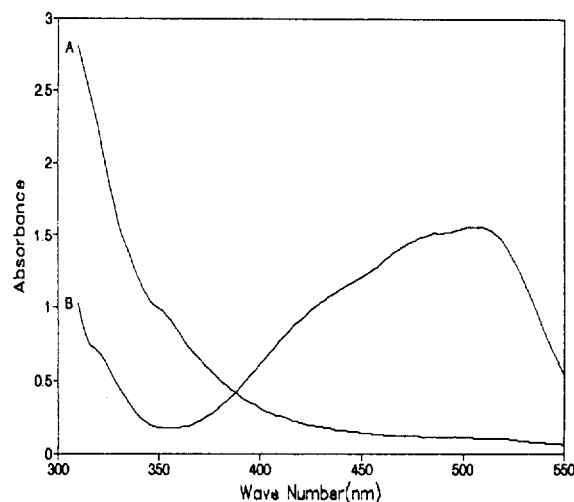


Figure 1. UV-VIS spectrum of iron-phenanthroline complex from A; Crude 2-HEMA products from FeCl₃·6H₂O+NaNO₃ system, B; Crude 2-HEMA products from FeCl₃·6H₂O+PMP system. Condition; 1% (v/v) of crude 2-HEMA in potassium acetate-acetic acid buffer (1×10⁻² M, pH 4), [Phenanthroline]=2×10⁻⁴ M.

This leads us to postulate that PMP itself can reduce other chemicals, even transition metal complexes. In order to test the validity of this hypothesis, the crude 2-HEMA products were diluted to 1% (v/v) with potassium acetate-acetic acid buffer (1×10⁻² M, pH 4), then 2 ml of 0.01 N aq. phenanthroline solution was added, and the UV-VIS spectra of the resulting solutions were taken. It is known that phenanthroline forms a complex with Fe²⁺ (λ_{max}, 515 nm) and Fe³⁺ (λ_{max}, 394 nm)^{9a}. The results showed that the crude product from the PMP system clearly had λ_{max} at 515 nm, while that from the NaNO₃ system revealed a shoulder around 350 nm^{9b} giving no characteristic of λ_{max} from 370 nm to 515 nm (Figure 1).

This implies that Fe³⁺ ion was reduced to Fe²⁺ ion in the PMP system during the course of the reaction. To ascertain the reducing ability of PMP, Fe³⁺ ion in water was reac-

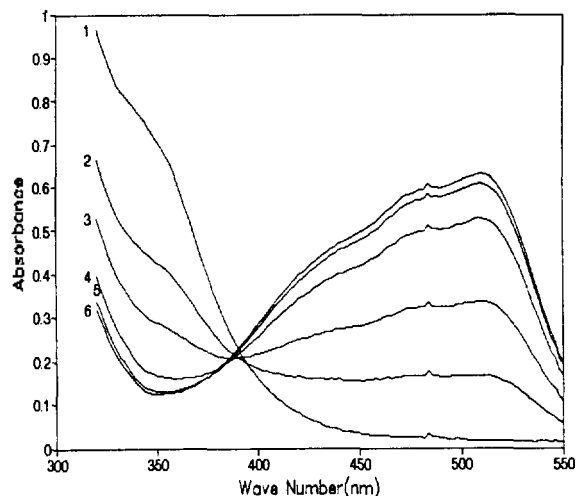


Figure 2. UV-VIS spectra change of iron-phenanthroline complex after addition of PMP to Fe^{3+} ion. Condition: potassium acetate-acetic acid buffer, 1×10^{-2} M, pH 4, 25°C , $[\text{FeCl}_3] = 3.6 \times 10^{-4}$ M, $[\text{PMP}] = 7.8 \times 10^{-4}$ M, $[\text{Phenanthroline}] = 2 \times 10^{-4}$ M; after (1) 0 sec, (2) 40 sec, (3) 70 sec, (4) 120 sec, (5) 300 sec, (6) 600 sec.

ted with PMP in a separate experiment, and the products were monitored by taking the UV-VIS spectra as demonstrated in Figure 2. The concentration of $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ was 3.6×10^{-4} M and that of PMP was 7.8×10^{-4} M. Immediately apparent in Figure 2 is that the reduction of Fe^{3+} did occur very quickly, even at room temperature. After 600 seconds, a shoulder at 354 nm was completely disappeared. In the NaNO_3 system, however, NO_3^- ion has kept Fe^{3+} ion intact. It could even reoxidize the Fe^{2+} ion to Fe^{3+} ion at 85°C , which was proven by the UV-VIS spectra.¹⁰

It is desirable in many catalytic reactions to have catalytic systems whose activity is maintained throughout the reaction. Considering the catalytic system utilized in this study, a hard Lewis acid (such as Cr^{6+} and Fe^{3+} ions) seems to have good catalytic activity. This can be accounted for the fact that ethylene oxide, a hard base, can be coordinated to or interact with the hard metal ions for the hydroxyethylation of MA. In the PMP system, PMP reduced Fe^{3+} ion to Fe^{2+} ion, that is, PMP made the catalyst softer, resulting in a loss of the catalytic activity.

The inhibition by NaNO_3 may be related to, if any, the formation of O_2 from NaNO_3 ¹¹ or the oxidizing power of NaNO_3 . In methacrylic acid medium, NaNO_3 could be equilibrated with HNO_3 , and with nitrogen dioxide, O_2 , and H_2O .¹² The inhibition effect of O_2 had also been reported.¹³ Together with the oxidizing power of NaNO_3 it can give the maximum inhibition effect in FeCl_3 catalyst system. FeCl_3 itself has been proved of its high inhibition effect in radical polymeri-

zation reaction.¹⁴ Actually, the reduced Fe^{2+} ion formed by any radical can be reoxidized repeatedly by NaNO_3 .

In conclusion, when amine derivatives or metal catalysts are used in the synthesis of 2-HEMA, NaNO_3 which is a mild oxidizing agent is more effective inhibitor than PMP.

References

- O. Wichtale, in *Encyclopedia of Polymer Technology*, Vol. 15, p. 275, Wiley, New York, 1971.
- Japan Kokai, 02,649 (1971).
- (a) Brit. Patent, 1,096,035 (1967); (b) Neth. Appl., 6,611, 627 (1967).
- (a) Japan Kokai, 23,019 (1977); (b) Japan Kokai, 42,657 (1982); (c) Japan Kokai, 54,514 (1976).
- V. A. Podgornova *et al.*, *Zh. Prikl. Khim.*, 50(4), 878 (1977).
- P. Ivanova *et al.*, *Applied Cat.*, 53, 41 (1989).
- (a) Japan Kokai, 125,315 (1974); (b) FR, 1,485,764 (1967); (c) Japan Kokai, 27,457 (1988); (d) U. S. Patent, 2,819,296 (1958); (e) Japan Kokai, 26,810 (1976).
- GC condition was as follows: stationary phase; polyethylene glycol 6000(10%), support; Chromosorb W(AW) DMCS 60-80 mesh, SS, ID; 1/8 inch, length; 2 m. Carrier gas; N_2 , injector temperature; 220°C , detector(FID) temperature; 300°C , column temperature; 125°C (3 min), temperature programming; $2^\circ\text{C}/\text{min}$, final temperature; 150°C (5 min).
- (a) J. Bassett *et al.*, "Vogel's Textbook of Quantitative Chemical Analysis", 5th Ed., p. 691, Longman, 1989.
- The oxidation condition was as follows: 1×10^{-2} M potassium acetate-acetic acid buffer, pH 4, $[\text{Phenanthroline}] = 2 \times 10^{-4}$ M, $[\text{NaNO}_3] = 4 \times 10^{-3}$ M, $[\text{FeCl}_2] = 2.7 \times 10^{-4}$ M, 85°C . Even though excess NaNO_3 was used, the oxidation reaction of Fe^{2+} ion was not completed. After 30 min, about 10% of Fe^{2+} ion was oxidized to Fe^{3+} ion.
- O_2 formation was detected by GC. GC condition was as follows: stationary phase; Molecular sieve 5A, SS, ID; 1/8 inch, length; 2 m. Carrier gas; He, injector temperature; 125°C , detector(TCD) temperature; 125°C , column temperature; 110°C . The crude 2-HEMA product (25 ml) from FeCl_3 and NaNO_3 was added by 1.47 mmol of NaNO_3 , and cooked at 110°C in a closed system of 1 atm; The initial area ratio of O_2 to N_2 was 1/200, which was increased to 1/25 after 5 hours.
- N. N. Greenwood and A. Earnshaw, "Chemistry of Elements", p. 538, Pergamon press, 1984.
- (a) J. J. Kurland, *J. Polym. Sci., Polym. Chem. Ed.*, 18, 1139 (1980); (b) K. Kishore and V. A. Bhanu, *J. Polym. Sci., Polym. Chem. Ed.*, 26, 2832 (1988).
- C. H. Bamford, A. D. Jenkins, and R. Johnston, *J. Polymer Sci.*, 29, 355 (1958).