

## Green Emission Band Site of $\text{Ce}^{3+}$ in $\text{YAlO}_3:\text{Ce}^{3+}$ Phosphor

G. C. Kim, T. W. Kim<sup>†</sup>, S.-I. Mho<sup>†</sup>, and H. L. Park\*

Department of Physics, Faculty of Arts and Education Korea  
Institute of Technology and Education, Chungnam 333-860, Korea

<sup>†</sup>Department of Physics, Kwangwoon University, Seoul 139-701, Korea

<sup>†</sup>Department of Chemistry, Ajou University, Suwon 441-749, Korea

\*Department of Physics, Yonsei University, Seoul 120-749, Korea

Received September 6, 1996

It is well known that  $\text{YAlO}_3$  is a good laser host material<sup>1</sup> and  $\text{YAlO}_3$  activated with rare-earth and transition metal ions is used for scintillators and screens in optical devices.<sup>2,3</sup> The fluorescence excitation spectra of  $\text{YAlO}_3:\text{Ce}^{3+}$  phosphor reveal that the UV and visible emission spectra are arising from 4f-5d transitions of  $\text{Ce}^{3+}$  ion in  $\text{YAlO}_3$ .<sup>4,5</sup> In this communication, we are going to report the cerium site in  $\text{YAlO}_3:\text{Ce}^{3+}$  which have been debated over the years.<sup>5</sup> Especially, the site of  $\text{Ce}^{3+}$  green emission band is not known exactly.

### Experimental

The  $\text{YAlO}_3:\text{Ce}^{3+}$  phosphor was prepared from starting compositions consisting of  $\text{Y}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ ,  $\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ , and  $\text{CeO}_2$ . The concentration of cerium was varied from 0.001 to 0.05 mole%. The constituents were well mixed and reacted at 1000 °C for 5hrs. The phases of products were checked through the conventional XRD technique. For emission measurements, an Oriel 1000W Hg (Xe) lamp and a 250 nm band pass filter (Oriel 53340) combination were used for an excitation source. The emission spectra were obtained using a 75 cm Spex monochromator equipped with an RCA31034 photomultiplier tube. The signals from the photomultiplier tube were electronically amplified and displayed on an X-Y recorder.

### Results and Discussion

The emission spectra of cerium doped  $\text{YAlO}_3:\text{Ce}^{3+}$  along with undoped  $\text{YAlO}_3$  are shown in Figure 1. We observed one broad emission band peaking around 370 nm in undoped  $\text{YAlO}_3$  and two broad emission bands, *i.e.*, around 370 nm and 500 nm, in cerium doped  $\text{YAlO}_3$ . The origin of 370 nm emission band has been interpreted as a self-activating center, *i.e.*, optical transition between conduction band of  $\text{YAlO}_3$  to oxygen 2p band.<sup>6</sup> The emission band around 370 nm exhibits red shift and a new emission band around 500 nm is appearing when we doped  $\text{Ce}^{3+}$  ions in  $\text{YAlO}_3$ . Also the red shift of 370 nm emission band and the emission intensity of 500 nm band are enhanced when the  $\text{Ce}^{3+}$  ion concentration is increased in  $\text{YAlO}_3$ . The apparent red shift of 370 nm emission band is attributed to the  $\text{Ce}^{3+}$  5d absorption located near 350 nm.<sup>4</sup> This absorption band of  $\text{Ce}^{3+}$  is located at high energy side of  $\text{YAlO}_3$  emission band. Thus, the increment of  $\text{Ce}^{3+}$  concentration in  $\text{YAlO}_3$ ,

enhances the absorption and the apparent red shift in  $\text{YAlO}_3:\text{Ce}^{3+}$  can be observed accordingly. The  $\text{Ce}^{3+}$  absorption in

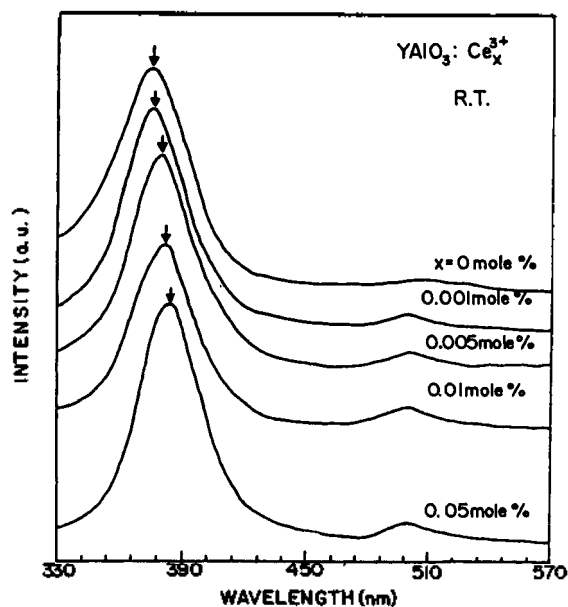


Figure 1. Emission spectra of  $\text{YAlO}_3:\text{Ce}^{3+}$ .

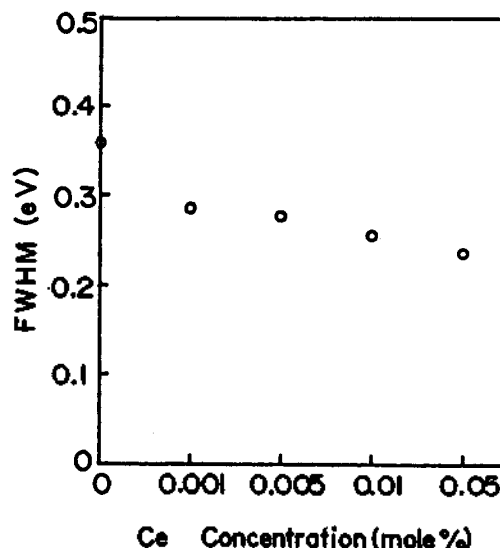


Figure 2. Cerium concentration dependent FWHM of 370 nm emission band of  $\text{YAlO}_3:\text{Ce}^{3+}$ . The energy of 1 eV corresponds to  $8066 \text{ cm}^{-1}$ .

\*To whom all correspondence should be addressed.

$\text{YAlO}_3:\text{Ce}^{3+}$  also exhibits the apparent narrowing of emission band. The Figure 2 depicts  $\text{Ce}^{3+}$  concentration dependent FWHM (Full Width at Half Maximum) of 370 nm emission band. As can be seen in Figure 2, the band narrowing is more pronounced as the concentration of  $\text{Ce}^{3+}$  in  $\text{YAlO}_3$  is increased. The foregoing observations positively support that two emission bands in  $\text{YAlO}_3:\text{Ce}^{3+}$  is closely related to  $\text{Ce}^{3+}$  ions in  $\text{YAlO}_3$  host.

The  $\text{Ce}^{3+}$  sites in  $\text{YAlO}_3$  have been proposed<sup>7</sup> and conjectured<sup>8</sup>, but the supporting arguments are less convincing. The  $\text{YAlO}_3$  has perovskite structure same as  $\text{SrTiO}_3$  and the existing polyhedra are  $\text{YO}_{12}$ ,  $\text{YAl}_8$  and  $\text{AlO}_6$  in this structure. The ionic radii of  $\text{Ce}^{3+}$ ,  $\text{Y}^{3+}$  and  $\text{Al}^{3+}$  are 0.94 Å, 0.92 Å and 0.51 Å respectively. Thus the more probable  $\text{Ce}^{3+}$  sites in  $\text{YAlO}_3$  are  $\text{YO}_{12}$  and  $\text{YAl}_8$  polyhedra where  $\text{Ce}^{3+}$  is substituted for  $\text{Y}^{3+}$  from the ionic radii argument. It is generally accepted that the UV emission band in  $\text{YAlO}_3:\text{Ce}^{3+}$  is originated from the occupied site of  $\text{Ce}^{3+}$  in  $\text{YO}_{12}$  polyhedron. The green emission center in  $\text{YAlO}_3:\text{Ce}^{3+}$  has not been established to date. Mares *et al.*<sup>8</sup> reported the green emission band in  $\text{YAlO}_3:\text{Ce}^{3+}$ . They also suggested that the possible occupied site of green emission of  $\text{Ce}^{3+}$  in  $\text{YAlO}_3$  is  $\text{YAl}_8$  polyhedra without any positively convincing arguments. The  $\text{Ce}^{3+}$  related green emission band was disappeared when  $\text{YAlO}_3$  was codoped with  $\text{Nd}^{3+}$ ,  $\text{Cr}^{3+}$  and  $\text{Ce}^{3+}$ .<sup>8</sup> This observation suggested that many types of polyhedra, *i.e.*,  $\text{YAl}_8$ ,  $\text{CeAl}_8$ , and  $\text{NdAl}_8$ , could be formed when  $\text{Nd}^{3+}$ ,  $\text{Cr}^{3+}$  and  $\text{Ce}^{3+}$  ions were codoped in  $\text{YAlO}_3$ . Thus energy transfer between ions,  $\text{Ce}^{3+} \rightarrow \text{Nd}^{3+}$  and  $\text{Ce}^{3+} \rightarrow \text{Cr}^{3+}$ , could be possible and the energy transfer between ions was man-

ifested with disappearing of green emission band. The above rationale supports that the origin of green emission band site of  $\text{Ce}^{3+}$  in  $\text{YAlO}_3$  is  $\text{YAl}_8$  polyhedron where  $\text{Ce}^{3+}$  is substituted for  $\text{Y}^{3+}$ .

In summary, we investigated the emission characteristics of  $\text{YAlO}_3:\text{Ce}^{3+}$  and the origin of  $\text{Ce}^{3+}$  related green emission band site in  $\text{YAlO}_3:\text{Ce}^{3+}$  has been established as  $\text{YAl}_8$  polyhedron. In other words, the cerium is substituted for yttrium such that  $\text{CeAl}_8$  polyhedron can be formed and cerium in this site is the origin of green emission band in  $\text{YAlO}_3:\text{Ce}^{3+}$ .

**Acknowledgment.** This work has been supported by Korean Research Foundation.

## References

1. Weber, N. J.; Bass, M.; Andringa, K.; Monchamo, R. R.; Comperchio, E. *Appl. Phys. Lett.* **1969**, *15*, 342
2. Takeda, T.; Miyata, T.; Maramatsu, F.; Tomiki, T. *J. Electrochem. Soc.* **1980**, *127*, 438.
3. Autrata, R.; Schauer, P.; Kvapil, Jos.; Kvapil, J. *Res Technol.* **1983**, *18*, 907.
4. Weber, M. J. *J. Appl. Phys.* **1973**, *44*, 3205.
5. Mares, J. A.; Nikl, M.; Pedrini, C.; Moine, B.; Bkazek, K. *Mater. Chem. Phys.* **1992**, *32*, 342.
6. Tomik, T.; Fukudome, F.; Kaminao, M.; Fujisawa, M.; Tanakahara, Y. *Jpn. J. Phys. Soc.* **1986**, *55*, 2090.
7. Diehl, R.; Brandt, G. *Mater. Res. Bull.* **1975**, *10*, 85.
8. Mares, J. A.; Nikl, M.; Blazek, K. *Phys. Stat. Sol. (a)* **1991**, *127*, k65.

## Superfast Transfer via Crossover of F Electronic Energy to $\text{OH}^-$ Vibration in $\text{RbCl}$

S. Y. Lee<sup>†</sup> and Du-Jeon Jang\*

Department of Chemistry and Research Institute of Molecular Science, Seoul National University, Seoul 151-742, Korea

<sup>†</sup>Department of Chemistry, College of Natural Sciences, Kyunggi-Do 449-701, Korea

Received September 16, 1996

Since Dexter, Klick, and Russell reported a crossover mechanism which provides a criterion for the nonradiative quenching of simple impurity centers,<sup>1</sup> the fate of an electronically excited F center in alkali halides has been studied as one of the typical cases.<sup>1-3</sup> The relaxed excited F ( $\text{F}^*$ ) centers in rubidium and potassium halides have a strong luminescence with a microsecond-long lifetime at cryogenic temperatures, while those in lithium and sodium halides have a poor luminescence.<sup>4,5</sup> This remarkable difference in the two types of hosts can be explained by the difference in crossover energy barriers from the relaxed excited state to the crossing point of the excited and ground state potential curves.<sup>1</sup> However, the luminescence in  $\text{KCl}$ , in which the barrier is too high for effective crossover, is reported<sup>6,7</sup> to decrease by the concentration increase of doped molecular

defects such as  $\text{OH}^-$  and  $\text{CN}^-$ .  $\text{F}_H$  formation, association of F center with a molecular defect, makes F absorption broader and lower in energy and quenches F luminescence drastically.<sup>8</sup> Vibrational emission and anti-Stokes Raman scattering from molecular defects observed after F center excitation indicate that the electronic excitation energy of an F center transfers into the stretching vibrational mode of a molecular defect.<sup>9-11</sup>

The energy transfer rate in randomly distributed crystals is varied very much, depending on transfer distance, temperature and host.<sup>8-12</sup> However, the superfast transfer component in aggregated crystals is much the same, regardless of concentration, isotope, and host.<sup>13</sup> This superfast recovery, resulting from the deactivation of an excited F-molecular defect pair, is achieved by the lattice relaxation<sup>14</sup> of the ex-