

## Self-Assembled Supramolecular Architecture Based on an Achiral Bolaamphiphilic Diacid in Binary System

Soo Jin Lee, Shim Sung Lee, Chang Geun Lee,<sup>†</sup> and Jong Hwa Jung<sup>\*</sup>

Department of Chemistry (BK21) and Research Institute of Natural Science, Gyeongsang National University, Jinju 660-701, Korea. \*E-mail: jonghwa@gnu.ac.kr

<sup>†</sup>Department of Polymer Science and Engineering, Pusan National University, Pusan 609-735, Korea


Received November 20, 2006

**Key Words:** Achiral bolaamphiphiles. Binary system. Nano-structures. Self-assembly. Supramolecular architectures

A new family of polymers that includes topologically complex polymers<sup>1</sup> and self-assembled nanostructures<sup>2-6</sup> has recently attracted much attention.<sup>4d</sup> The non-covalent self-assembly technique, unlike chemical reaction or polymerization methods, has the advantage of directly producing well-defined two- and three-dimensional structures such as sheets, rod, fibers, tubes, disks, and spheres. Notably, these nanostructures can be constructed with high efficiency and accuracy, and yet with minimum energy.<sup>7</sup>

Organic amphiphiles typically possess a chiral moiety as well as functional groups with potential to form multiple hydrogen bonds, such as sugars,<sup>8</sup> peptides,<sup>9</sup> or nucleotide bases.<sup>4c-d,8</sup> However, only a few examples for self-assembled supramolecular structures of organic amphiphiles consisting of achiral moieties have been described.<sup>10</sup> Therefore, our initial motivation to prepare bolaamphiphilic diacids was to develop self-organized pseudo-linear polymers stabilized by intermolecular hydrogen-bonds, and that incorporated suitable guest additives with achiral functional groups.

With this idea in mind, we employed a simple bola-form amphiphile ("bolaamphiphile") **1**, consisting of one diphenyl ether group as a hydrophobic moiety at the center, flanked by two carboxylic acids as the terminal hydrophilic groups. In **1**, the linkage we introduce between the hydrophobic and the hydrophilic moieties is an amide group, known to form a linear hydrogen bond chain. We herein report the assembling behavior of **1** with and without guest additives. The additives such as 4,4'-dipyridyl (4,4'-bpy) and 2,2'-dipyridyl (2,2'-bpy) are so common that their interaction behaviors have been well-defined especially in the coordination polymer networks.<sup>3a</sup> We have investigated the influence of the dipyridyl additives on the morphologies of self-assembled **1** and self-assembled **1** combined by bpy which are denoted


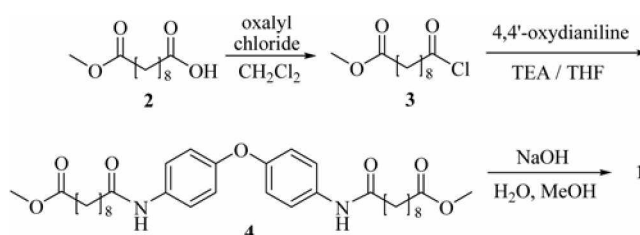


**Scheme 1.** Synthetic route for achiral bolaamphiphilic diacid **1**.


with [**1**] and [**1**+bpy], respectively, by optical microscopy, SEM, FT-IR, powder-XRD and differential scanning calorimetry (DSC).

Achiral bolaamphiphile **1** was synthesized in three steps (Scheme 1). The monomethyl sebacate **2** was chlorinated with oxalyl chloride to give methyl-10-chloro-10-oxodecanoate **3**. Reaction of **3** with 4,4'-oxydianiline afforded diamide derivative **4**. Treatment of **4** with NaOH gave the desired product **1** as a brown powder.

The self-assembly reactions of **1** (3-5 mg) with and without dipyridyl additives (3 equiv) were accomplished by dissolving the reactants in acidic, neutral, and basic conditions in water/ethanol (4:1 v/v, 50 mL) at 80 °C, respectively. The pH of each solution was adjusted with 0.1 M NaOH or 0.1 M HCl aqueous solution.<sup>11</sup> After the incubation of the solutions at room-temperature for several hours, the formation of stable supramolecular assemblies was confirmed. In the absence of additives, SEM pictures for [**1**] (0.50 mM) obtained at pH = 4 show a film-like structure (Figure 1a) whereas at pH = 7, the structures are comprised of bundles

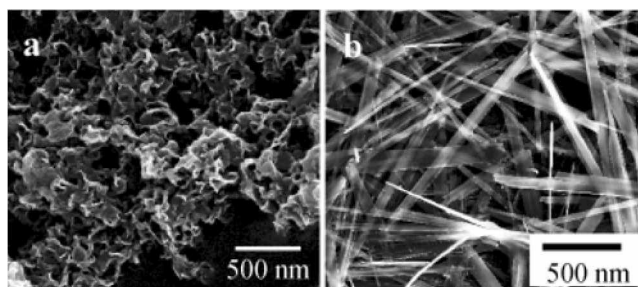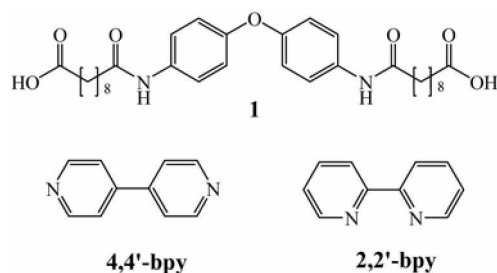

**Figure 1.** SEM pictures for [**1**] obtained at (a) pH = 4 and (b) pH = 7, respectively.

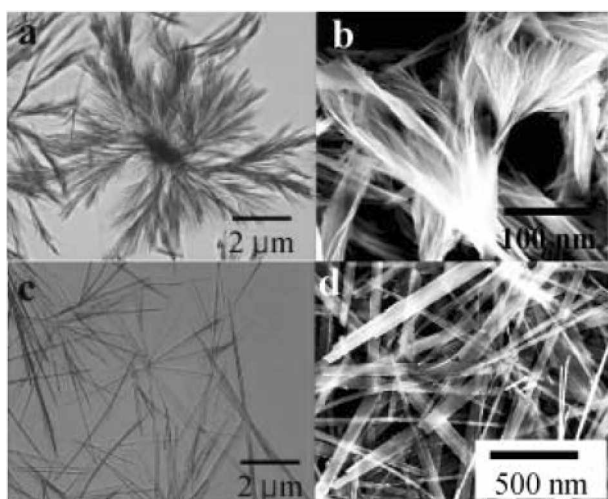


**Figure 2.** Optical microscopic (a and c) and SEM (b and d) pictures of [1+4,4'-bpy] (a and b) and product obtained from the reaction of 1 with 2,2'-bpy (c and d) obtained at pH = 7.

of 100 nm diameter submicro-fibers (Figure 1b). At pH = 10, however, the self-assembly of 1 did not occur. These results indicate that the morphologies of [1] are strongly dependent on the pH of the solutions.

The morphological changes of [1+4,4'-bpy] and [1+2,2'-bpy] were observed (Figure 2). The [1+4,4'-bpy] (1.50 mM) was revealed as a loosely twisted fiber at pH = 7 (Figures 2a and 2b), showing the influence of the ionic hydrogen-bonding between the carboxyl groups of 1 and the pyridyl nitrogen atoms of 4,4'-bpy (e.g.  $\text{COO}^- \cdots \text{PyH}^+$ ) on the morphology of the assembled product. However, no significant differences were noted in the visual morphology between [1] and [1+2,2'-bpy] (Figures 2c and 2d).

Since the microscopic structural views for [1] indicated the participation of the ionic intermolecular hydrogen-bonding, we compared the FT-IR spectra of [1] obtained at pH = 4 and 7 (Figure 3). At pH = 7, spectral bands of [1] appear at

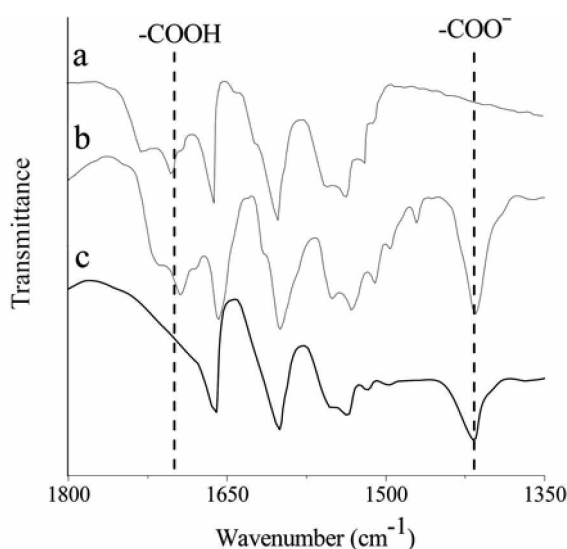

**Figure 3.** FT-IR spectra for [1] obtained at (a) pH = 4, (b) pH = 7, and (c) pH = 10.

1701 and 1410  $\text{cm}^{-1}$  for COOH and  $\text{COO}^-$  species, respectively. Meanwhile, at pH = 4, the spectrum of [1] contains only a band at 1701  $\text{cm}^{-1}$  for COOH. The solid sample 1 obtained at pH = 10 shows a band for the fully ionized  $\text{COO}^-$  species, and gave no specific morphology. Hence, the superstructure of [1] is provided mainly by intermolecular hydrogen bonding interactions between COOH and  $\text{COO}^-$  species at pH = 7.

The intermolecular ionic hydrogen-bonding for [1+4,4'-bpy] was also confirmed by Fermi resonance ( $\nu_{\text{OH}}$ ) by FT-IR analysis as depicted in Figure 4.<sup>12</sup> For example, we observed the respective  $\nu_{\text{OH}}$  and its Fermi resonance at 2450 and 1930  $\text{cm}^{-1}$  (Supporting Information: Figure S1). Additionally, by NMR analysis, we determined that 40-45 mole% of 4,4'-bpy existed within the same fiber. These multiple evidences strongly support the view that 4,4'-bpy was truly incorporated into the superstructure of [1] to form the pseudo-linear polymer. However, the product obtained from the self-assembly reaction of 1 with 2,2'-bpy shows no peak corresponding to the 2,2'-bpy, indicating that 1 does not interact with 2,2'-bpy.

The IR spectrum for [1] in solid state also shows a strong band at 1630  $\text{cm}^{-1}$  corresponding to C=O group whereas the spectrum for 1 in DMSO solution shows an absorbance band at 1680  $\text{cm}^{-1}$  for the same functional group (Figure S2). These findings suggest that the amide groups of [1] obtained from a mixture of water and ethanol play a critical role for the intermolecular hydrogen-bonds between C=O and NH.

To confirm the molecular packing structure, we measured the powder-X-ray diffraction pattern for [1] and [1+4,4'-bpy] (Figure S3). [1] shows a strong high-ordered reflection peak at 2.75°, indicating that it forms a well-organized layer structure by intermolecular hydrogen bonding interaction and  $\pi$ - $\pi$  stacking (Figure 4). The  $d$ -spacing was calculated from the Bragg equation to be 3.29 nm (3.42 nm predicted by the CPK molecular modeling). In contrast, the small-angle diffraction pattern for [1+4,4'-bpy] appeared at 4.35 nm, less than twice the extended molecular length of 1, but larger than the length of one molecule. This result suggests that [1] was well-assembled and constructed in a layer structure through the ionic hydrogen bonds with 4,4'-bpy (Figure 4).

The self-assembled fibers were isolated from the aqueous dispersion by a nitrocellulose membrane with 0.22  $\mu\text{m}$  of pore size, and the isolated samples were dried and used for DSC measurement. [1] showed a phase transition at 222.9 °C (Figure S4), while the [1+4,4'-bpy] exhibited an endothermic peak at 212.9 °C, indicating that 4,4'-bpy is incorporated into the organized systems in microscopic levels (Figure 3). However, the phase transition temperature for the assembled product obtained from 1 and 2,2'-bpy was same as that for [1], also indicating the absence of 2,2'-bpy in the product.

In conclusion, the bolaamphiphile 1 in the absence and presence of bpy additives can be self-assembled into supramolecular nanostructures. In particular, the self-assembly reaction of 1 and 4,4'-bpy forms the pseudo-linear polymer [1+4,4'-bpy] as a result of objective architectures *via* mole-

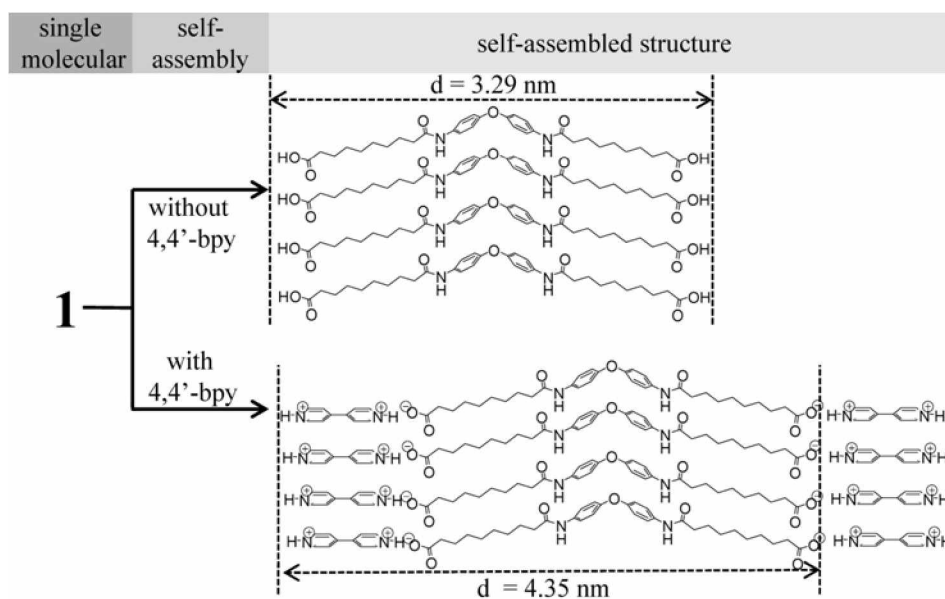


Figure 4. Molecular packing modes for [1] (top) and [1+4,4'-bpy] (bottom).

cular assemblies based on effective intermolecular hydrogen-bonding interaction between these two components.

### Experimental Section

**Apparatus for spectroscopy measurement:**  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra were measured by a Bruker ARX 300 apparatus. IR spectra (KBr pellets) were obtained using a Shimadzu FT-IR 8100 spectrometer.

**SEM observations:** Scanning electron micrographs (SEM) was taken on Hitachi S-4500. The dry sample was coated with palladium-platinum. The accelerating voltage of SEM was 5–15 kV and the emission current was 10  $\mu\text{A}$ .

**XRD measurements:** The XRD of a freeze-dried sample was measured with a Rigaku diffractometer (Type 4037) using graded  $d$ -space elliptical side-by-side multilayer optics, monochromated Cu  $K\alpha$  radiation (40 kV, 30 mA), and an imaging plate (R-Axis IV). The typical exposure time was 10 min with a 150-mm camera length. [1] and [1+4,4'-bpy] were vacuum-dried to constant weight and then put into capillary tubes, without being powdered.

**DSC measurement:** Differential scanning calorimetry (DSC) was performed on a Seiko DSC6100 high-sensitivity differential scanning calorimeter equipped with the nitrogen as cooling unit. The self-assembly was hermetically sealed in silver pan and measured against a pan containing alumina as the reference. The thermograms were recorded at a heating rate  $1\text{ }^\circ\text{Cmin}^{-1}$ .

**Preparation of the self-assembled samples and pH adjustment:** For self-assembly, a weighted powder (3.0–5.0 mg) of products was dispersed in acidic, neutral, or basic solution (water and ethanol: 4:1 v/v, 30 mL) at  $80\text{ }^\circ\text{C}$  for 30 min. The pH of solutions was then adjusted with 0.1 M NaOH or 0.1 M HCl aqueous solution. The transparent aqueous dispersion was gradually cooled to room temper-

ature and kept standing without vibration. After several hours, the cotton-like product formed by self-assembly was obtained. The product was collected for further analysis.

**3.** To a suspension of **2** (0.40 g, 1.85 mmol) in dry  $\text{CH}_2\text{Cl}_2$  (2 mL) containing a few drops of DMF was added oxalyl chloride (1.17 g, 9.2 mmol) carefully *via* syringe. After the effervescence has ceased, the reaction mixture was stirred for 1 h at room temperature. Removal of the solvent and the unreacted oxalyl chloride in vacuo afforded **3**. No further purification was done.

**4.** To a solution of 4,4'-oxydianiline (0.138 g, 0.69 mmol) in dry THF (5 mL) at  $66\text{ }^\circ\text{C}$  under  $\text{N}_2$  was added TEA (0.6 g, 5.2 mmol). The reaction mixture was stirred at  $66\text{ }^\circ\text{C}$  for 10 min. The reaction mixture was added **3** (0.4 g, 1.7 mmol). After 6 h, the precipitate was removed by filtration. Then, the solvent was removed by rotary evaporation to produce a yellow solid. This crude product was purified by column chromatography (silica-gel, ethyl acetate/*n*-hexane, 1:4) to give the product **4** (330 mg, 81%).  $^1\text{H}$  NMR (300 MHz,  $\text{CDCl}_3$ ,  $25\text{ }^\circ\text{C}$ )  $\delta$  7.63 (d, 4H,  $J = 9$  Hz), 6.89 (d, 4H,  $J = 9$  Hz), 3.67 (s, 6H), 2.35–2.37 (m, 8H), 1.45–1.21 (m, 24); MS (EI)  $m/z$  597 ( $\text{M}+\text{H}^+$ ); Anal. Calcd for  $\text{C}_{34}\text{H}_{48}\text{N}_2\text{O}_7$ : C: 68.43, H: 8.11, N: 4.69, found C: 67.50, H: 8.25, N: 4.72.

**1.** **4** (200 mg, 0.33 mL) was dissolved in MeOH (5 mL) and 1 N NaOH (1.5 mL, 1.5 mmol) was added. The mixture was stirred at room temperature for 4 h. The MeOH was removed under reduced pressure and the solution thus obtained cooled in an ice bath and acidified with 1 N HCl (10 mL) with vigorous stirring. The white solid precipitated was filtered off, washed with  $\text{H}_2\text{O}$  and dried **1** (0.180 g, 91%). No further purification was done.  $^1\text{H}$  NMR (300 MHz,  $\text{CDCl}_3$ ,  $25\text{ }^\circ\text{C}$ )  $\delta$  7.59 (d, 4H,  $J = 9$  Hz), 6.99 (d, 4H,  $J = 9$  Hz), 2.48–2.45 (m, 8H), 1.49–1.24 (m, 24); MS (FAB)  $m/z$  569 ( $\text{M}+\text{H}^+$ ); Anal. Calcd for  $\text{C}_{32}\text{H}_{44}\text{N}_2\text{O}_7$ : C: 67.58, H: 7.80, N: 4.93, found C: 68.02, H: 7.65, N: 4.90.

**Acknowledgment.** This work was supported by the KOSEF (F01-2004-10061-0).

### References

- (a) Tomalia, D. A.; Naylor, A. M.; Goddard, A. *Angew. Chem. Int. Ed. Engl.* **1990**, *29*, 138. (b) Hawaker, C. J.; Frechet, J. M. J. *J. Am. Chem. Soc.* **1990**, *112*, 7638. (c) Majoral, J.-P.; Caminade, A.-M. *Chem. Rev.* **1999**, *99*, 845. (d) Jung, J. H.; Rim, J. A.; Lee, S. J.; Park, S. M.; Kim, B. H. *Bull. Korean Chem. Soc.* **2005**, *26*, 120.
- (a) Lehn, J.-M.; Mascal, M.; Decian, A.; Fischer, J. *J. Chem. Soc., Chem. Commun.* **1990**, 479. (b) Whitesides, G. M.; Mathias, J. P.; Seto, C. T. *Science* **1991**, *254*, 1312. (c) Ghadiri, M. R.; Granja, J. R.; Milligan, R. A.; McRee, D. E.; Khazanovich, N. *Nature* **1993**, *366*, 5988.
- (a) Lehn, J.-M. *Makromol. Chem., Macromol. Symp.* **1993**, *69*, 1. (b) Kato, T.; Nakano, M.; Moteki, T.; Uryu, T.; Ujiie, S. *Macromolecules* **1995**, *28*, 8875.
- (a) Gulik-Krzywicki, T.; Fouquey, C.; Lehn, J.-M. *Proc. Natl. Acad. Sci. U.S.A.* **1993**, *90*, 163. (b) Kimizuka, N.; Kawasaki, T.; Hirata, K.; Kunitake, T. *J. Am. Chem. Soc.* **1998**, *120*, 4092. (c) Shimizu, T.; Iwauara, R.; Masuda, M.; Hanada, T.; Yase, K. *J. Am. Chem. Soc.* **2001**, *123*, 5947. (d) Shimizu, T. *Macromol. Rapid Commun.* **2002**, *23*, 311. (e) Iwaura, R.; Yoshida, K.; Masuda, M.; Oshnishi-Kameyama, M.; Yoshida, M.; Shimizu, T. *Angew. Chem. Int. Ed.* **2003**, *42*, 1009. (f) Cho, E. J.; Kang, J. K.; Kang, S.; Lee, J. Y.; Jung, J. H. *Bull. Korean Chem. Soc.* **2006**, *27*, 1881.
- (a) Sasaki, D. Y.; Kurihara, K.; Kunitake, T. *J. Am. Chem. Soc.* **1992**, *114*, 10994. (b) Boland, T.; Ratner, B. D. *Langmuir* **1994**, *10*, 3845. (c) Shimomura, M.; Nakamura, F.; Ijio, K.; Taketsuna, H.; Tanaka, M.; Nakamura, H.; Hasebe, K. *J. Am. Chem. Soc.* **1997**, *119*, 2341.
- (a) Sijbesma, R. P.; Beijer, F. H.; Brunsveld, L.; Folmer, B. J. B.; Ky Hirschberg, J. H. K.; Large, R. F.; M. Lowe, J. K. L.; Meijer, E. W. *Science* **1997**, *278*, 1601. (b) Brunsveld, L.; Folmer, B. J. B.; Meijer, E. W.; Sijbesma, R. P. *Chem. Rev.* **2001**, *101*, 4071.
- Zimmerman, S. C.; Zeng, F.; Reichert, D. E. C.; Kolotuchin, S. V. *Science* **1996**, *271*, 1095.
- (a) Masuda, M.; Hanada, T.; Okada, Y.; Yase, K.; Shimizu, T. *Macromolecules* **2000**, *33*, 9233. (b) Feriggeri, A.; Gronwald, O.; van Bommel, K. J. C.; Shinkai, S.; Reinhoudt, D. N. *J. Am. Chem. Soc.* **2002**, *124*, 10754. (c) Kiyonaka, S.; Sugiyasu, K.; Shinkai, S.; Hamachi, I. *J. Am. Chem. Soc.* **2002**, *124*, 10954. (d) Gronwald, O.; Shinkai, S. *Chem. Eur. J.* **2001**, *7*, 4329.
- (a) Bong, D. T.; Clark, T. D.; Granja, J. R.; Gradiri, M. R. *Angew. Chem. Int. Ed.* **2001**, *40*, 988. (b) Fernandez-Lopez, S.; Kim, H.-S.; Choi, E. C.; Delgado, M.; Granja, J. R.; Khasanov, A.; Krehenbuehl, K.; Long, G.; Weinberger, D. A.; Wilcoxon, K. M.; Ghadiri, M. R. *Nature* **2001**, *412*, 452.
- (a) Lu, Q.; Luo, Y.; Li, L.; Liu, M. *Langmuir* **2003**, *19*, 285. (b) Aoki, K.; Nakagawa, M.; Seki, T.; Ichimura, K. *Bull. Chem. Soc. Jpn.* **2002**, *75*, 253. (c) Masui, H.; Porrata, P.; Douberty, G. E. *J. Nano Lett.* **2001**, 461.
- (a) Kogiso, M.; Ohnishi, S.; Yase, K.; Masuda, M.; Shimizu, T. *Langmuir* **1998**, *14*, 4978. (b) Kogiso, M.; Hanada, T.; Yase, K.; Shimizu, T. *Chem. Commun.* **1998**, 1791.
- Johnson, S. L.; Rumon, K. A. *J. Phys. Chem.* **1965**, *69*, 74.