

# A Study on Magnetic Abrasive using Sludge

Hee-Nam Kim\*

**Abstract** – In this paper, we have investigated the characteristics of the magnetic abrasive using sludge on polishing of internal finishing of seamless stainless steel tube applying magnetic abrasive polishing. Either green carborundum(GC) grain was used to resin sludge at a low temperature, and the sludge of magnetic abrasive powder was synthesized and crushed into 200 meshes. Surface roughness was measured before and after polishing, and more than 38% of improvement of surface roughness was achieved when grain was used under a specific condition. Even though some degree of surface roughness due to deeper scratches still exist, but the result showed a prospective magnetic abrasive polishing using sludge with green carborundum grains.

## 1. Introduction

As the technology of industry is continuously developing, more precise and debris free parts are required in numerous manufacturing tools for food production, medical instrument, and semiconductor manufacturing. A processing method that relies on direct contact of tools to processing material has been widely used for most of applications, but this can create deformation and debris in a local area due to mechanical cutting. Numerous efforts have been made to avoid potential problems and improve the preciseness and cleanness, and one of them is magnetic abrasive

polishing method. Magnetic abrasive polishing utilizes magnetism that pulls a magnetic substance and enables to provide fine finishing. Many study for polishing tools and proper abrasive has been performed [1]-[9]: the polishing performance associated with magnitude of the magnetism and the placement of poles, developing abrasive for highly solid ceramic and a ultra high alloy, synthesize abrasive using D, iron oxide, and alumina. Since abrasive in magnetic abrasive polishing determines the precision and cleanness, developing effective abrasive and polishing method is a key to success.

In this experiment, sludge from steel

---

\* Department of Mechanical Engineering,  
Myongji University, 38-2 Nam-dong, Cheoin-gu, Yongin city, Gyeonggi Do 449-728, Korea

manufacturing was recycled as magnetic material. The sludge was processed with green carborundum grain at a low temperature and applied for the polishing of internal finishing of seamless stainless steel tube applying magnetic abrasive polishing. Recycling of sludge from steel industry is beneficial in terms of manufacturing cost and environmentally advantageous.

The ultimate goals of this study are;

- 1) increasing practical use of existing common lathe for fine polishing with a simple attachment of magnetic generator;
- 2) investigating proper process condition with minimum cost.

## 2. Experimental apparatus

### 2.1 Magnetic abrasion

A high gradient electromagnet whose maximum flux is 1.5 Tesla was employed, and the experiment was performed attaching to an existing common lathe. Figure 1 photo. of experimental equipment of magnetic polishing experimental set up. In order to easily control the air gap between poles and entity, poles were designed to be perpendicular to the sample for rectilinear motion.

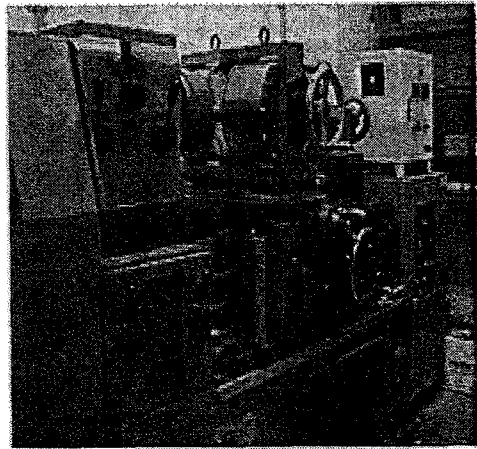


Fig.1 Photograph of experimental equipment of magnetic polishing

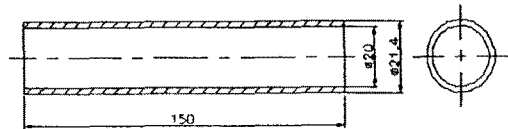


Fig. 2 Geometry and dimension of specimen

### 2.2 Magnetic abrasive and sample

Sludge and 1,000 meshes of green carborundum grains were used for magnetic material and abrasive, respectively. Each type of magnetic abrasive was synthesized to be approximately 30 meshes in granular structure. The compositions of magnetic abrasives are provided in Table 1. Sample material in this experiment is the seamless stainless steel tube, which is extensively used for the pressure parts of automotive systems. The geometry of the sample is presented in Figure 2. Surface roughness of samples was also measured before any polishing, and their averaged values are

ranges from 0.08 to 0.09  $\mu\text{m Ra}$ . An example of measured surface roughness is provided in Figure 3.

Table 1 Compositions of the mixture rate

Magnetic material	Sludge (Fe3O4)
Abrasive grain	GC
Composition	1 : 1
Resin	0.20 (ml/g)
Synthesis temperature	185 (°C)
Synthesis time	120 (minutes)
Average particle size	30 (meshes)

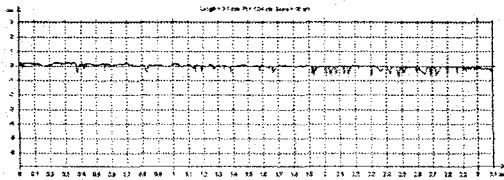


Fig. 3A surface roughness curve of internal face inseamlrss stainless steel tube.

Table 2 Polishing conditions

Work piece	Seamless stainless steel
Polishing speed	31.8, 54.9, and 63.6 (m/min)
Feed rate	0.15 (mm/rev)
Magnetic flux density	1,500, 3,000, and 6,000 (G)
Pass number	5 and 10 (times)
Grain type	Granular structure

### 2.3 Experimental method

As it is depicted in Figure 2, seamless

stainless steel tube was loaded on the magnetic abrasive polishing tool with 2mm of air gap between the outer surface of the tubes and poles. Then, a series of experiments was performed according to the polishing conditions provided in Table 2.

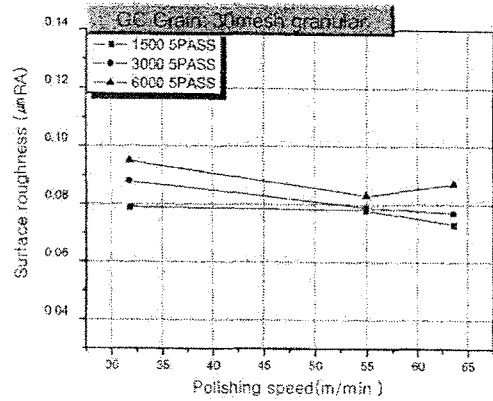


Fig. 4 (a) Surface roughness according to polishing condition (granular structure type magnetic abrasive: GC)

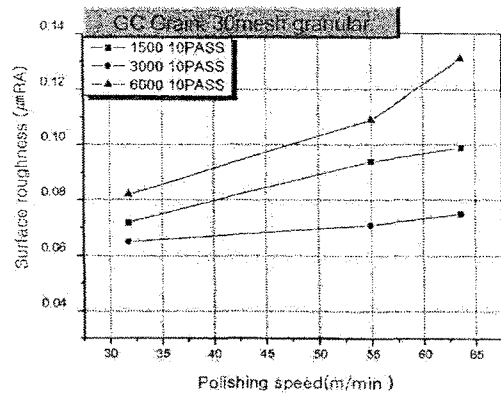


Fig. 4 (b) Surface roughness according to polishing condition (granular structure type magnetic abrasive: GC)

## 3. Result and discussion

The inter surface roughness of the tubes polished with white alumina grains of 30 meshes granular structure is presented in Figure 4(a),(b) As in the case of green carborundum in Figure 4(a),(b) the finest surface was achieved with the following condition; magnetic flux density=1500 G, polishing velocity=31.8 m/min, and five times repetitions of polishing. The surface roughness increased along the increment of magnetic flux density to 3000 G and 6000 G, and this implies that magnetic flux density does not always proportional to the degree of roughness. In other words, even with small amount of magnetic flux density, finer surface can be achieved when the polishing velocity is controlled within some degree such ring movement does not take place. When the polishing is repeated over 10 times at the velocity of 31.8m/min, minimum degree of roughness was obtained at 6000 G and the roughness increased in the order to 3000 G and 1500 G. This phenomenon is speculated that self agitation of strong magnetic brush occurred at 6000 G has effect on replacing existing abrasive grains with fresh ones and contributes to achieving mature polishing.

As it is illustrated in the figure, the when the polishing is repeated over 10 times,

finest polishing was achieved at 54.9 m/min with 3000 G and 31.8 m/min with either.

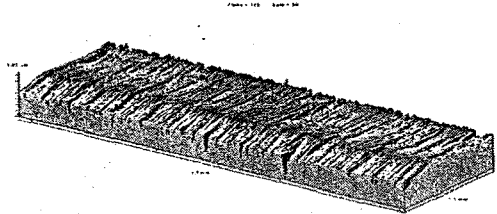


Fig. 5 Surface roughness profile after magnetic polishing(GC 31.8m/min, 1500G, 5pass)

Surface roughness profile after magnetic polishing with GC grains under the condition of 31.8 m/min, 1500 G, and 5 pass is presented in Figure 5. Comparing with the profile before any treatment, improved surface profile has been achieved. However, some amounts of deeper scratches still exist, and they are responsible for the averaged roughness of 0.065  $\mu\text{m Ra}$ .

#### 4. Conclusions

According to the study of magnetic abrasive polishing using sludge from steel manufacturing applying to the seamless stainless steel tube, we have the following three conclusions:

- 1) GC abrasive can provide satisfying amount of surface roughness under the

following process condition: magnetic flux density=1500 G, polishing velocity = 31.8 m/min. In addition, the polishing performance improves along the increment of magnetic flux density.

2) Sludge mixed with white alumina grains under the same polishing condition, and this shows a good potential as an abrasive.

3) Magnetic abrasive polishing has been successfully performed with the synthesis of either white alumina as abrasive and sludge as magnetic material.

## References

- (1) M. Anzai and T. Nakagawa, "Improve the Efficient of Magnetic Finishing," SEISAN KENKYU, Vol. 45, No. 12, pp. 816-820, 1993.
- (2) T. Shinmura and H. Yamaguchi, "Study on a New Internal Finishing Process by Applying Magnetic Abrasive Machining," Journal of JSME, Vol. 59, No. 560, pp. 293-299, 1993.
- (3) T. Shinmura, Y. Hamano, and H. Yamaguchi, "A New Precise Deburring Process for Inside Tubes by the Application of Magnetic Abrasive Maching", J. of JSME, Vol. 64, No. 620, pp.312-318, 1998.
- (4) T. Shinmura and T. Aizawa, "Study on Internal Finishing of a Non-ferromagnetic Tubing by Magnetic Abrasive Machining Process," Journal of JSPE, Vol. 54, No. 4, pp. 767-773, 1987.
- (5) M. Anzai, T. Sudo, and T. Nakagawa, "Development of Magnetic Abrasive and It's Finishing Characteristics," SEISAN KENKYU, Vol. 43, No. 11, pp. 13-22, 1991.
- (6) H.N. Kim, Y.K. Yun, and J.W. Shim, "Ultra Finishing by Magnet-abrasive Grinding for Internal-face of STS304 pipe," Proc. of the Korean Society of Precision Engineering Conference, Oct. 2001, pp.947-952.
- (7) H.N. Kim, Y.K. Yun, and J.W. Shim, "Super Precise Finishing of Internal-face in STS304 pipe Using The Magnetic Abrasive Polishing," Journal of the Korea Institute of Industrial Safety, Vol. 17, No. 3, pp. 30-35, 2002.
- (8) H.N. Kim, S.K. Song, Y.J. Chung, Y.K. Yun, H.W. Kim, S.W. Cho, and J.W. Shim, "Development of The Magnetic Abrasive Using Ba-Ferrite," Journal of the Korea Institute of Industrial Safety, Vol. 18, No. 2, pp. 46-49, 2003.
- (9) H.N. Kim, S.K. Song, Y.K. Yun, H.W. Kim, B.S. Kim, H.J. Ahn, and J.W. Shim, "The Effects of Ba-Ferrite Magnetic Abrasive Behavior on Polishing Characteristics," Proc. of the Korean Society of Precision Engineering Conference, Jun. 2003, pp. 565-568.