

Methanol Barriers Derived from Layer-by-Layer Assembly of Poly(ethersulfone)s for High Performance Direct Methanol Fuel Cells

Junglim Ok,^{†,§} Dong Wook Kim,[†] Changjin Lee,[†] Won Choon Choi,[‡] Sungmin Cho,[§] and Yongku Kang^{†,*}

[†]Advanced Materials Division and [‡]New Chemistry Research Division, Korea Research Institute of Chemical Technology, Daejeon 305-600, Korea. *E-mail: ykang@kriect.re.kr

[§]School of Chemical Engineering, Sungkyunkwan University, Suwon 440-746, Korea

Received November 15, 2007

Layer-by-layer assembled multilayers of poly(ethersulfone)s were deposited on the surface of Nafion membrane for the application of direct methanol fuel cells (DMFC). Aminated poly(ethersulfone) (APES) and sulfonated poly(ethersulfone) (SPES) were used as a polycation and a polyanion for fabrication of the multilayer films. UV/Vis absorption spectroscopy verified a linear build-up of the multilayers of APES and SPES on the surface of Nafion. Thin multilayer films deposited on the Nafion membrane enabled methanol permeability of the membrane to decrease by 78% in comparison with the pristine Nafion. The performance of DMFCs in concentrated methanol was highly enhanced by using the multilayer modified Nafion.

Key Words : Layer-by-layer self-assembly, Poly(ethersulfone), Nafion membrane, Direct methanol fuel cells, Methanol permeability

Introduction

Direct methanol fuel cell (DMFC) using a liquid methanol as a fuel is recently recognized as a promising candidate to compete with the conventional batteries for powering portable electronic devices.¹⁻⁶ In the heart of DMFC is the proton exchange membrane, Nafion, which is a fluorocarbon polymer electrolyte with perfluoroether sulfonic acid, serves as a typical membrane for DMFC because it has superior proton conductivity, thermal and chemical durability, and oxidative stability. However its high methanol crossover (methanol permeability through the membrane from anode to cathode) not only lowers the fuel efficiency but also decreases the open circuit voltage, resulting in a poor cell performance.^{7,8} Several attempts have been carried out to modify the Nafion membrane by blending with other polymers,⁹ incorporating inorganic fillers or particles,¹⁰ coating barrier films on the Nafion,^{11,12} and so on. Among them, we are interested in surface modification of Nafion by coating a thin barrier film through a layer-by-layer self assembly technique.


The layer-by-layer assembly is a unique coating method to deposit a thin multilayer film on a substrate by sequential electrostatic adsorption between the negatively and positively charged polyelectrolytes. The simple but highly versatile method allows us to tailor functionality of the films in accordance with our special needs and to control the film thickness in a nanometer regime. Many functional charged species can be applied for this technique, including functional polymers, clay platelets, inorganic nanoparticles, etc.^{13,14} In recent papers, one of the authors (D.W. Kim) reported ordered multilayer nanocomposites by the layer-by-layer self-assembly between delaminated clay nanoparticles and amphiphilic ionic polyacetylenes.^{15,16} The resulting ultrathin films deposited on Nafion membrane was found to

block transport of the water vapor through the membrane.¹⁶ In our recent experimental results, the multilayer films on the Nafion membranes were also found to be an efficient methanol barrier.¹² Methanol permeability was reduced to about half by the method.

In this work, we used poly(ethersulfone)s as a barrier to methanol transport because the polymer is known an efficient methanol barrier due to a rigid nature of the polymer backbone and also it exhibits good mechanical, thermal and chemical stabilities.^{17,18} We modified the poly(ethersulfone) by amination and sulfonation reaction in order to increase their proton conductivity and to impart charge nature for layer-by-layer deposition procedure. Then we coated a thin multilayer film on the Nafion using the aminated poly(ethersulfone) and the sulfonated poly(ethersulfone) by layer-by-layer method. Methanol permeability and proton conductivity of the modified Nafion membranes were measured and performance of DMFC based on the membrane was also investigated.

Experimental

Poly(ethersulfone) (Udel[®] P-3500, Amoco) was aminated by azidation of the lithiated poly(ethersulfone) and then consecutive reduction by NaBH₄.¹⁷ Sulfonated poly(ethersulfone) (SPES) was prepared by reacting chlorotrimethylsilane and chlorosulfonic acid with poly(ethersulfone) (see Scheme 1).¹⁸ Structure and degree of substitution of the functionalized poly(ethersulfone) were carefully characterized by means of NMR spectroscopy. Aminated poly(ethersulfone) (APES) was dissolved in dimethylformamide (DMF) at 2 wt% and then diluted 10 times with addition of deionized water, which was used for polycation solution in the layer-by-layer assembly. SPES was dissolved in DMF at 5 wt % and then diluted with deionized water to the

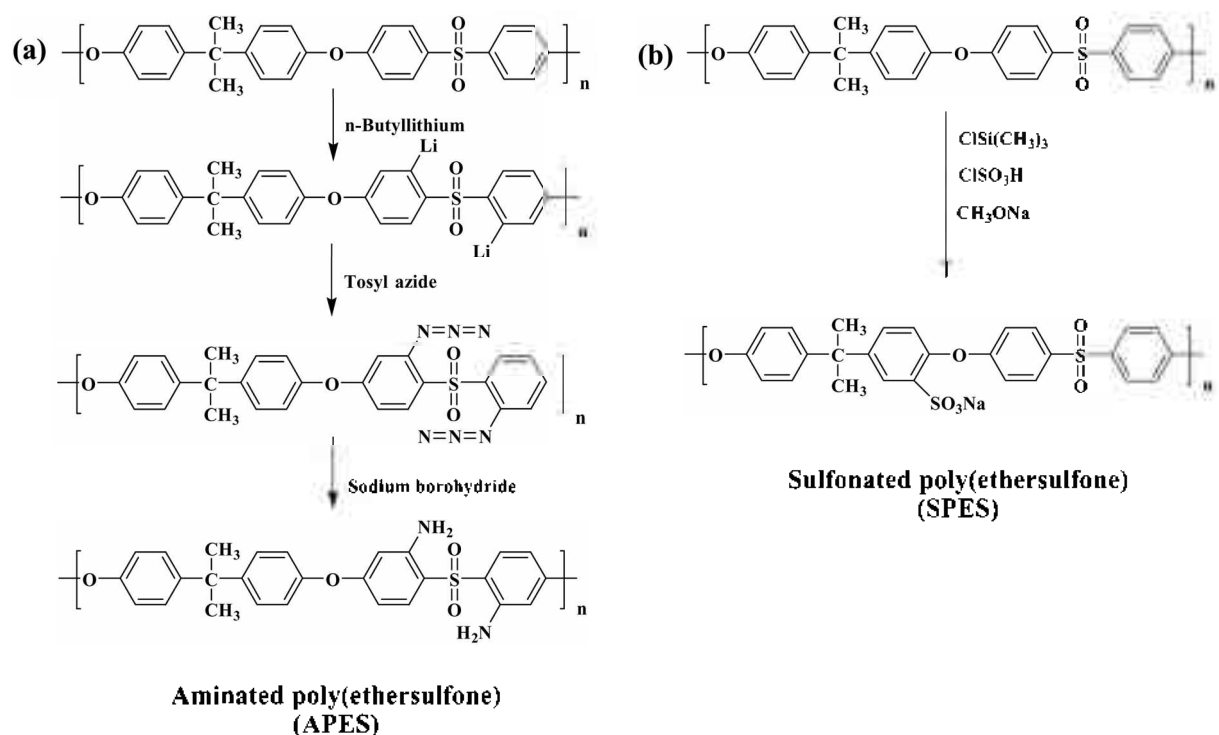

Scheme 1. Synthetic routes for (a) aminated poly(ethersulfone) (APES) and (b) sulfonated poly(ethersulfone) (SPES).

concentration of 1 wt%. The SPES solution was used for the polyanion.

Nafion membrane (Nafion[®] 115 from Aldrich, 127 μm thick) was treated by H_2O_2 and H_2SO_4 solution according to the previously reported procedures.¹⁹ The Nafion membrane was dipped in each APES and SPES solutions at room temperature for 10 min to deposit the multilayer films on the Nafion. After each dipping step, the membrane was rinsed with deionized water to remove weakly bound polyelectrolyte molecules. The layer-by-layer assembled membrane was finally rinsed with deionized water, followed by protonation in 1 M H_2SO_4 solution and then rinsed again with deionized water.

The build-up of APES/SPES multilayers on Nafion membranes was in-situ monitored by UV/Vis spectroscopy. TEM (model: TECNAI G², Phillips) equipped with Energy Dispersive X-ray Spectroscopy (EDXS) was used to examine the thickness and morphology of the multilayers.

Proton conductivity of the modified Nafion was measured in deionized water at room temperature using a four-probe conductivity cell equipped with impedance analyzer (4194A, Hewlett-Packard Co.).

Methanol permeability of the membrane was determined by RI-detector at 30 $^\circ\text{C}$ using a diffusion cell consisting of two compartments that were separated by the membrane. One compartment of the cell had a 2 M methanol solution in deionized water and the other compartment was filled with only deionized water. Solution in both cell compartments was stirred during the experiment.²⁰

To test performance of DMFCs, Pt-Ru (atomic ratio = 1:1) and Pt black catalyst (Johnson Matthey Co.) with a loading of

5 mg/cm^2 were used in each electrode. Catalyst ink, which was a mixture of the catalyst powder, Nafion solution (Aldrich, 5 wt% solution in lower aliphatic alcohols/water mixture), isopropyl alcohol, and water, was coated onto the polyimide films. The catalyzed layers were then transferred onto the Nafion membrane by the decal method.²¹ The catalyzed membrane was hot-pressed at 130 $^\circ\text{C}$ under a pressure of 6 MPa for 5 min. The geometrical area of the electrode was 4 cm^2 . The methanol solution (1, 5, 8 M) was fed to the anode side at 2 mL/min and the pure oxygen was supplied to the cathode at 500 mL/min.

Results and Discussion

Synthetic routes for the aminated poly(ethersulfone) and the sulfonated poly(ethersulfone) are described in Scheme 1. Poly(ethersulfone) was effectively aminated by successive reactions of lithiation of the ortho position to sulfonyl group in the polymer backbone, azidation with tosyl azide, and reduction by sodium borohydride. Degree of substitution (DS: the number of functional group in the repeating unit) in the aminated poly(ethersulfone) was estimated by comparing integral of the amine peak at 6.06 ppm with one of the aromatic protons peaks at 6.18–7.71 ppm in the ^1H NMR spectrum according to the literature.¹⁷ The DS was found to be 1.93. Sulfonation of the poly(ethersulfone) was performed by chlorotrimethylsilane and chlorosulfonic acid. Its DS was estimated 0.50 by comparing integral ratios of the aromatic protons at 6.93–7.82 ppm in ^1H NMR spectrum according to the literature.²²

APES and SPES solutions in the mixture of DMF and

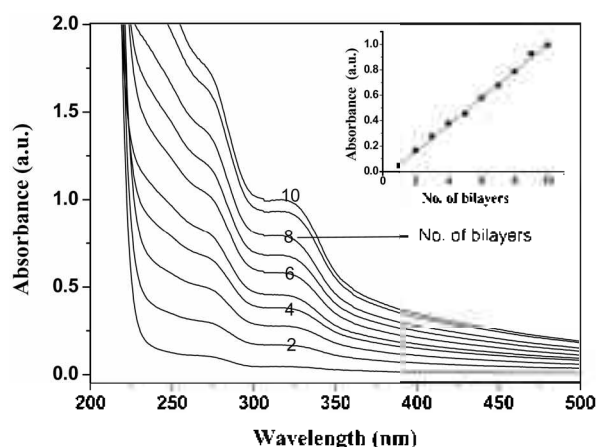


Figure 1. The UV/Vis absorption spectra of the Nafion membrane deposited with multilayers of APES and SPES by layer-by-layer assembly. The inset depicts the change of the absorbance at 325 nm as a function of the number of bilayers.

water were used to prepare the multilayer films on the Nafion membrane by layer-by-layer self-assembly technique. The sequential build-up of the oppositely charged polymers on the membrane was in-situ monitored by UV/Vis absorption spectroscopy as shown in Figure 1. The absorption spectra showed linear increase of the optical density at 325 nm, which was characteristic absorption band for APES. This indicated that the same amount of the polymers was deposited in every dipping cycle and the multilayers were deposited in a regular manner.

TEM equipped with EDXS was used to visually investigate the morphology and thickness of the 10 bilayers of APES and SPES on the surface of Nafion membrane. Figure 2(a) showed a cross-sectional image of the modified Nafion membrane embedded in epoxy resin, which was microtomed in a cryogenic environment. Figure 2(b) described EDXS line scan result, in which concentration profiles of fluorine and sulfur atoms between the points A and B in Figure 2(a) were displayed. The fluorine content abruptly increased as the EDXS line scan approached the point B, indicating that the point A belonged to the epoxy region and B to the Nafion. The dark narrow band between A and B must be the multilayers of APES and SPES containing lots of sulfur atoms since the concentration of sulfur was shown much higher over the region. TEM image in Figure 2(a) revealed that the 10 bilayers were approximately 300 nm thick, which corresponded to 30 nm per bilayer. Also the image indicated that the multilayers were deposited uniformly over the entire surface of the Nafion membrane.

Table 1 summarized the methanol permeability and ionic conductivity of the multilayer-deposited Nafion membranes together with those of the pristine membrane. Methanol permeability was reduced to 1.24×10^{-6} cm²/s for the 5 bilayer-deposited membrane and 3.81×10^{-7} cm²/s for the 10-bilayer-deposited membrane. The multilayers of the poly(ethersulfone)s take up only 0.2% or so of the total mass of membranes considering the thicknesses of the multilayers and the Nafion membrane (300 nm vs. 127 μ m). Our results

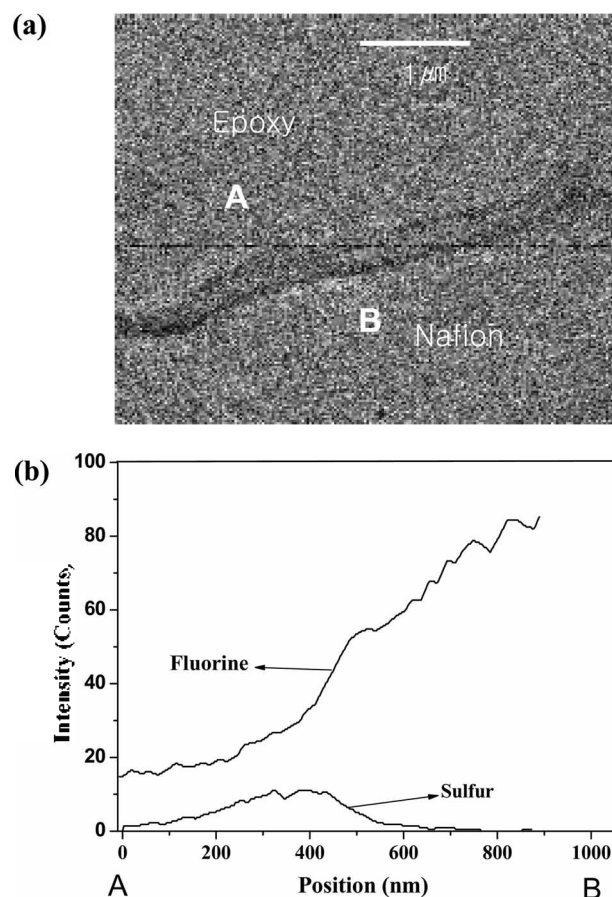


Figure 2. (a) TEM image of cross-section obtained by cryogenic microtoming the Nafion membrane deposited with 10 bilayers of APES and SPES, which was embedded in epoxy resin, and (b) The change of intensity of fluorine and sulfur content from epoxy region to Nafion obtained by EDXS line scan experiment.

Table 1. Methanol permeability and ionic conductivity of the pristine Nafion and the multilayer-deposited Nafion membranes


Samples	Methanol permeability (cm ² /s)	Ionic Conductivity (S/cm)
Pristine Nafion	1.74×10^{-6}	8.81×10^{-2}
5 bilayer-deposited Nafion	1.24×10^{-6}	6.4×10^{-2}
10 bilayer-deposited Nafion	3.81×10^{-7}	6.0×10^{-2}

indicated that such thin multilayers were an effective methanol barrier. The methanol permeability was dropped by 78% when it was compared to the pristine Nafion. Ion conductivity, however, was affected adversely by the multilayer deposition. The 10 bilayer-deposited membrane showed a 32% decrease in ionic conductivity than the pristine one. Being compared with the 78% decrease in methanol permeability, 32% drop in ionic conductivity was not much. Such relatively small decrease in ion conductivity would be because the sulfonated poly(ethersulfone) contained sulfonic acid that may serve as a proton conductor.

DMFC was prepared using the 10 bilayer-deposited Nafion membranes and its performance was compared with

Table 2. Open circuit voltage and maximum power density of the direct methanol fuel cells using the pristine Nafion and the 10 bilayer-deposited Nafion membranes at the feeding concentration of methanol of 1, 5, and 8 M and at the operating temperature of 30 and 60 °C

Feeding concentration of methanol		1 M		5 M		8 M	
Operating temperature		30 °C	60 °C	30 °C	60 °C	30 °C	60 °C
Open circuit voltage (mV)	Pristine Nafion	610	672	480	530	415	485
	10 bilayer-deposited Nafion	651	708	580	614	549	551
Maximum power density (mW/cm ²)	Pristine Nafion	32.45	89.5	10.43	31.05	7.65	18.59
	10 bilayer-deposited Nafion	44.55	92.88	29.64	58.9	18.9	39.65

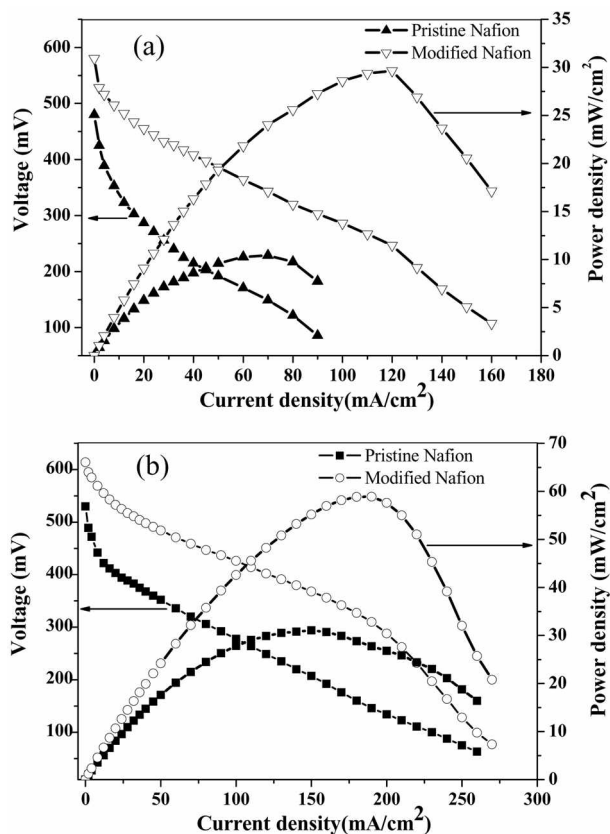**Figure 3.** The polarization curves of direct methanol fuel cells using the pristine Nafion and the 10 bilayer-deposited Nafion membranes (a) at 30 °C and (b) at 60 °C at the feeding concentration of methanol of 5 M.

one based on the pristine Nafion. Figure 3 showed the single cell performances of DMFCs prepared by the modified Nafion membrane and the pristine one by feeding 5 M methanol at 30 °C and 60 °C. The open circuit voltage was measured 480 mV at 30 °C and 530 mV at 60 °C for the cell using the pristine Nafion. With the Nafion membrane deposited by the 10 bilayers of poly(ethersulfone)s, the open circuit voltage increased to 580 mV at 30 °C and to 614 mV at 60 °C. The decrease in methanol crossover by the APES/SPES multilayers seemed to result in the higher open circuit voltage than the pristine Nafion by 21% at 30 °C and 16% at 60 °C. The maximum power density of the cells was much greatly affected by the modification of the membrane. The maximum power density jumped 2.8 times at 30 °C and 1.9 times at 60 °C compared to the pristine Nafion.

The cell performance was also measured at several different feeding concentrations of methanol as summarized in Table 2. In case of the pristine Nafion, the cell performance declines drastically as the methanol solution concentrates from 1 M to 8 M. This was because the methanol crossover in the pristine Nafion became severer at a higher methanol concentration and hence the performance of DMFC deteriorated. With the modified Nafion membrane, the cell performance became much better at higher methanol concentration. At 8 M, for example, the open circuit voltage of the cell based on the modified Nafion increased by 134 mV at 30 °C and 66 mV at 60 °C, and the maximum power density increased by 2.5 times at 30 °C and 2.1 times at 60 °C in comparison with the cell of the pristine Nafion. This result again showed that the APES/SPES multilayers were effectively deterring the methanol transport through the membranes and enhancing the cell performance.

In conclusion, we have demonstrated here that modification of Nafion membrane through layer-by-layer assembly of poly(ethersulfone)s has led to 2.8 times increase in maximum power density in DMFCs. The self-assembled multilayer was found to effectively prevent the methanol from migrating through the membrane by 78%. It is worthy of note that the layer-by-layer assembly method is a very simple procedure and the resulting films are as thin as 300 nm, but the effect is found to be substantial in terms of the cell performance.

References

- Kordesch, K.; Smader, G. *Fuel Cell and Their Applications*. WILEY-VCH: Weinheim, 1996.
- Bockris, J. O'M.; Srinivasan, S. *Fuel Cells: Their Electrochemistry*. McGraw-Hill Book Company: New York, 1969.
- DeLuca, N. W.; Elabd, Y. A. *J. Polym. Sci.: Part B: Polym. Phys.* **2006**, *44*, 2201.
- Han, S. K.; Hwang, J. K.; Han, O. H. *Bull. Korean Chem. Soc.* **2007**, *28*, 2442.
- Liu, J. G.; Zhou, Z. H.; Zhao, X. S.; Xin, Q.; Sun, G. Q.; Yi, B. L. *Phys. Chem. Chem. Phys.* **2004**, *6*, 134.
- Ye, Q.; Zhao, T. S.; Liu, J. G. *Electrochem. Solid-State Lett.* **2005**, *8*, A549.
- Kim, Y. J.; Choi, W. C.; Woo, S. I.; Hong, W. H. *Electrochim. Acta* **2004**, *49*, 3227.
- Mauritz, K.; Moore, R. *Chem. Rev.* **2004**, *104*, 4535.
- DeLuca, N. W.; Elabd, Y. A. *J. Membr. Sci.* **2006**, *282*, 217.
- (a) Libby, B.; Smyrl, W. H.; Cussler, E. L. *Electrochem. Solid State Lett.* **2001**, *4*, A197. (b) Miyake, N.; Wainright, J. S.; Savinell, R. F. *J. Electrochem. Soc.* **2001**, *148*, A905.

11. (a) Hobson, L. J.; Ozu, H.; Yamaguchi, M.; Hayase, S. *J. Electrochem. Soc.* **2001**, *148*, A1185. (b) Jiang, S.; Liu, Z.; Tian, Z. Q. *Adv. Mater.* **2006**, *18*, 1068. (c) Tang, H.; Pan, M.; Jiang, S.; Wan, Z.; Yuan, R. *Colloids Surf. A: Physicochem. Eng. Aspects* **2005**, *262*, 65.
 12. Kim, D. W.; Choi, H. S.; Lee, C.; Blumstein, A.; Kang, Y. *Electrochim. Acta* **2004**, *50*, 659.
 13. (a) Decher, G. *Science* **1997**, *277*, 1232. (b) Decher, G.; Eekle, M.; Schmitt, J.; Struth, B. *Current Opin. Colloid Interface Sci.* **1998**, *3*, 32. (c) Decher, G.; Schlenoff, J. B. *Multilayer Thin Films*; WILEY-VCH: Weinheim, 2003.
 14. (a) Hong, J. D.; Park, E. S.; Park, A. L. *Bull. Korean Chem. Soc.* **1998**, *19*, 1156. (b) Kumar, S. K.; Park, J. K.; Hong, J. D. *Langmuir* **2007**, *23*, 5093.
 15. (a) Kim, D. W.; Blumstein, A.; Kumar, J.; Samuelson, L. A.; Kang, B.; Sung, C. *Chem. Mater.* **2002**, *14*, 3925. (b) Kim, D. W.; Kumar, J.; Blumstein, A. *Appl. Clay Sci.* **2005**, *30*, 134.
 16. Kim, D. W.; Ku, B. C.; Steeves, D.; Nagarajan, R.; Blumstein, A.; Kumar, J.; Gibson, P. W.; Ratto, J. A.; Samuelson, L. A. *J. Membr. Sci.* **2006**, *275*, 12.
 17. (a) Guiver, M. D.; Robertson, G. P. *Macromolecules* **1995**, *28*, 94. (b) Guiver, M. D.; Robertson, G. P.; Foley, S. *Macromolecules* **1995**, *28*, 7612.
 18. Nolte, R.; Ledjef, K.; Bauer, M.; Mulhaupt, R. *J. Membr. Sci.* **1993**, *83*, 211.
 19. Lewis, F. A. *Int. J. Hydrogen Energy* **1996**, *21*, 461.
 20. Tricoli, V. *J. Electrochem. Soc.* **1998**, *145*, 3798.
 21. Wilson, M. S.; Gottesfeld, S. *J. Appl. Electrochem.* **1992**, *22*, 1.
 22. Noshay, A.; Robeson, L. M. *J. Appl. Polym. Sci.* **1976**, *20*, 1885.
-