

Effects of Reaction Conditions on Cobalt-Catalyzed Fischer-Tropsch Synthesis: Interactions between Operating Factors

Hossein Ajamein, Majid Sarkari, Farhad Fazlollahi, and Hossein Atashi*

*Department of chemical engineering, Faculty of engineering, University of Sistan & Baluchestan, P.O. Box 98164-161, Zahedan, Iran. *E-mail: h.ateshy@hamoon.usb.ac.ir*
(Received June 19, 2011; Accepted August 19, 2011)

ABSTRACT. In Fischer-Tropsch Synthesis, because of few reactants (H_2 , CO), scarce operating parameters affected on efficiency especially the selectivity of products. In this research, effect of operating parameters on the selectivity of Co-Mn-TiO₂ Fischer-Tropsch synthesis catalyst were studied by design of experimental procedure and Taguchi method. According to this research, interactions between operating factors have a crucial effect on light products selectivity. Among these interactions, (temperature \times feed ratio) has the main influence on light hydrocarbons selectivity. It was concluded that temperature and feed ratio (H_2/CO) were the most integral operating parameters for much greater selectivity of light hydrocarbons.

Key words: Fischer-Tropsch synthesis, Operating parameters, Taguchi method

INTRODUCTION

Fischer-Tropsch synthesis (FTS) reaction is a process in which syngas is converted to a variety of products including light gas and heavy hydrocarbons.¹ Because FTS is a surface reaction, the conversion of synthesis gas over a catalyst is the most noticeable step. As a result, catalyst selection seems to be very important. Recently, Co-Mn catalyst has received enormous attention because of higher olefin and middle distillation cut selectivity. Furthermore, it has been revealed that cobalt based catalysts are specifically greater than iron based catalysts in catalyst life. Another contrast between them is water gas shift reaction that is overlooked in cobalt based catalysts.^{2,3}

Dwindling the petroleum reservoirs worldwide and FTS environmental prominence have caused extensive researches on the Fischer Tropsch synthesis. In most cases, they emphasized on catalyst manufacturing and optimization,^{4,5} kinetic modeling,⁶⁻⁸ mechanism⁹ and reactor modeling.^{10,11} Meanwhile, a little attention has been allocated to the effect of operating parameters on reactor design and selectivity of products over cobalt based catalysts. Temperature, pressure and feed gas composition have been mainly mentioned as significant effects on selectivity of FTS products.¹ Dry (1974) declared that temperature effect on selectivity is not manifest and self sufficient. But it depends somewhat on type of catalyst and other process conditions. He implied that if process and catalyst were set up for wax production, an increase in temperature would lower the selectivity of desired product. But for

light hydrocarbons, temperature is not an influential factor. He also expressed that gas composition has different effect in diverse situation like temperature. It is the dominant factor to control selectivity for fixed bed wax producing catalysts while the pressure is not important.¹² Thereafter in 2002, he announced that increasing temperature raises the selectivity of methane in Co-based catalysts. Therefore increasing feed ratio (H_2/CO) shifts the selectivity to lighter and more saturated hydrocarbons.¹³

In other research, optimum values for temperature and feed ratio (H_2/CO) were proposed due to parabolic trend of products selectivity. In other words, the selectivity of products in lower extent is slight, then it trends to high values and eventually it decreases again. They interpreted that in low temperature due to slight mobility of reactant molecules, most of them have not chance to increase their chain length to convert to methane. But in high temperature they are more energetic and selectivity of long chain products rises as CH_2 intermediate production increases.^{14,15}

Among these researches, there is no one that probes the optimum values of operating parameters and surveys the effect of interactions between these parameters by experimental design methods. The experimental design is widely used to optimize process parameter values in order to improve the quality properties of a product for example. Conventional experimental design methods are generally complex and do not always reach the desired objectives. Moreover, these methods require a large number of experiments when the number of process parameters increases.¹⁶

Taguchi's method makes use of an experimental process for finding an optimal design. In Taguchi methods, variables or factors are arranged in an orthogonal array (OA) to minimize the number of tests. Taguchi methods can rapidly and accurately acquire technical information to design and produce low-cost, highly reliable products and processes.¹⁷ Its most advanced applications allow engineers to develop flexible technology for the design and production of families of high quality products, greatly reduce research and development, and delivery time.¹⁸

In this study an inexpensive and easy-to-operate experimental strategy based on Taguchi's parameter design has been adopted to investigate the effect of various parameters and their interactions. This procedure has been successfully applied for parametric appraisal in different process optimization problems. In addition, the analysis of variance (ANOVA) is done to identify the most significant control factors and their interactions.

MATERIALS AND METHODS

Catalyst preparation

In this research the optimal supported cobalt manganese sample was prepared by co-precipitation method as follows. Aqueous solutions of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (0.5 M) (99%, Merck) and $\text{Mn}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$ (0.5 M) (99%, Merck) with different molar ratios were pre-mixed and the resulting solutions was heated to 70 °C in a round bottomed flask fitted with a condenser. Aqueous Na_2CO_3 (0.5 M) (99.8%, Merck) was dropwise added to the mixed nitrate solution with stirring while the temperature was maintained at 70 °C until $\text{pH } 8 \pm 0.1$ was achieved. The resulting precipitate was then left in this medium for times ranging from 0 to 240 min. The aged precipitate was then filtered and then washed several times with warm distilled water. Then, in order to prepare TiO_2 supported catalyst, the optimal amount of 30% wt of TiO_2 based on the total catalyst weight was added to the mixed solution of cobalt and manganese nitrates with the molar ratio of 25%Co/75%Mn and then filtered, washed, dried in an oven at 120 °C for 16 hours to give a material denoted as the catalyst precursor and calcined in static air in a furnace at 500 °C for 16 hours.

Powder X-ray diffraction (XRD) measurements were carried out using a Bruker axs Company, D8 Advance diffractometer (Germany). The actual phases identified for catalyst precursor were MnCO_3 (rhombohedral) and $\text{Co}(\text{OH})_2$ (hexagonal), and for calcined catalyst were Co_3O_4 (cubic), $(\text{Co},\text{Mn})(\text{Co},\text{Mn})_2\text{O}_4$ (tetragonal), MnO_2 (tetragonal and

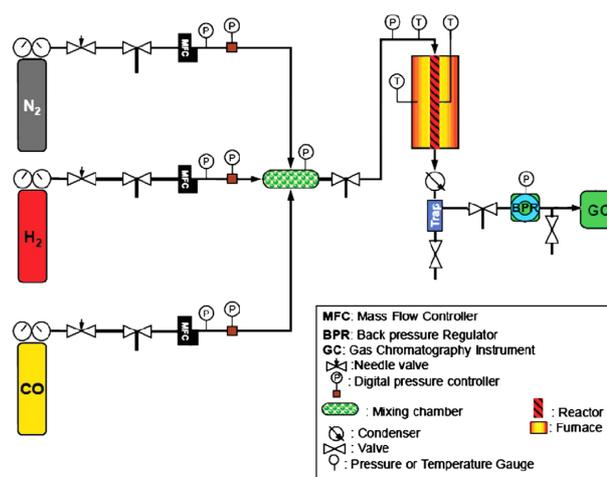


Fig. 1. Schematic diagram of the reactor used.

orthorhombic), CoMnO_3 (rhombohedral) and TiO_2 (tetragonal).

Catalytic performance

A schematic representation of the experimental setup is shown in Fig. 1. Fischer-Tropsch synthesis was carried out in a fixed-bed micro-reactor made of stainless steel with an inner diameter of 12 mm. Three mass flow controllers (Brooks, Model, 5850E) were used to adjust automatically flow rate of the inlet gases comprising CO, H_2 and N_2 (purity of 99.999%). Mixture of CO, H_2 and N_2 was subsequently introduced into the reactor, which was placed inside a tubular furnace (Atbin, Model, ATU 150-15). Temperature of reaction was controlled by a thermocouple inserted into catalytic bed and visually monitored by a computer. Prior to the catalytic activity measurements, the samples were crushed, sieved (mesh size: 0.1-2.5 mm) and then was held in middle of the reactor using quartz wool. The catalyst was in situ pre-reduced at atmospheric pressure under H_2 - N_2 flow ($\text{N}_2/\text{H}_2=1$, flow rate of each gas= 30 ml/min), at 400 °C for 16 hours. It consists of an electronic back pressure regulator which can control the total pressure of the desired process using a remote control via the TESCOM software package integration that improves or modifies its efficiency that capable for working on pressure ranging from atmospheric pressure to 100 bar. In each test, 1.0 g catalyst was loaded and the reactor operated about 12 hours to ensure steady state operations were attained.

A small portion of the reactor effluent was sent to gas chromatograph (GC) for on-line analysis. The Varian Technologies CP-3400 gas chromatograph equipped with a 10-port sampling valve (Supelco Company, USA, Visi Model),

flam ionization detector (FID) and thermal conductivity detector (TCD) and a capillary column for separating compounds. The contents of sample loop were injected automatically into a packed column (Hayesep DB, Altech Company, USA, 1/8" OD, 10 meters long, and particle mesh 100/120). Helium was employed as a carrier gas for optimum sensitivity (flow rate=30 ml/min). The calibration was carried out using various calibration mixtures and pure compounds obtained from American Matheson Gas Company (USA). GC controlling and collection of all chromatograms were done via an IF-2000 Single channel data interface (TG Co, Tehran, Iran) at windows® environment.

Design of Experiments procedure

The steps of the Taguchi experimental design are: (a) to select the output variable(s) (response(s)) to be optimized; (b) to identify the factors (input variables) affecting output variable(s) and to choose the levels of these factors; (c) to select the appropriate orthogonal array; (d) to assign factors and interactions to the columns of the array; (e) to perform experiments; at this step it is important to randomize the trials in order to minimize the systematic error; (f) to analyze the results using analysis of variance (ANOVA); (g) to determine the optimal process parameters; (h) to perform confrmatory experiments, if it is necessary.¹⁹

In this study, Taguchi experimental design was employed for analyzing the influence of operating parameters and their interactions on selectivity of Fischer Tropsch synthesis products. Therefore, 3 control factors were considered: (A) Temperature, (B) pressure and (C) feed ratio (H₂/CO). For each factor two levels were chosen. The control factors and their levels are summarized in *Table 1*. Three interaction between temperature & pressure (A×B),

Table 1. Control factors and their levels

Factors	Level 1	Level 2
A: Temperature	250	260
B: Pressure	4	12
C: Ratio (H ₂ /CO)	1	1.5

temperature & ratio (A×C) and pressure & ratio (B×C) were assessed. According to Taguchi method, the L₈ orthogonal array with 3 main factors at 2 levels each and three interactions were adopted for the study. It signifies that Taguchi procedure suggested eight tests for applying the desired responses. Because we wanted to assess the effects of main factors and their interactions on selectivity of methane, ethane, ethylene, propane and propylene as Fischer-Tropsch synthesis products, we had to integrate all responses to one as is explained in.¹⁹

RESULTS AND DISCUSSIONS

Two experimental designs were utilized to understand whether interaction effects are important or not. In the first the interaction effects were ignored. So the Taguchi method suggested a L₉ orthogonal array matrix for tests. *Table 2* shows the L₉ matrix and the integral responses for each test for the first design which interaction effects were ignored. By following the Taguchi method steps an ANOVA table for first design was achieved which is illustrated in *Table 3*.

According to *Table 3* the error value is 66.735% which is much more than the criteria value which is 15%. In such a case, when the error value is more than 15%, it can be concluded that an important factor or interaction effects are disregarded. Therefore in the second design interac-

Table 2. Factor settings for Taguchi L₉ design and integrated responses for the first design

Experiment Number	Factors			Integrated Response
	Temperature (A)	Pressure (B)	Feed Ratio (C)	
1	1	1	1	35.74
2	2	2	1	31.53
3	1	3	3	42.02
4	2	1	2	25.62
5	2	3	3	27.78
6	2	3	1	71.65
7	3	1	3	31.77
8	3	2	1	40.09
9	3	3	2	28.78

Table 3. ANOVA analysis for the first design (without interaction effects consideration)

Factors	DOF	SS	Variance	F-Ratio	P %
A: Temperature	2	111.205	55.632	0.36	0
B: Pressure	2	468.433	234.216	1.518	10.29
C: Ratio (H ₂ /CO)	2	665.373	332.686	2.156	22.97
Error	2	308.493	154.246	-	66.735
Total	6	1553.504			100

Table 4. Factor settings for Taguchi L₈ design and integrated responses

Experiment Number	Column number, position of the factors, interactions and levels							Integrated Response
	1	2	3	4	5	6	7	
	A	B	A×B	C	A×C	B×C	empty	
1	1	1	1	1	1	1	1	32.38
2	1	1	1	2	2	2	2	35.22
3	1	2	2	1	1	2	2	30.98
4	1	2	2	2	2	1	1	39.03
5	2	1	2	1	2	1	2	64.75
6	2	1	2	2	1	2	1	26.1
7	2	2	1	1	2	2	1	61.72
8	2	2	1	2	1	1	2	27.44

tion effect was exerted.

In this case, the factor settings for Taguchi L₈ design and integrated responses are tabulated in Table 4. Now with regard to these responses, the analysis of variance (ANOVA) is applied in order to test the equality of several means, resulting in what process parameters (factors or interactions) are statistically significant.

The results of ANOVA are presented in a table that displays for each factor (or interaction) the values of:

· SS_i: sum of squares of each factor.

$$SS_i = \sum_{i=1}^n y_i$$

· Total sum of squares (S_T): sum of squared deviations from the mean.

$$S_T = \sum_{i=1}^n (y_i - \bar{y}_i)^2$$

· DOF: degree of freedom which is the number of levels for each factor minus 1.

· Variance: division of sum of squared over degree of freedom of each factor.

$$V_i = \frac{SS_i}{DOF_i}$$

· F: F is the ratio between the mean of squares effect and the mean of squares error.

$$F_i = \frac{V_i}{V_{Error}}$$

F-test is used to see the significance of each factor (or interaction) on the response variable.

· P: P is the probability value which gives the degree of confidence at which the factor (or interaction) is significant.

$$P_i = \frac{SS'_i}{S_T}$$

· Pure Sum (SS'_i):

$$SS'_i = SS_i - (V_{Error} - DOF_i)$$

Fig. 2 illustrates the mean average of main factors and interactions. The order of operating parameters and their interaction on the target function is as follows:

- 1) Interaction A×C (Temperature × Ratio)
- 2) Ratio (H₂/CO)
- 3) Temperature
- 4) Interaction B×C (Pressure × Ratio)
- 5) Interaction A×B (Temperature × Pressure)
- 6) Pressure

In this design the error value of 0.038% is much lower than the criterion value 15%. So it can be deduced that for this design interaction effects especially A×C have a crucial effect on integrated responses. In ANOVA table, for a degree of freedom of 1 for the numerator (effect) and 1 for the denominator (error), the factor is significant with 95% confidence if F exceeds 161.45, and with 90% confidence for F higher than 39.864.¹⁹ Thus, the values of F in the ANOVA of integrated response for selectivity (Table 4) confirm that the interaction (Temperature × Ratio), and in a lower extent ratio (H₂/CO) and temperature had a significant effect on selectivity as shown in Fig. 2. The result from Taguchi analysis demonstrated the optimum process conditions in Table 5. For this optimum test the evaluated value for integrated response is 65.032.

CONCLUSIONS

The effect of operating parameters such as temperature, pressure and feed ratio (H₂/CO) on selectivity of light FTS

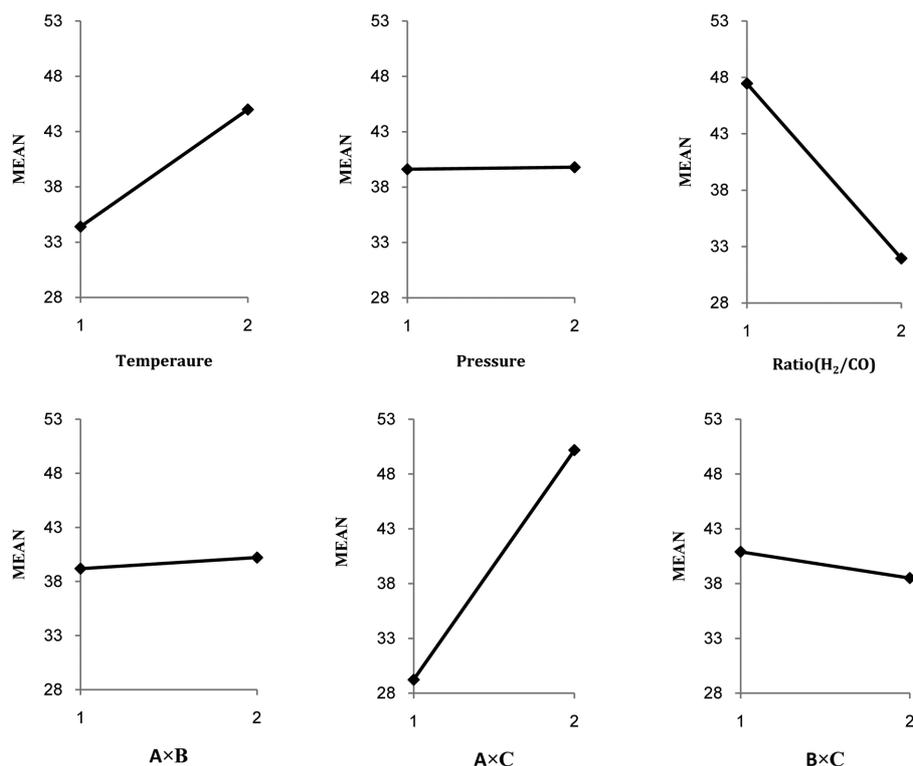


Fig. 2. Analysis of effects of control factors and interactions on mean response.

Table 5. ANOVA analysis

Factors	DOF	SS	Variance	F-Ratio	Pure sum	P %
A: Temperature	1	224.720	224.720	2586.926	224.633	14.059
B: Pressure	1	0.065	0.065	0.752	0.000	0.000
A×B	1	2.101	2.101	24.195	2.014	0.126
C: Ratio (H ₂ /CO)	1	481.120	481.120	5538.531	481.033	30.106
A×C	1	878.224	878.224	10109.888	878.137	54.959
B×C	1	11.471	11.471	132.056	11.384	0.712
Error	1	0.086	0.086			0.038
Total	7	1597.790				100

Table 6. Optimum operating parameters

Factors	Level
Temperature	270
Pressure	12
Ratio (H ₂ /CO)	1

products were investigated by Taguchi method. From ANOVA table, as a result of Taguchi method, the interaction A×C (Temperature × Feed Ratio) had the main effect on C₂ and C₃ hydrocarbons selectivity. P-values demonstrate that feed ratio and temperature are the further important parameters. According to the Taguchi method, the best temperature, pressure and feed ratio for the most

values of selectivity for light hydrocarbons are 270 °C, 12 bar and H₂/CO=1, respectively.

Acknowledgments. The authors gratefully acknowledge the financial support of this work by University of Sistan and Baluchestan Research Council.

REFERENCES

1. Steynberg, A. P. *Studies in Surface Science and Catalysis*, 152; Steynberg, A. P.; Dry, M., Eds.; Elsevier, Amsterdam, 2004.
2. Keyser, M. J.; Everson, R. C.; Espinoza, R. L. *Ind. Eng. Chem.* **2000**, *39*, 48.
3. Zakeri, M.; Samimi, A.; Khorram, M.; Atashi, H.; Mirzaei,

- A. *Powder Technol.* **2010**, *200*, 164.
4. Keyser, M. J.; Everson, R. C.; Espinoza, R. L. *Appl. Catal., A: General.* **1998**, *171*, 99.
5. Feyzi, M.; Irandoust, M.; Mirzaei, A. A. *Fuel Process. Technol.* **2011**, *92*, 1136.
6. Atashi, H.; Siami, F.; Mirzaei, A.; Sarkari, M. *J. Ind. Eng. Chem.* **2010**, *16*, 952.
7. Sari, A.; Zamani, Y. Sayyed and Taheri, A. *Fuel Process. Technol.* **2009**, *90*, 1305.
8. Gideon Botes, F.; van Dyk, B.; McGregor, C. *Ind. Eng. Chem. Res.* **2009**, *48*, 10439.
9. H. Davis, B., *Catal. Today* **2009**, *141*, 25.
10. Guettel, R.; Turek, T. *Chem. Eng. Sci.* **2009**, *64*, 955.
11. Wang, Y. N.; Xu, Y. Y.; Li, Y. W.; Zhao, Y. L.; Zhang, B. *J. Chem. Eng. Sci.* **2003**, *58*, 867.
12. Dry, M. E. *Ind. Eng. Chem., Prod. Res. Dev.* **1976**, *15*, 282.
13. Dry, M. E. *Catal. Today* **2002**, *71*, 227.
14. Mirzaei, A.; Faizi, M.; Habibpour, R. *Appl. Catal., A: General.* **2006**, *306*, 98.
15. Mirzaei, A. A.; Habibpour, R.; Faizi, M.; Kashi, E. *Appl. Catal., A: General.* **2006**, *301*, 272.
16. Rao, R. S.; Kumar, C. G.; Prakasham, R. S.; Hobbs, P. J. *Biothech. J.* **2008**, *3*, 510.
17. Byrne, D. M.; Taguchi, S. *Quality Progress.* **1987**, *20*, 19.
18. Antony, J.; Kaye, M.; Frangou, A. *TQM Magazine.* **1998**, *10*, 169.
19. Roy, R. K. *Design of Experiments Using Taguchi Approach: 16 steps to Product and Process Improvement*; John Wiley & Sons: New York, 2001.
-