

• Original Article

Effects of Water Chemistry on Aggregation and Soil Adsorption of Silver Nanoparticles

Sujin Bae, Yu Sik Hwang, Yong-Ju Lee, Sung-Kyu Lee

Future Environmental Research Center, Korea Institute of Toxicology, Jinju, Korea

Objectives In this study, we investigated the influence of ionic strength and natural organic matter (NOM) on aggregation and soil adsorption of citrate-coated silver nanoparticles (AgNPs).

Methods Time-resolved dynamic light scattering measurements and batch adsorption experiments were used to study their aggregation and soil adsorption behaviors, respectively.

Results The aggregation rate of AgNPs increased with increasing ionic strength and decreasing NOM concentration. At higher ionic strength, the AgNPs were unstable, and thus tended to be adsorbed to the soil, while increased NOM concentration hindered soil adsorption. To understand the varying behaviors of AgNPs depending on the environmental factors, particle zeta potentials were also measured as a function of ionic strength and NOM concentration. The magnitude of particle zeta potential became more negative with decreasing ionic strength and increasing NOM concentration. These results imply that the aggregation and soil adsorption behavior of AgNPs were mainly controlled by electrical double-layer repulsion consistent with the Derjaguin-Landau-Verwey-Overbeek theory.

Conclusions This study found that the aggregation and soil adsorption behavior of AgNPs are closely associated with environmental factors such as ionic strength and NOM and suggested that assessing the environmental fate and transport of nanoparticles requires a thorough understanding of particle-particle interaction mechanisms.

Keywords Aggregation, Ionic strength, Natural organic matter, Silver nanoparticles, Soil adsorption

Correspondence:Yu Sik Hwang, PhD
17 Jegok-gil, Munsan-eup, Jinju
660-844, Korea
Tel: +82-55-750-3834
Fax: +82-55-750-3799
Email: yshwang@kitox.re.kr

Received: June 25, 2012

Accepted: October 8, 2012

Published online: May 7, 2013

This article is available from: <http://e-eh.ohg/>

Introduction

With the advancement of nanotechnology, the use of nanomaterials is rapidly increasing in a multitude of fields (electronics, cosmetics, biotechnology, material science, etc.) [1]. In particular, silver nanoparticles (AgNPs) are widely used in consumer products such as electronics, household, nursery products and textiles because of their unique antibacterial activity [2,3]. According to the report by the Woodrow Wilson International Center for Scholars [4], AgNPs are the most commonly used nanomaterials. As the use of consumer products containing AgNPs becomes widespread, AgNPs will eventually be released into the environment. For example, upon washing textiles em-

bedded with AgNPs, the AgNPs can be released into water [5,6]. Also, it was found that the AgNPs from paints used for outdoor applications can be released into the surrounding environment by rain events [7]. Potential introduction of AgNPs into the environment has motivated intensive study on the potential toxicity of AgNPs on the ecosystem [2,8-10]. However, relatively little is known for the fate and transport of AgNPs in the environment, which is equally essential to their risk assessments [11,12].

Environmental fate and transport of nanoparticles can be significantly influenced by aggregation in water and adsorption onto the soil matrix [13,14]. Aggregation of nanoparticles, causing an increase of particle size, can typically lead to sedimenta-

tion and thereby decrease of nanoparticle concentration in water [15] and can have a significant effect on their chemical reactivities (or toxicity) [16,17]. In addition, nanoparticles can be adsorbed (or deposited) onto solid surfaces, which can reduce the transport and bioavailability of nanoparticles [15]. Therefore, a thorough understanding of aggregation and soil adsorption behaviors involved in the fate and transport of nanoparticles is an essential step for accurate prediction of their potential risks to human health and the environment.

In general, it is known that aggregation and soil adsorption behaviors of nanoparticles depend on their physicochemical properties and solution chemistry [11,14,18]. Several studies have investigated the effects of the types of AgNPs (i.e., coating types) as well as solution chemistry (i.e., salt type and concentration) on their aggregation behaviors [11,19]. However, there

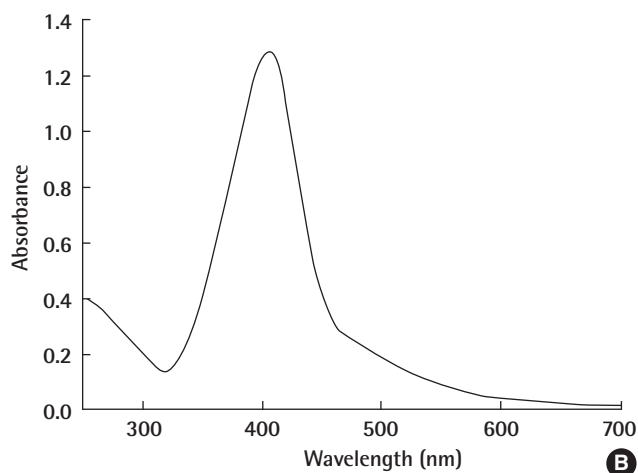
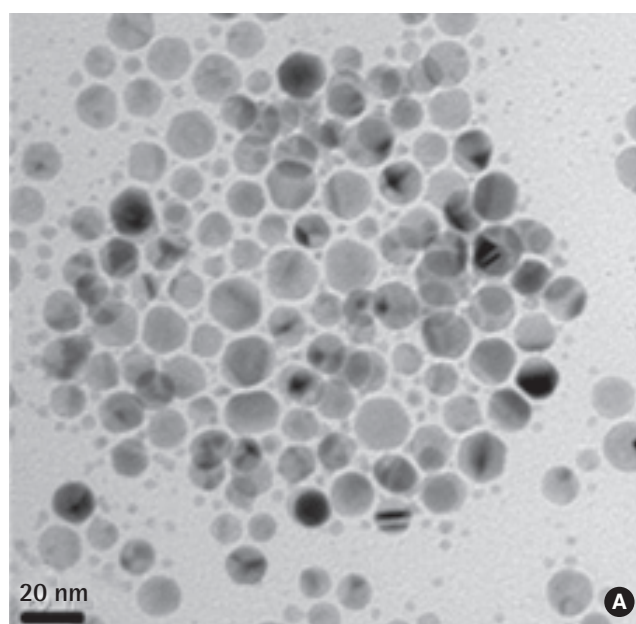


Figure 1. (A) Transmission electron microscopy image, (B) Ultraviolet-visible absorption spectrum of silver nanoparticles.

is relatively a lack of research on soil adsorption of AgNPs. In particular, little is known about the influence of environmental parameters on simultaneous particle aggregation and soil adsorption. In addition, it is not clear whether the currently available guidelines for the soil adsorption testing of chemicals (e.g., Organization for Economic Cooperation and Development (OECD) Test Guideline 106 [20]) are applicable to nanoparticles or not.

The purpose of this study is to assess how environmental parameters such as ionic strength and natural organic matter (NOM) can influence the aggregation and soil adsorption of citrate-coated AgNPs. The aggregation and soil adsorption of AgNPs were tested using time-resolved dynamic light scattering (TR-DLS) and batch adsorption method, respectively, at sodium nitrate (NaNO_3) solutions and in both the presence and absence of humic acid.

Materials and Methods

Materials

Citrate-coated AgNPs were obtained from ABC Nanotech (Daejeon, Korea) and used without further purification. According to the vendor-supplied specification, the arithmetic mean particle diameter was 13.3 nm. Transmission electron microscopy (TEM) (Tecnai G2 F30 S-Twin, Eindhoven, Netherlands) imaging of the AgNPs showed that these nanoparticles are in reasonable agreement with the manufacturer's specifications (Figure 1A). Ultraviolet-visible (UV/Vis) absorbance spectrum (Lambda 25 UV/Vis spectrometer; PerkinElmer Life and Analytical Sciences, New York, NY, USA) of the AgNPs showed a maximum peak at 405 nm, which agrees with previously published results (Figure 1B) [21].

NaNO_3 (99%, Sigma-Aldrich, Missouri, MO, USA) and humic acid (Sigma-Aldrich) were used to evaluate the influence of ionic strength and NOM, respectively. All aqueous samples were prepared using high performance liquid chromatography (HPLC)-quality distilled water (B&J HPLC Certified Solvent).

Soil used for adsorption studies was sampled from a rice paddy field in Daejeon, Korea. The soil was air-dried for 7 days, after which it was crushed in a mortar and passed through a 2 mm

Table 1. Physicochemical properties of soil for adsorption test

pH (in 10 mM CaCl_2)	CEC ^a (mEQ/100 g)	Organic carbon content ^b (%)	Clay content (%)	Soil texture
4.52	13.46	1.20	18.75	Sandy loam

CEC, cation exchange capacity.

^aMeasured by the 1N-ammonium acetate method; ^bMeasured by the Tyurin method.

sieve and kept at room temperature before use. Table 1 shows the physicochemical properties of soil used in this study.

Aggregation Kinetics

The aggregation kinetics of AgNPs in various solution conditions were characterized by monitoring the hydrodynamic diameters (D_h) as a function of time through TR-DLS. In order to evaluate the effect of ionic strength on aggregation, 0.1 mL of the AgNPs stock suspension (100 mg/L) was transferred to a disposable cuvette (Kartell, Milan, Italy) and the appropriate amount of NaNO_3 and distilled water were added to achieve the desired electrolyte concentration. The final volume of the suspension was 1 mL with a final AgNPs concentration of 10 mg/L. The resulting solution was gently shaken. Then the D_h of the AgNPs was measured at 25°C for 90 minutes at intervals of 15 seconds using the ZetaSizer Nano ZS (Malvern Instruments Inc., Worcestershire, UK).

For the aggregation experiments with humic acid, 0.1 mL of the AgNPs suspension precontacted with humic acid solution was transferred to a disposable cuvette and the appropriate amount of stock NaNO_3 and distilled water were added to achieve the desired electrolyte concentration. The final concentration of humic acid and AgNPs were 50 mg/L and 10 mg/L, respectively.

The initial aggregation rate (k) of AgNPs can be determined by fitting the initial linear increase [11] using equation 1:

$$\frac{1}{N_0} \left(\frac{dD_h(t)}{dt} \right)_{t \rightarrow 0} \propto k \quad (1)$$

where N_0 is the initial AgNPs concentration. In this study, since all samples have the same particle concentration (i.e., 10 mg/L), the attachment efficiency (α , the inverse of the particle stability ratio W) was calculated by normalizing the initial rate of increase in $D_h(t)$ of a given electrolyte concentration by the initial rate of increase in $D_h(t)$ under favorable (fast) aggregation conditions (i.e., diffusion-limited conditions) where the rate is independent of electrolyte concentration [11] using equation 2:

$$\alpha = \frac{k}{k_{fast}} = \frac{\frac{1}{N_0} \left(\frac{dD_h(t)}{dt} \right)_{t \rightarrow 0}}{\frac{1}{N_{0,fast}} \left(\frac{dD_h(t)}{dt} \right)_{t \rightarrow 0,fast}} = \frac{\left(\frac{dD_h(t)}{dt} \right)_{t \rightarrow 0}}{\left(\frac{dD_h(t)}{dt} \right)_{t \rightarrow 0,fast}} \quad (2)$$

The zeta potentials of the AgNPs were measured in folded capillary cells at 25°C using the same instrument (i.e., ZetaSizer Nano ZS). Three measurements were carried out for each sample.

Batch Adsorption Experiments

Batch soil adsorption experiments were carried out according

to the method similar to that described by the OECD Test Guideline 106 [20]. For experimental condition varying ionic strength, NaNO_3 was used as a substitute for calcium chloride in order to minimize the possibility of AgCl precipitation ($K_{sp} = 1.77 \times 10^{-10}$ [22]) and the enhanced aggregation of AgNPs in the presence of divalent cation (Ca^{2+}) [23].

The soil samples (1.25 g) and 47.5 mL of NaNO_3 background solution were transferred to 50 mL Falcon test tubes and were equilibrated by shaking overnight before the day of the adsorption experiment to reach the equilibrium of background solution and dried soil. Afterwards, a certain volume of the stock solution of AgNPs was added to achieve the final desired concentrations. The tubes were sealed and shaken by using an orbital shaker (JSOS-700; JS Research Inc., Gongju, Korea) at 200 rpm. All adsorption experiments were performed in the dark condition at $25 \pm 1^\circ\text{C}$. After shaking until equilibrium, the supernatants were collected by a centrifuge at 3,000 rpm for 20 minutes (Centrifuge 5810R; Eppendorf, New York, NY, USA). The supernatant was treated with nitric acid, and the concentration of total silver was measured using ICP-OES (OPTIMA ICP-OES 7000; Perkin-Elmer, Norwalk, CT, USA). Each experiment was done at least three times. The control experiments were performed in the same manner without soil.

The adsorption coefficient (K_d) was calculated using the linear adsorption isotherm model and K_d value was the ratio between the concentration of the AgNPs in the soil phase (C_s^{ads}) and in the aqueous solution (C_{aq}^{ads}), when adsorption equilibrium (eq) was reached:

$$K_d = \frac{C_s^{ads}(eq)}{C_{aq}^{ads}(eq)} \quad (3)$$

The results of the adsorption experiments were also analyzed using the Freundlich adsorption isotherm model:

$$C_s^{ads}(eq) = K_F \cdot C_{aq}^{ads}(eq)^{\frac{1}{n}} \quad (4)$$

where K_F is the Freundlich adsorption coefficient and $1/n$ is Freundlich exponent.

Results

Aggregation Experiment

Effects of Ionic Strength

Representative aggregation profiles as measured by TR-DLS at various NaNO_3 concentrations are presented in Figure 2A. At NaNO_3 concentrations below 20 mM, the size of AgNPs did not change and remained very stable through the measured duration. Above the 20 mM NaNO_3 , the aggregation rate increased with increasing NaNO_3 concentration. At approximate-

ly 100 mM NaNO₃, the aggregation rate of AgNPs was maximum and further increases in the NaNO₃ concentration had no appreciable effect.

The attachment efficiencies (α) at varying NaNO₃ concentrations calculated using Equation 2 are shown in Figure 2B. There

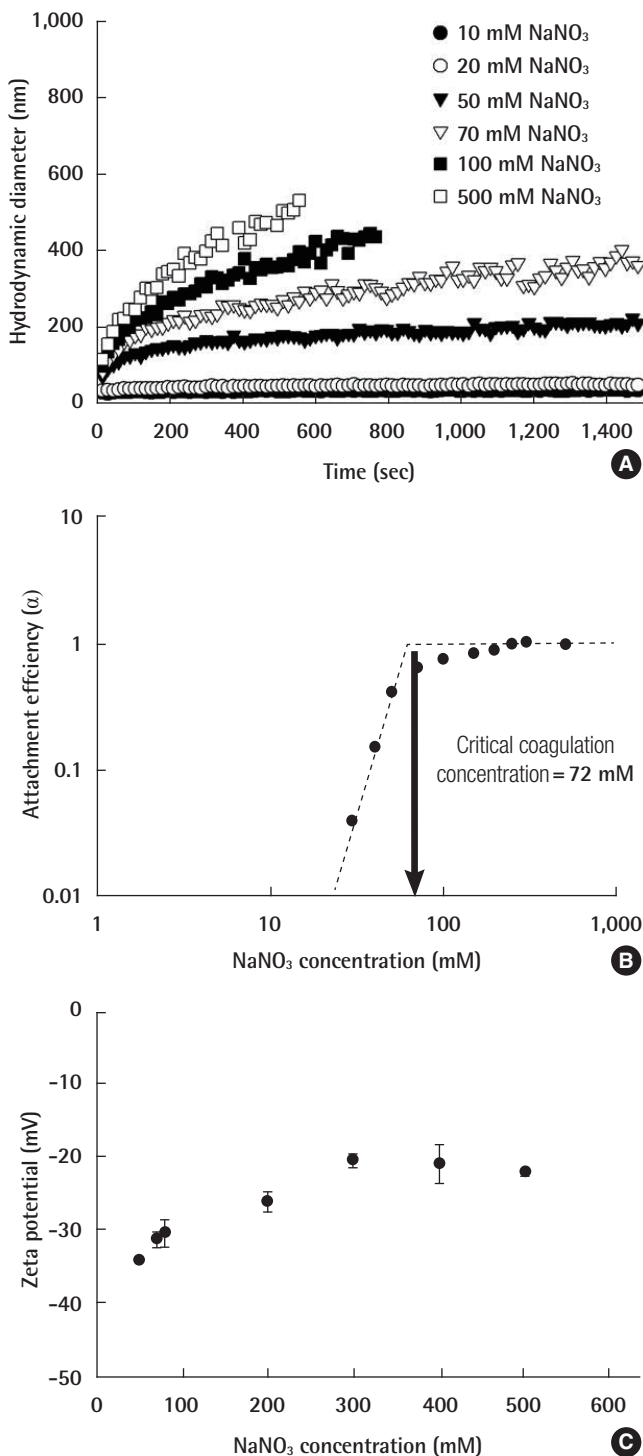


Figure 2. (A) Representative aggregation profiles, (B) attachment efficiency, and (C) zeta potential of silver nanoparticles at different sodium nitrate (NaNO₃) concentrations.

were two distinct aggregation regimes, which follows the Derjaguin-Landau-Verwey-Overbeek (DLVO) interaction of typical colloidal particles [11,18,24]. According to the DLVO theory, the stability of colloidal particles is determined by the combination of van der Waals attraction and electrostatic repulsion between two particles. As a result, at low ionic strength, the electrostatic repulsion interferes with aggregation (i.e., a reaction-limited regime [$\alpha < 1$]). At high ionic strength, the energy barrier from electrostatic repulsion is completely eliminated. This condition is called a diffusion-limited regime ($\alpha = 1$), and the aggregation rate is maximized without any further dependence on ionic strength. The electrolyte concentration at the boundary between the two regimes is commonly defined as the critical coagulation concentration (CCC) [11]. As shown in Figure 2, the CCC value of AgNPs was 72 mM NaNO₃.

The zeta potentials of AgNPs as a function of NaNO₃ concentration are illustrated in Figure 2C. AgNPs were negatively charged over the range of NaNO₃ concentration studied and the surface charges became less negative with increasing NaNO₃ concentration due to charge screening, which are consistent with the aggregation results.

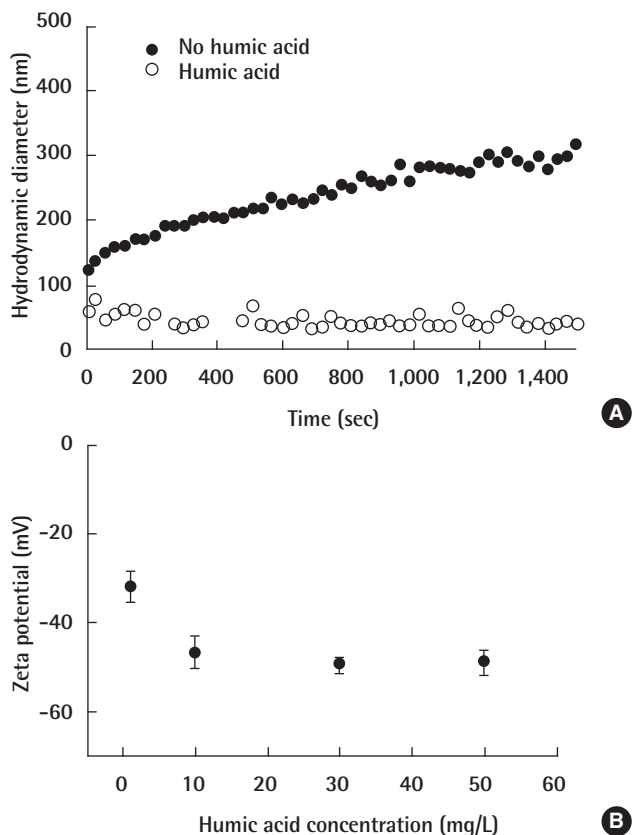


Figure 3. (A) Aggregation profiles and (B) zeta potential of silver nanoparticles in the absence/presence of humic acid under solution conditions of 50 mM sodium nitrate concentration.

Effects of NOM

To study the effects of NOM on the aggregation behavior, the aggregation kinetics of AgNPs in 50 mM NaNO₃ solution were compared in the presence and absence of humic acid (Figure 3A). In the absence of humic acid, AgNPs in 50 mM NaNO₃ continued to aggregate; however, in the presence of humic acid

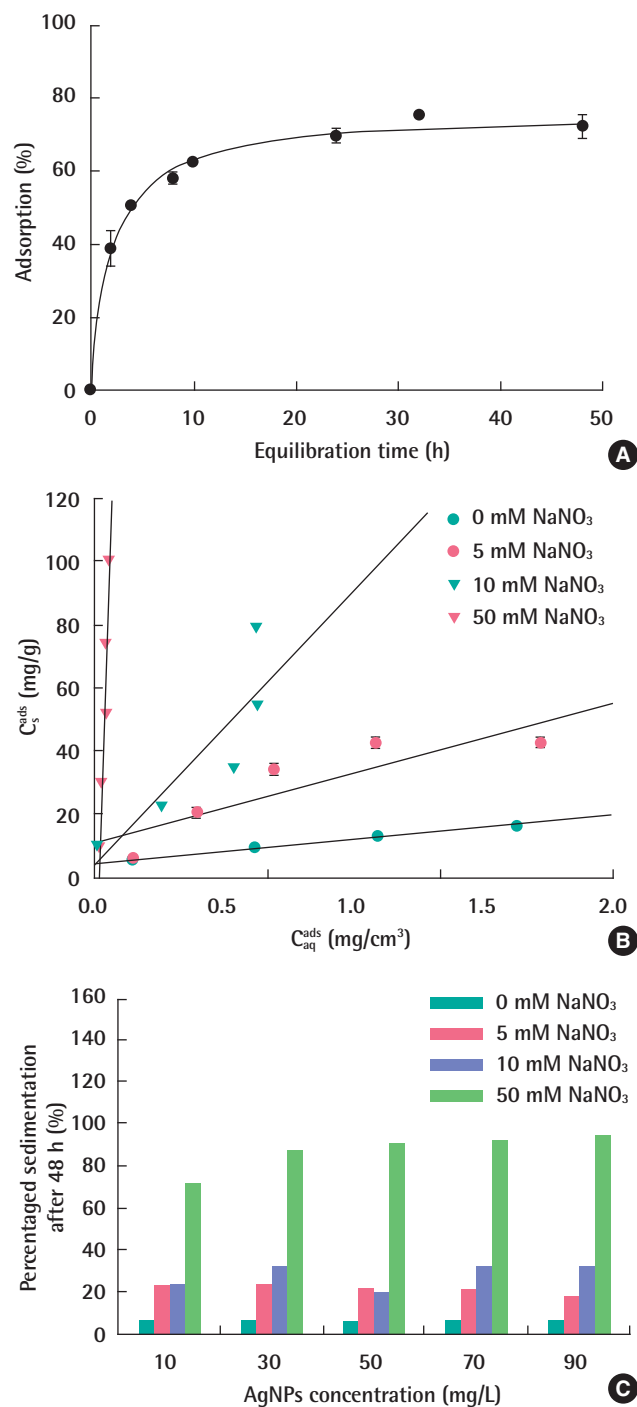


Figure 4. (A) The adsorption kinetics of silver nanoparticles (AgNPs) (50 mg/L) on soil at 10 mM sodium nitrate (NaNO₃), (B) the adsorption isotherms of AgNPs, and (C) sedimentation percentage of AgNPs in the control test at different NaNO₃ concentrations after 48 hours.

(50 mg/L), the size of AgNPs did not change and remained very stable over the experiment period.

The zeta potentials of the AgNPs measured in the presence of humic acid are shown in Figure 3B. As the humic acid concentration increased, the magnitude of negative surface charge increased as well, which is most likely because the negatively charged humic acid binds to the AgNPs. This result was consistent with the increased stability of AgNPs in the presence of humic acid.

Soil Adsorption Experiment

Figure 4A shows the adsorption kinetics of AgNPs (50 mg/L) on soil at 10 mM NaNO₃. The adsorption equilibrium was reached in approximately 24 hours. Based upon this, 48 hours contact time was determined as the equilibrium time for adsorption experiments in this study.

Effects of Ionic Strength

In order to minimize the aggregation of AgNPs prior to soil adsorption, the effects of ionic strength on soil adsorption were evaluated in NaNO₃ concentrations below 50 mM, a reaction-limited regime in the aggregation tests. Figure 4B presents the adsorption isotherms of AgNPs as a function of NaNO₃ concentration. The adsorption of AgNPs on soil increased as the ionic strength increased. The fitted linear and Freundlich adsorption isotherm parameters are shown in Table 2. The Freundlich adsorption isotherm appeared to be a better fit than linear adsorption isotherm.

Table 2. Linear adsorption isotherm and Freundlich adsorption isotherm of silver nanoparticles at different sodium nitrate (NaNO₃) concentrations and in the absence/presence of humic acid under solution conditions of 50 mM NaNO₃ concentration

NaNO ₃ concentration (mM)	Including sedimentation		Except sedimentation			
	K _d (cm ³ g ⁻¹)	R ²	K _d (cm ³ g ⁻¹)	R ²		
Linear adsorption isotherm						
0	8	0.99	5	0.96		
5	22	0.77	12	0.68		
10	87	0.75	47	0.77		
50	2,431	0.96	59	0.96		
50 (HA) ^a	11	0.66	5	0.27		
NaNO ₃ concentration (mM)	Including sedimentation			Except sedimentation		
	K _f	1/n	R ²	K _f	1/n	R ²
Freundlich adsorption isotherm						
0	12	0.53	0.99	9	0.44	0.96
5	36	0.86	0.91	21	0.87	0.87
10	61	0.49	0.82	35	0.42	0.81
50	109,378	2.48	1.00	35	0.77	0.96
50 (HA) ^a	28	0.29	0.91	25	0.23	0.75

HA, humic acid.

^aadded 50 mg/L humic acid.

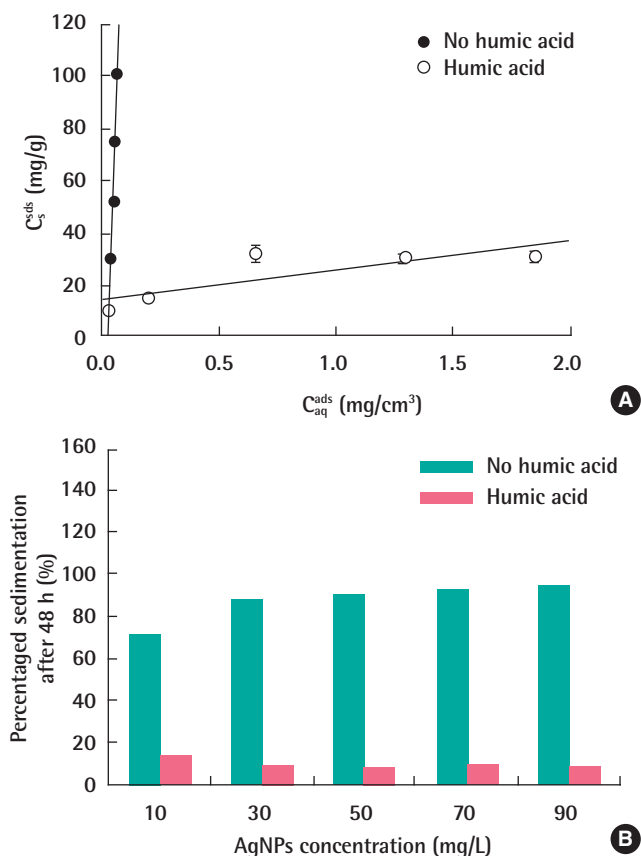


Figure 5. (A) The adsorption isotherms of silver nanoparticles (AgNPs) and (B) sedimentation percentage of AgNPs in the control test in the absence/presence of humic acid under solution conditions of 50 mM sodium nitrate (NaNO_3) concentration after 48 hours.

Figure 4C shows the control experiments with only AgNPs in NaNO_3 solution without soil in order to check the stability of AgNPs in each NaNO_3 solution. With increasing the ionic strength, the percentage of AgNPs sedimentation increased as well. In particular, at the highest NaNO_3 concentrations (i.e., 50 mM), the amount of the settled AgNPs ranged from 70% to 90% and the settled amount increased depending on the initial concentration of AgNPs. The results are consistent with the results of aggregation experiments, which suggests that adsorption and sedimentation by aggregation took place simultaneously during adsorption tests. In this respect, the corrected adsorption coefficients of AgNPs were also presented by excluding the amount of settled AgNPs obtained from each control experiment in Table 2. Even if we compare the corrected K_d values, it was obvious that the adsorption of AgNPs increased with the ionic strength. The high adsorption with increasing ionic strength can be attributed to their lower negative surface potential.

Effects of NOM

The effects of humic acid on AgNPs adsorption are presented in Figure 5A. The adsorption of AgNPs on soil significantly de-

creased in the presence of humic acid. For example, the linear K_d decreased from 2400 (without humic acid) to 11 (with humic acid) (Table 2). Figure 5B also shows the control experiments without soil. As consistent with the aggregation experiments, humic acid stabilized AgNPs and thus decreased the sedimentation. As can be seen Figure 3B, the binding of humic acid to AgNPs increased the magnitude of negative surface charge of AgNPs, which increased the electrostatic repulsion between AgNPs particles as well as AgNPs and soil matrix. In addition, the structure of the humic acid bound to the AgNPs surface was known to increase the stability of the particles by steric hindrance [24].

Discussion

The focus of this study was on the effects that environmental variables such as ionic strength and NOM may have on the aggregation and soil adsorption of AgNPs. The results of our experiments showed that both aggregation and soil adsorption increased with increasing ionic strength. The presence of NOM had an opposite effect: both aggregation and soil adsorption decreased in the presence of humic acid.

The results provide a basis for predicting the mobility of AgNPs in the natural environment. When AgNPs are released into the aquatic environment exhibiting high ionic strength, AgNPs will aggregate and accumulate in sediments or soils rather than remain in suspension. Additionally, AgNPs released into NOM-rich environments will likely remain stable in water, and thus exhibit high mobility as compared to environments poor in NOM. The study also provides information necessary for development of test guidelines related to the safety of nanomaterials as well as their environmental risk assessment.

Acknowledgements

This study was supported by the Industrial Core Technology Program (10034759, Risk Management Technology for Nano Products) funded by the Ministry of Knowledge Economy and by the research project funded by the Korea Institute of Toxicology.

Conflict of Interest

The authors have no conflicts of interest with material presented in this paper.

References

1. Niemeyer CM. Nanoparticles, proteins, and nucleic acids: biotech-

- nology meets materials science. *Angew Chem Int Ed* 2001;40(22):4128-4158.
2. Hwang IS, Cho J, Hwang JH, Hwang B, Choi H, Lee J, et al. Antimicrobial effects and mechanism(s) of silver nanoparticle. *Korean J Microbiol Biotechnol* 2011;39(1):1-8 (Korean).
 3. Whiteley CM, Valle MD, Kevin C Jones KC, Sweetman AJ. Challenges in assessing the environmental fate and exposure of nano silver. *J Phys Conf Ser* 2011. doi:10.1088/1742-6596/304/1/012070.
 4. Project on Emerging Nanotechnologies. An inventory of nanotechnology-based consumer products currently on the market [cited 2011 Nov 17]. Available from: http://www.nanotechproject.org/inventories/consumer/analysis_draft/.
 5. Benn TM, Westerhoff P. Nanoparticle silver released into water from commercially available sock fabrics. *Environ Sci Technol* 2008;42(11):4133-4139.
 6. Geranio L, Heuberger M, Nowack B. The behavior of silver nanotextiles during washing. *Environ Sci Technol* 2009;43(21):8113-8118.
 7. Kaegi R, Sinnet B, Zuleeg S, Hagedorfer H, Mueller E, Vonbank R, et al. Release of silver nanoparticles from outdoor facades. *Environ Pollut* 2010;158(9):2900-2905.
 8. Kittler S, Greulich C, Diendorf J, Köller M, Epple M. Toxicity of silver nanoparticles increases during storage because of slow dissolution under release of silver ions. *Chem Mater* 2010;22(16):4548-4554.
 9. Kennedy AJ, Hull MS, Bednar AJ, Goss JD, Gunter JC, Bouldin JL, et al. Fractionating nanosilver: importance for determining toxicity to aquatic test organisms. *Environ Sci Technol* 2010;44(24):9571-9577.
 10. Panacek A, Prucek R, Safarova D, Dittrich M, Richtrova J, Benickova K, et al. Acute and chronic toxicity effects of silver nanoparticles (NPs) on *Drosophila melanogaster*. *Environ Sci Technol* 2011;45(11):4974-4979.
 11. Huynh KA, Chen KL. Aggregation kinetics of citrate and polyvinylpyrrolidone coated silver nanoparticles in monovalent and divalent electrolyte solutions. *Environ Sci Technol* 2011;45(13):5564-5571.
 12. National Institute of Environmental Research. Study on hazardous properties of manufactured silver nanoparticles. Seoul: Ministry of Environment; 2010, p. 9 (Korean).
 13. Areepitak T, Ren J. Model simulations of particle aggregation effect on colloid exchange between streams and streambeds. *Environ Sci Technol* 2011;45(13):5614-5621.
 14. Godinez IG, Darnault CJ. Aggregation and transport of nano-TiO₂ in saturated porous media: effects of pH, surfactants and flow velocity. *Water Res* 2011;45(2):839-851.
 15. Zhang Y, Chen Y, Westerhoff P, Crittenden J. Impact of natural organic matter and divalent cations on the stability of aqueous nanoparticles. *Water Res* 2009;43(17):4249-4257.
 16. Liu J, Aruguete DM, Murayama M, Hochella MF Jr. Influence of size and aggregation on the reactivity of an environmentally and industrially relevant nanomaterial (PbS). *Environ Sci Technol* 2009;43(21):8178-8183.
 17. Jiang J, Oberdörster G, Biswas P. Characterization of size, surface charge, and agglomeration state of nanoparticle dispersions for toxicological studies. *J Nanopart Res* 2009;11(1):77-89.
 18. Chen KL, Elimelech M. Influence of humic acid on the aggregation kinetics of fullerene (C₆₀) nanoparticles in monovalent and divalent electrolyte solutions. *J Colloid Interface Sci* 2007;309(1):126-134.
 19. El Badawy AM, Scheckel KG, Suidan M, Tolaymat T. The impact of stabilization mechanism on the aggregation kinetics of silver nanoparticles. *Sci Total Environ* 2012;429:325-331.
 20. Organization for Economic Co-operation and Development. (OECD). Test No. 106: adsorption -- desorption using a batch equilibrium method [cited 2012 Nov 12]. Available from: http://www.oecd-ilibrary.org/environment/test-no-106-adsorption-desorption-using-a-batch-equilibrium-method_9789264069602-en.
 21. Kim KD, Han DN, Kim HT. Optimization of experimental conditions based on the Taguchi robust design for the formation of nano-sized silver particles by chemical reduction method. *Chem Eng J* 2004;104(1-3):55-61.
 22. Levard C, Hotze EM, Lowry GV, Brown GE Jr. Environmental transformations of silver nanoparticles: impact on stability and toxicity. *Environ Sci Technol* 2012;46(13):6900-6914.
 23. El Badawy AM, Luxton TP, Silva RG, Scheckel KG, Suidan MT, Tolaymat TM. Impact of environmental conditions (pH, ionic strength, and electrolyte type) on the surface charge and aggregation of silver nanoparticles suspensions. *Environ Sci Technol* 2010;44(4):1260-1266.
 24. Qu X, Hwang YS, Alvarez PJ, Bouchard D, Li Q. UV irradiation and humic acid mediate aggregation of aqueous fullerene (nC₆₀) nanoparticles. *Environ Sci Technol*. 2010;44(20):7821-7826.