

# Bond strength of resin cement to CO<sub>2</sub> and Er:YAG laser-treated zirconia ceramic

Shahin Kasraei<sup>1</sup>,  
Loghman Rezaei-  
Soufi<sup>1\*</sup>, Bijan Heidari<sup>2</sup>,  
Fariborz Vafae<sup>2</sup>

<sup>1</sup>Dental Research Center,  
Department of Restorative Dentistry,  
<sup>2</sup>Department of Prosthodontic,  
Dental School, Hamadan University  
of Medical Sciences, Hamadan, Iran

Received April 13, 2014;  
Accepted July 18, 2014.

<sup>1</sup>Kasraei S; Rezaei-Soufi L, Dental  
Research Center, Department  
of Restorative Dentistry, Dental  
School, Hamadan University of  
Medical Sciences, Hamadan, Iran  
<sup>2</sup>Heidari B; Vafae F, Department  
of Prosthodontic, Dental School,  
Hamadan University of Medical  
Sciences, Hamadan, Iran

## \*Correspondence to

Loghman Rezaei-Soufi, DDS, MS,  
Associate Professor, Dental Research  
Center, Department of Restorative  
Dentistry, Dental School, Hamadan  
University of Medical Sciences,  
Shahid Fahmideh Blvd, Hamadan,  
Iran  
TEL, +98-913-317-6197; FAX,  
+98-811-825-0588; E-mail,  
loghmansofi@umsha.ac.ir

**Objectives:** It is difficult to achieve adhesion between resin cement and zirconia ceramics using routine surface preparation methods. The aim of this study was to evaluate the effects of CO<sub>2</sub> and Er:YAG laser treatment on the bond strength of resin cement to zirconia ceramics. **Materials and Methods:** In this *in-vitro* study 45 zirconia disks (6 mm in diameter and 2 mm in thickness) were assigned to 3 groups ( $n = 15$ ). In control group (CNT) no laser treatment was used. In groups COL and EYL, CO<sub>2</sub> and Er:YAG lasers were used for pretreatment of zirconia surface, respectively. Composite resin disks were cemented on zirconia disk using dual-curing resin cement. Shear bond strength tests were performed at a crosshead speed of 0.5 mm/min after 24 hr distilled water storage. Data were analyzed by one-way ANOVA and *post hoc* Tukey's HSD tests. **Results:** The means and standard deviations of shear bond strength values in the EYL, COL and CNT groups were  $8.65 \pm 1.75$ ,  $12.12 \pm 3.02$ , and  $5.97 \pm 1.14$  MPa, respectively. Data showed that application of CO<sub>2</sub> and Er:YAG lasers resulted in a significant higher shear bond strength of resin cement to zirconia ceramics ( $p < 0.0001$ ). The highest bond strength was recorded in the COL group ( $p < 0.0001$ ). In the CNT group all the failures were adhesive. However, in the laser groups, 80% of the failures were of the adhesive type. **Conclusions:** Pretreatment of zirconia ceramic via CO<sub>2</sub> and Er:YAG laser improves the bond strength of resin cement to zirconia ceramic, with higher bond strength values in the CO<sub>2</sub> laser treated samples. (*Restor Dent Endod* 2014;39(4):296-302)

**Key words:** CO<sub>2</sub> laser; Er:YAG laser; Resin cement; Zirconium oxide

## Introduction

During the past decade, zirconia ceramic technology has led to rapid advances in metal-free dentistry.<sup>1</sup> Unique properties of yttrium oxide (yttrium-tetragonal zirconia polycrystal, Y-TZP), namely its flexural strength of 1,000 MPa, chemical stability, biocompatibility and optical properties, have made Y-TZP a good choice for the fabrication of all-ceramic crowns, long-span bridges, posts and cores and implants.<sup>2-5</sup> Zirconium oxide crowns can be cemented using conventional and adhesive techniques.<sup>6,7</sup>

Previous studies have shown that indirect all-ceramic restorations require a durable bond between the cement and the ceramic for longevity.<sup>8-11</sup> Use of resin cements improves retention, fracture resistance and the marginal adaptation of the restoration to the tooth structures.<sup>10,12</sup> It has been reported that use of adhesive resin cements

containing phosphate monomers may contribute to bonding of zirconia restorations to tooth structures.<sup>13-15</sup>

There is no consensus for achieving optimal bond strength between composite resins and zirconia. Zirconia ceramics have a highly crystalline structure. Therefore, achieving a proper micromechanical bond between the resin cement and zirconia ceramic restoration with routine preparation techniques, including acid etching with hydrofluoric acid, is considered an ineffective method.<sup>9,16</sup> Other techniques have been suggested for surface treatment, including surface abrasion, sandblasting, abrasion with diamond burs, air abrasion with aluminum oxide, silicoating, and selective infiltration etching.<sup>17,18</sup> Recently, due to advances in laser techniques, some studies have suggested application of lasers such as CO<sub>2</sub>, Er:YAG and Nd:YAG to bring about changes on zirconia ceramics to improve their bond to tooth structures.<sup>12,17,19,20</sup> Some studies have shown that use of CO<sub>2</sub> and Er:YAG lasers improves the bond strength to zirconia ceramics.<sup>12,17,19,20</sup> However, some studies have yielded contradictory results.<sup>20-22</sup>

The aim of the present study was to evaluate and compare the effects of CO<sub>2</sub> and Er:YAG lasers on the shear bond strength of resin cement to zirconia ceramic. Based on the null hypothesis of this study, pretreatment of the zirconia ceramic surface with CO<sub>2</sub> and Er:YAG lasers has no effect on shear bond strength of resin cement to zirconia ceramic.

## Materials and Methods

The present *in vitro* study was performed on 45 zirconia disks. Presintered zirconia cylinders (9.8 mm in diameter and 20 mm in height, Ceramill Zi, Amann Girrbach AG, Koblach, Austria) were prepared by a milling machine (Ceramill, Multix, Amann Girrbach AG) and copy milling technique based on the manufacturer's instructions to obtain specimens with a dimension of 2.5 mm in diameter and 7.5 mm in height (Table 1). Next, the specimens

were densely sintered in a furnace (Sirona Dental Systems LLC, Charlotte, NC, USA) under the conditions (1,530°C for 1 hour and cooling for 6 hours) suggested by the manufacturer using the proprietary sintering program (Amann Girrbach AG). The discoid-specimen size after sintering was 6 mm in diameter and 2 mm in thickness. The specimen surfaces were treated with airborne particle abrasion with 50 µm Al<sub>2</sub>O<sub>3</sub> at 2-bar pressure and were polished by hand with 600-grit silicon carbide paper (Matador 991A, Soflex, Starcke GmbH & Co. KG, Melle, Germany) to standardize them.

All the specimen surfaces were treated with airborne particle abrasion with 50 µm Al<sub>2</sub>O<sub>3</sub> at 2-bar pressure and were wet polished by hand with 600-grit silicon carbide paper (Matador 991A, Soflex, Starcke GmbH & Co. KG) to standardize them. The surfaces of sintered zirconia disks were observed by x2.5 loop, and samples with surface cracks or voids were replaced by new ones. The specimens were cleaned in an ultrasonic bath containing isopropanol for 3 minutes and dried by air syringe before surface treatment and then were randomly assigned to 3 groups of 15:

CNT group: No surface pretreatment was applied in this group (control).

COL group: The bonding surfaces of zirconia disks were irradiated by CO<sub>2</sub> laser (Smart US 20D, Deka, Florence, Italy). Laser beam parameters were selected based on the results of previous studies for micromechanical retention.<sup>17,19,21,23</sup> The wavelength of CO<sub>2</sub> laser was 10.6 µm, with a pulse repetition of 100 Hz, pulse duration of 160 ms, output energy of 3W and energy density of 265.39 J/cm<sup>2</sup>. Laser was delivered by a 600 µm hollow ceramic tip that was hand-adjusted perpendicular to the ceramic surface at a distance of approximately 1 mm. Laser beam diameter at the irradiated surface was 0.48 mm. The whole surface of the zirconia disk, measuring 6 mm in diameter (0.28 cm<sup>2</sup>), was irradiated for 10 seconds at a rate of 2 mm/s using horizontal surface scanning mode.<sup>17,19,21</sup>

**Table 1.** characteristics of materials used in the current study

Material	Type of material	Batch number	Manufacturer
Ceramill Zi	Presintered dental zirconia ceramic	37360	Amann Girrbach AG, Koblach, Austria
Filtek Z 250	Composite resin	N395226	3M ESPE, St. Paul, MN, USA
Panavia F2.0	Dual cure adhesive resin cement	Liquid A: 00299A Liquid B: 00173A Paste A: 00489A Paste B: 00022A	Kuraray, Tokyo, Japan
Silicon carbide paper	Sand paper	61173	Matador 991A, Soflex, Starcke's Co., Melle, German

EYL group: The surfaces of zirconia disks were covered with graphite powder to increase laser energy absorption and irradiated with Er:YAG laser (Fidelis Plus III, Fotona, Ljubljana, Slovenia). Laser parameters were set as follows: wavelength of 2,940 nm, pulse duration of 50  $\mu$ s (SSP), output power of 2 W, pulse repetition of 10 Hz and energy density of 200 mJ, using R14 handpiece and an 800  $\mu$ m sapphire tip, with water/air spray ratio of 4/4. The sapphire tip was adjusted by hand at an approximate distance of 0.5 mm, perpendicular to the disk surface and the entire zirconia disk surface (0.28 cm<sup>2</sup>), was irradiated at a rate of 2 mm/s for 10 seconds using horizontal surface scanning mode.<sup>12,19</sup>

One additional specimen from each group was prepared and sputter-coated with gold for evaluation of micro-morphology of the zirconia surface. The samples were analyzed using scanning electron microscope (JSM-6335F, JEOL, Tokyo, Japan) at  $\times$ 1,000 and  $\times$ 5,000 magnifications.

Composite resin disks (Filtek Z 250, 3M ESPE, St. Paul, MN, USA), 3 mm in diameter and 2 mm in thickness, were fabricated by packing composite resin in one increment into transparent plastic molds placed on glass slabs followed by light-curing for 40 seconds at a distance of 1 mm using a light-curing unit (Demi, Kerr Corporation, Middleton, WI, USA) with 1,000 mW/cm<sup>2</sup> intensity. The composite resin disks were cemented to the surface of zirconia samples using a dual-curing resin cement (Panavia F2.0, Kuraray Noritake Dental Inc., Osaka, Japan). First, the primers A and B were admixed and then applied to the surface of ceramic and composite resin with a microbrush. After 20 seconds, the resin cement tubes A and B were mixed and placed between ceramic disks and composite resin and each composite resin disk was bonded to a zirconia disk by finger pressure.<sup>17,20,21</sup> Excess cement was eliminated and the specimens were light-cured for 20 seconds. Finally, the specimens were rinsed with air and

water spray and stored in distilled water at 37°C for 24 hours before shear bond strength testing. The shear bond strength test was performed in a universal mechanical testing machine (Dartec HC10, Dartec Ltd., Stourbridge, England) at a strain rate of 0.5 mm/s.

All the fractured samples were evaluated twice under a stereomicroscope (SZ40, Olympus, Tokyo, Japan) at  $\times$ 40 magnification for fracture modes (cohesive, adhesive and mixed) by one operator. Data were analyzed by SPSS 13, using one-way ANOVA and *post-hoc* Tukey's HSD tests. Statistical analysis was set at a confidence interval of 0.95%, power of 80% and a significance level of  $p < 0.05$ .

## Results

The highest ( $12.12 \pm 3.02$  MPa) and lowest ( $5.97 \pm 1.14$  MPa) mean shear bond strength values were observed in the COL and CNT groups, respectively. The mean shear bond strength value in the EYL group was  $8.65 \pm 1.77$  MPa (Table 2). One-way ANOVA showed statistically significant differences in shear bond strength values between the three groups. Pairwise comparison of the groups by *post-hoc* Tukey's tests showed significant differences between all groups (Table 2).

Evaluation of the mode of failure in groups showed that 100% of the fractures in the CNT group were adhesive (between zirconia and cement). However, in the COL and EYL groups, 80% of the failures were adhesive and 20% were mixed (between the composite resin and resin cement) (Table 2). The SEM photograph of zirconia ceramic surface treated with CO<sub>2</sub> and Er:YAG laser under an electron microscope at  $\times$ 1,000 and  $\times$ 5,000 magnifications showed that application of 3W CO<sub>2</sub> laser beam to the surface of zirconia produced cracks on the ceramic surface. Surface pretreatment by Er:YAG laser enhanced surface roughness with a scaly appearance (Figures 1 - 3).

**Table 2.** Comparison of the shear bond strength of resin cement to zirconia ceramic

Groups	Shear bond strength (Mpa)	<i>p</i> value*	Mode of Failures(%)		
			Adhesive	Cohesive	Mixed
CNT	$5.97 \pm 1.14^a$		100	0	0
COL	$12.12 \pm 3.02^c$	0.0001	80	0	20
EYL	$8.65 \pm 1.77^b$		80	0	20

\*One-way ANOVA; The different superscript letters indicate a significant difference within column by Tukey's HSD tests ( $p < 0.05$ ).

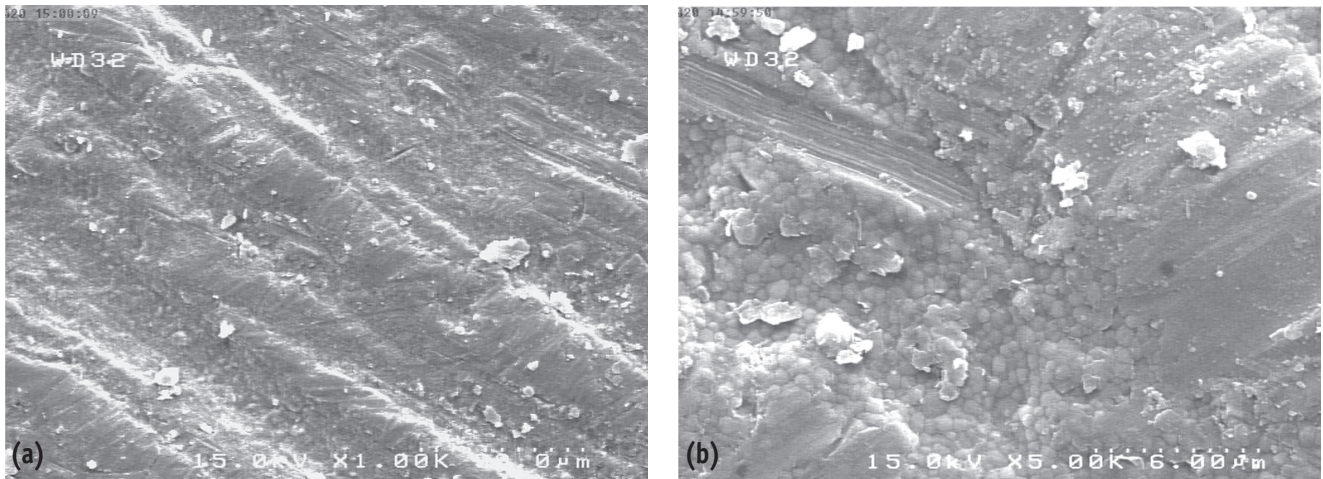


Figure 1. Scanning electron microscopic view of zirconia surface in the control group. (a) ×1,000; (b) ×5,000.

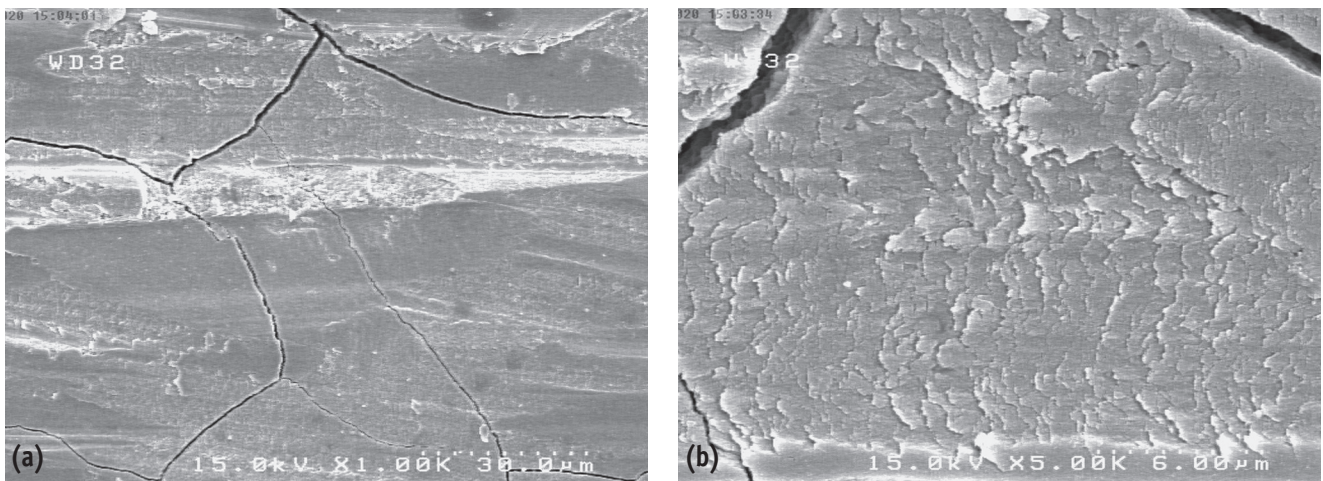


Figure 2. Scanning electron microscopic view of CO<sub>2</sub> laser-treated zirconia surface, revealing a rough scaly surface with microcracks. (a) ×1,000; (b) ×5,000.

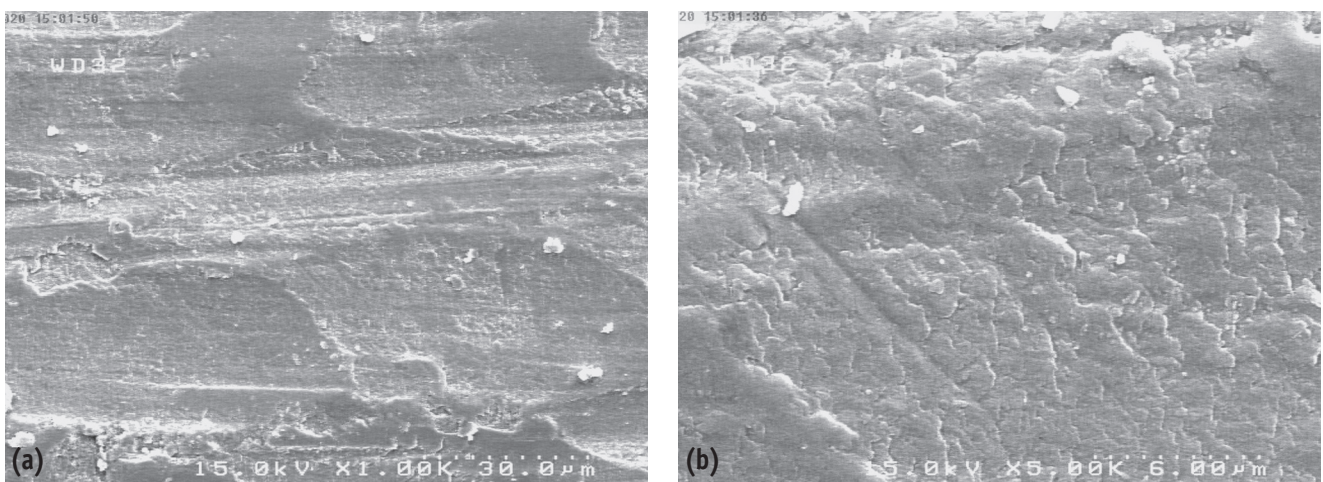


Figure 3. Scanning electron microscopic view of Er:YAG laser-treated zirconia surface, revealing a rough surface without microcracks. (a) ×1,000; (b) ×5,000.

## Discussion

Considering current advances in laser technology, laser beam irradiation is used in various dental procedures, including roughening the surface of ceramics. In the present study, the effects of Er:YAG and CO<sub>2</sub> lasers on shear bond strength of resin cement to zirconia ceramic were evaluated and compared. In this study, in both case and control groups, Panavia cement which has ester phosphate monomer (10-methacryloyloxydecyl dihydrogen phosphate: MDP) was used, because there has been numerous evidences showing that the bonding to Y-TZP ceramics will be improved by using products having chemical affinity to metal oxides.<sup>24,25</sup> Ester phosphate monomers such as MDP have chemical reaction with zirconium oxide and form a strong bond with zirconia ceramics.<sup>26</sup> The results of the present study clearly showed that surface preparation with CO<sub>2</sub> and Er:YAG lasers increased the shear bond strength of resin cement to zirconia surface ( $p < 0.001$ ). Therefore, the null hypothesis of the study was refuted. Consistent with the results of the present study, some previous studies have also shown that CO<sub>2</sub> and Er:YAG lasers can increase the shear bond strength of resin cement to zirconia without aging method and after thermocycling.<sup>12,17,19,23,27,28</sup>

Zirconia ceramic can completely absorb the energy of the CO<sub>2</sub> laser beam. After absorption of laser energy, a process called heat induction produces shell-like ruptures on the ceramic surface, which can provide a micromechanical bond between the resin material and the ceramic surface after resin tags penetrate into these cracks and set.<sup>17,28</sup> Micromorphologic evaluation of the surface of ceramics has shown that the CO<sub>2</sub> laser produces a rough surface with a scaly appearance and microcracks.<sup>12,17,28</sup> The micrograph of the zirconia disc surface in our study also showed scaly appearance and microcracks (Figure 2). Akyil *et al.* showed that treatment of zirconia surfaces by CO<sub>2</sub> laser at power of 4 W resulted in microcrack, scaly appearance and significantly increased bond strength of resin cement to zirconia.<sup>19</sup> It seems that resin penetration to microcracks leads to increased bond strength of resin cement to zirconia; however weakening the sub surface of zirconia could affect the mode of fracture.

Er:YAG is not absorbed as well as the CO<sub>2</sub> laser by the zirconia surface. Thus, in order to enhance its absorption, we covered the ceramic surface with graphite powder. As seen on SEM images (Figure 3), Er:YAG laser increased surface roughness without causing microcracks on the zirconia ceramic surface and significantly increased the resin cement bond strength ( $p = 0.004$ ). Previous studies have demonstrated that Er:YAG laser produces a rough surface.<sup>12,29,30</sup> Akin *et al.* reported that irradiation of a lower power Er:YAG laser at 150 mJ, 10 Hz, 1 W and long pulse for 20 seconds on Y-TZP ceramic material enhanced the surface roughness without microcrack formation on the

ceramic surface.<sup>27</sup> In contrast, some studies have shown that irradiation of zirconia ceramic surfaces with CO<sub>2</sub> and Er:YAG lasers does not result in an increase in shear bond strength of resin cement to pretreated surfaces.<sup>20,22,28,29,31</sup> This discrepancy in results may be attributed to differences in surface laser pretreatment methods. Absorption of the laser beam energy by the material surface is the most important interaction (the thermomechanical effect) between the laser and the material.<sup>12</sup> Increase in output energy and pulse rate of the laser beam results in increasing the energy density and thermal effects on the surface. In pulsed lasers such as Er:YAG laser, changing the pulse duration changes the peak power and its effects on the material surface.

Foxton *et al.* reported that Er:YAG laser decreased the shear bond strength between zirconia cement and resin cement.<sup>22</sup> They used Er:YAG laser beam with 10 mJ/pulse and 200 Hz for 5 seconds; pulse duration was not reported in their study. However, in the present study, the Er:YAG laser beam parameters were 10 mJ/pulse, 200 Hz, and pulse duration of 50  $\mu$ s for 10 seconds. In the present study, the newer technology of Er:YAG laser with a pulse duration of 50  $\mu$ s was used. This low pulse duration increased the laser power peak, thus, increasing the effect of the laser energy on the surface. Lin *et al.* reported that Er:YAG laser had no effect on zirconia surface at different laser energy intensities (100, 200 and 300 mJ) and irradiation times (5, 10 and 15 seconds).<sup>29</sup> In contrast to the present study, they did not use graphite powder to increase absorption of laser energy by zirconia. Coating the surface with graphite powder increases the absorption of laser energy by the white opaque zirconia ceramic.

Contrary to the results of the present study, Akin *et al.* reported that Er:YAG laser significantly increased the bond strength of resin cement to zirconia more than the CO<sub>2</sub> laser. They reported smooth surfaces on CO<sub>2</sub> laser-treated zirconia samples with no retention.<sup>21</sup> These results may be attributed to the low energy density of the CO<sub>2</sub> laser beam (159.22 J/cm<sup>2</sup>) in their study. In our study, despite the low energy level of the CO<sub>2</sub> laser beam (3 W), the energy density of the laser beam was higher (265.39 J/cm<sup>2</sup>) considering the diameter of the laser beam delivered, which resulted in a rough surface due to its thermal effects. The rough surface was clearly seen in SEM micrographs (Figures 1 and 2). Scaly irregularities on the zirconia surface increase micromechanical retention and improve shear bond strength of resin cement to the zirconia surface.

Pretreatment of zirconia surface with CO<sub>2</sub> laser resulted in a greater increase in bond strength values compared to the Er:YAG laser ( $p < 0.001$ ) in the present study, which can be attributed to the extent and type of the surface irregularities produced on the zirconia surface. Microcracks produced by the irradiation of the zirconia surface with CO<sub>2</sub> laser were visible in different areas of the surface

on SEM micrographs while no microcracks were observed on the surfaces exposed to Er:YAG laser beam. A higher bond strength with the use of CO<sub>2</sub> laser may be attributed to better absorption of CO<sub>2</sub> laser compared to Er:YAG by the zirconia surface resulting in more surface roughness. Surface microcracks facilitate the penetration of resin tags and cement into such an irregular surface and improve adhesion. Profilometric evaluations are necessary to evaluate surface irregularities produced by laser beams on zirconia surfaces, which is one of the limitations of the present study. Consistent with the results of the present study, Akiyl *et al.* reported that preparation of zirconia surface with CO<sub>2</sub> laser resulted in a greater increase in shear bond strength of resin cement to this surface, compared to Er:YAG laser.<sup>19</sup>

Evaluation of fracture modes in the present study showed that 100% of fractures were adhesive in the control group. In the COL and EYL groups, 20% of the fractures were mixed. In other words, there was an increase in the frequency of mixed failures at the zirconia surface-resin cement interface with an increase in shear bond strength values, consistent with the results of some previous studies.<sup>20,21,32</sup> Apart from the bond strength between the resin cement and zirconia surface, the durability of the bond is more important for the clinical success of restorations.

## Conclusions

Under the limitations of the present study, preparation of zirconia ceramic surfaces with CO<sub>2</sub> and Er:YAG lasers significantly increased the bond strength of resin cement to zirconia ceramic, with the CO<sub>2</sub> laser being superior to Er:YAG laser.

## Acknowledgement

This article was prepared from a dissertation for a specialty degree in restorative dentistry. The authors would like to extend their gratitude to the Deputy of Research at Hamadan University of Medical Sciences and the Dental Research Center for the financial support provided.

Conflict of Interest: No potential conflict of interest relevant to this article was reported.

## References

- Vagkopoulou T, Koutayas SO, Koidis P, Strub JR. Zirconia in dentistry: Part 1. Discovering the nature of an upcoming bioceramic. *Eur J Esthet Dent* 2009;4:130-151.
- Christel P, Meunier A, Heller M, Torre JP, Peille CN. Mechanical properties and short-term *in-vivo* evaluation of yttrium-oxide-partially-stabilized zirconia. *J Biomed Mater Res* 1989;23:45-61.
- Hayashi K, Matsuguchi N, Uenoyama K, Sugioka Y. Re-evaluation of the biocompatibility of bioinert ceramics *in vivo*. *Biomaterials* 1992;13:195-200.
- Taira M, Nomura Y, Wakasa K, Yamaki M, Matsui A. Studies on fracture toughness of dental ceramics. *J Oral Rehabil* 1990;17:551-563.
- Blatz MB. Long-term clinical success of all ceramic posterior restorations. *Quintessence Int* 2002;33:415-426.
- Ernst CP, Cohnen U, Stender E, Willershausen B. *In vitro* retentive strength of zirconium oxide ceramic crowns using different luting agents. *J Prosthet Dent* 2005;93:551-558.
- Palacios RP, Johnson GH, Phillips KM, Raigrodski AJ. Retention of zirconium oxide ceramic crowns with three types of cement. *J Prosthet Dent* 2006;96:104-114.
- Rosenstiel SF, Land MF, Crispin BJ. Dental luting agents: a review of the current literature. *J Prosthet Dent* 1998;80:280-301.
- Piwowarczyk A, Lauer HC, Sorensen JA. The shear bond strength between luting cements and zirconia ceramics after two pre-treatments. *Oper Dent* 2005;30:382-388.
- Burke FJ, Fleming GJ, Nathanson D, Marquis PM. Are adhesive technologies needed to support ceramics? An assessment of the current evidence. *J Adhes Dent* 2002;4:7-22.
- Blatz MB, Sadan A, Kern M. Resin-ceramic bonding: a review of the literature. *J Prosthet Dent* 2003;89:268-274.
- Cavalcanti AN, Pilecki P, Foxton RM, Watson TF, Oliveira MT, Gianinni M, Marchi GM. Evaluation of the surface roughness and morphologic features of Y-TZP ceramics after different surface treatments. *Photomed Laser Surg* 2009;27:473-479.
- Blatz MB, Sadan A, Martin J, Lang B. *In vitro* evaluation of shear bond strengths of resin to densely-sintered high-purity zirconium-oxide ceramic after long-term storage and thermal cycling. *J Prosthet Dent* 2004;91:356-362.
- Tanaka R, Fujishima A, Shibata Y, Manabe A, Miyazaki T. Cooperation of phosphate monomer and silica modification on zirconia. *J Dent Res* 2008;87:666-670.
- Wolfart M, Lehmann F, Wolfart S, Kern M. Durability of the resin bond strength to zirconia ceramic after using different surface conditioning methods. *Dent Mater* 2007;23:45-50.
- Blatz MB. Adhesive cementation of high-strength ceramics. *J Esthet Restor Dent* 2007;19:238-239.
- Ural Ç, Külünk T, Külünk Ş, Kurt M. The effect of laser treatment on bonding between zirconia ceramic surface and resin cement. *Acta Odontol Scand* 2010;68:354-359.

18. Casucci A, Mazzitelli C, Monticelli F, Toledano M, Osorio R, Osorio E, Papacchini F, Ferrari M. Morphological analysis of three zirconium oxide ceramics: effect of surface treatments. *Dent Mater* 2010;26:751-760.
19. Akyil MS, Uzun IH, Bayindir F. Bond strength of resin cement to yttrium-stabilized tetragonal zirconia ceramic treated with air abrasion, silica coating, and laser irradiation. *Photomed Laser Surg* 2010;28:801-808.
20. Paranhos MP, Burnett LH Jr, Magne P. Effect of Nd:YAG laser and CO<sub>2</sub> laser treatment on the resin bond strength to zirconia ceramic. *Quintessence Int* 2011;42:79-89.
21. Akin H, Ozkurt Z, Kırmalı O, Kazazoglu E, Ozdemir AK. Shear bond strength of resin cement to zirconia ceramic after aluminum oxide sandblasting and various laser treatments. *Photomed Laser Surg* 2011;29:797-802.
22. Foxton RM, Cavalcanti AN, Nakajima M, Pilecki P, Sherriff M, Melo L, Watson TF. Durability of resin cement bond to aluminium oxide and zirconia ceramics after air abrasion and laser treatment. *J Prosthodont* 2011;20:84-92.
23. Ural C, Kalyoncuoğlu E, Balkaya V. The effect of different power outputs of carbon dioxide laser on bonding between zirconia ceramic surface and resin cement. *Acta Odontol Scand* 2012;70:541-546.
24. Yoshida K, Tsuo Y, Atsuta M. Bonding of dual-cured resin cement to zirconia ceramic using phosphate acid ester monomer and zirconate coupler. *J Biomed Mater Res B Appl Biomater* 2006;77:28-33.
25. Atsu SS, Kilicarslan MA, Kucukesmen HC, Aka PS. Effect of zirconium-oxide ceramic surface treatments on the bond strength to adhesive resin. *J Prosthet Dent* 2006;95:430-436.
26. Silva LH, Costa AK, Queiroz JR, Bottino MA, Valandro LF. Ceramic primer heat-treatment effect on resin cement/Y-TZP bond strength. *Oper Dent* 2012;37:634-640.
27. Akin H, Tugut F, Akin GE, Guney U, Mutaf B. Effect of Er:YAG laser application on the shear bond strength and microleakage between resin cements and Y-TZP ceramics. *Lasers Med Sci* 2012;27:333-338.
28. Ersu B, Yuzugullu B, Ruya Yazici A, Canay S. Surface roughness and bond strengths of glass-infiltrated alumina-ceramics prepared using various surface treatments. *J Dent* 2009;37:848-856.
29. Lin Y, Song X, Chen Y, Zhu Q, Zhang W. Effect of Er:YAG laser irradiation on bonding property of zirconia ceramics to resin cement. *Photomed Laser Surg* 2013;31:619-625.
30. Demir N, Subaşı MG, Ozturk AN. Surface roughness and morphologic changes of zirconia following different surface treatments. *Photomed Laser Surg* 2012;30:339-345.
31. Erdem A, Akar GC, Erdem A, Kose T. Effects of different surface treatments on bond strength between resin cements and zirconia ceramics. *Oper Dent* 2014;39:e118-127.
32. Usume A, Hamdemirci N, Kotoglu BY, Simsek I, Parlar O, Sari T. Bond strength of resin cement to zirconia ceramic with different surface treatments. *Lasers Med Sci* 2013;28:259-266.