

Penetration and Microleakage Assessment of Flowable Resin Applied on Carious Fissure Following Various Fissurotomy Techniques

Seok Kwon¹, Sangho Lee¹, Nanyoung Lee¹, Meongkwan Jih¹, Youngmi Yoon²

¹*Department of Pediatric Dentistry, School of Dentistry, Chosun University*

²*Graduate School of Dentistry, Chosun university*

Abstract

The purpose of this study was to evaluate the effect of fissurotomy on the penetration and microleakage of flowable resins for carious fissures. A total of 250 extracted premolars with early fissure caries were selected and divided into five groups according to the fissurotomy; no fissurotomy (n = 50), fissurotomy with Fissurotomy[®] original bur (n = 50), fissurotomy with Fissurotomy[®] Miro NTF bur (n = 50), fissurotomy with SF104R tapered diamond bur (n = 50), fissurotomy with 1/2 round carbide bur (n = 50). Two types of flowable resins (UniFil[®]Flow, Filtek[®]Flow) were used as sealing materials. All samples were sectioned and observed using a stereoscopic microscope after thermocycling and immersing in methylene blue solution. The adaptation of flowable resin to the fissure wall was observed using scanning electron microscopy. The penetration of flowable resin into the carious fissure was significantly increased by fissurotomy, which also decreased microleakage. Fissure preparation using different burs showed a significantly different in penetration, but did not show any difference in microleakage. Unifil[®]Flow showed better penetration than Filtek[®]Flow, but there was no significant difference in microleakage. Fissurotomy can be used to increase the penetration of flowable resin into carious fissures and decrease microleakage.

Key words : Pit and fissure sealant, Flowable resin, Fissurotomy, Carious fissure

I. Introduction

Pit and fissure is considered the area most susceptible to dental caries. Early diagnosis and treatment of pit and fissure caries are essential since it is not easily visible and can rapidly progress downward. Traditional treatment for occlusal caries is very invasive, requiring cutting of not only the carious structure, but also the intact pits and fissures. Recently, there has been a shift toward minimally invasive dentistry to preserve

the tooth structure with the development of adhesive systems and flowable resins with improved properties[1,2].

As the concept of minimally invasive dentistry is becoming more common, the treatment of occlusal caries has shifted into a combination of treatment and prevention by sealing the fissures regardless of the presence of caries. To prevent or treat occlusal fissure caries, the penetration and microleakage of sealants have the greatest impact on treatment success. It is also known that these factors are most strongly affected by

Corresponding author : Sangho Lee

Department of Pediatric Dentistry, School of Dentistry, Chosun University, 309, Pilmundae-ro, Dong-gu, Gwangju, 61452, Republic of Korea

Tel: +82-62-220-3865 / Fax: +82-62-225-8240 / E-mail: shclee@chosun.ac.kr

Received September 1, 2017 / Revised September 22, 2017 / Accepted September 22, 2017

※This research was supported by the research fund from Chosun University, 2017.

the anatomical shape of the fissure. Nagano[3] categorized the shape of occlusal fissures into four types, and suggested that types K and I are more difficult for sealants to penetrate than types U and V. Therefore, the mechanical modification of fissure shape, so called fissurotomy or enameloplasty was suggested to widen the fissure opening and improve the penetration depth of the sealants[4].

Although there is some controversies about the effectiveness of fissurotomy on retention rate of sealants, it is clear that fissurotomy has a positive effect on the penetration of sealant[5-8].

There are no definitive criteria for the treatment of early occlusal caries regarding whether to suppress the progress of a carious lesion through preventive measures or prepare a cavity and fill it with restorative material. Several studies have reported that the sealing of fissure caries inhibits the progression of the carious process[9-11]. However, other studies have reported that the sealing of carious fissures can create secondary caries through microleakage due to a lack of adhesion[12,13]. In order to solve such a problem, some attempts have been made to apply restorative material such as flowable resin using adhesive system to the carious fissure[14].

Recently, the physical properties such as viscosity, modulus of elasticity of flowable resins have improved, allowing them to be used as sealants. When flowable resin is used as a sealant, retention is expected to increase because of good abrasion resistance. However, penetration may be detrimental since the fluidity is relatively weak compare to conventional sealants. So, major concern is focused on the additional techniques such as fissurotomy to compensate the weakness of flowable resin as sealant in both sound and carious fissure.

The aim of this study is to evaluate the effect of fissurotomy on the penetration and microleakage of flowable resins for carious fissures.

II. Materials and methods

1. Materials

A total of 250 premolars with early pit and fissure caries that were extracted for orthodontic purposes were used in this study. Samples were examined by visual inspection, probing, and DIAGNOdent® (Kavo, Biberach, Germany) for the diagnosis of initial caries. The DIAGNOdent® value was measured for each sample on carious fissures in accordance with the

manufacturer's instructions. The diagnostic criteria for initial caries proposed by the manufacturer of DIAGNOdent® ranged between 14 and 20.

Fissurotomy® Original Bur (SS WHITE, USA), Fissurotomy® Miro NTF bur (SS WHITE, USA), SF104R tapered diamond bur (Shofu, Japan), and 1/2 round carbide bur (SS WHITE, USA) were used for the fissurotomy. Two flowable resins (Unifil® Flow, GC, Japan and Filtek®Flow, 3M-ESPE, USA), etchant (Ultra-Etch®, Dentsply, USA), and dentin adhesive (Single Bond®, 3M-ESPE, USA) were used in this study.

2. Sealing of carious fissures with flowable resin

Teeth were randomly assigned to 10 groups of 25 teeth based on the types of flowable resin and fissure preparation method (Table 1). Fissurotomy was performed with the Fissurotomy® Original bur, Fissurotomy® Miro NTF bur, SF104R tapered diamond bur, and 1/2 round carbide bur (Fig. 1), followed by acid etching for 20 s with 35% phosphoric acid, rinsing, and drying. A dentin adhesive was applied to the etched surface and cured for 10 s with BeLite® LED (B&L Biotec, South Korea), followed by placement of flowable resins and curing for 20 s.

3. Assessment of penetration depth and microleakage

Samples were stored in distilled water at room temperature for 24 h and then samples were subject to thermocycling for 500 cycles between 5°C and 55°C water baths for 30 seconds

Table 1. Sample distribution according to the materials and fissure preparation methods

Group	Fissure preparation method	Sample number
Unifil® Flow	I Control - no preparation	25
	II Fissurotomy® Original bur	25
	III Fissurotomy® Miro NTF bur	25
	IV SF104R tapered diamond bur	25
	V 1/2 round carbide bur	25
Filtek® Flow	VI Control - no preparation	25
	VII Fissurotomy® Original bur	25
	VIII Fissurotomy® Miro NTF bur	25
	IX SF104R tapered diamond bur	25
	X 1/2 round carbide bur	25

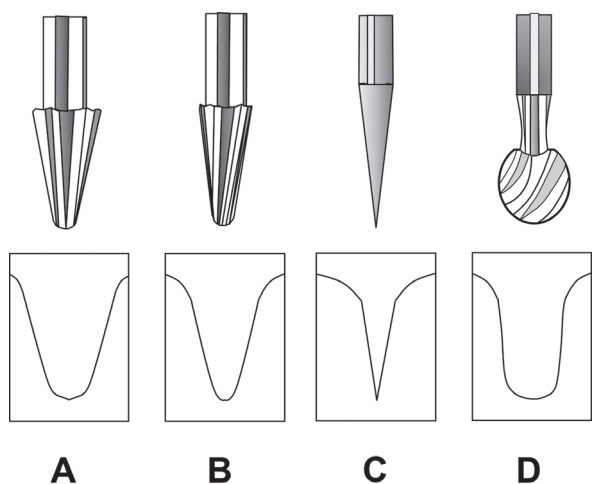


Fig. 1. Fissure preparation types with different burs: A) Fissurotomy® Original Bur, B) Fissurotomy® Micro NTF bur, C) SF 104R tapered diamond bur, and D) 1/2 round carbide bur.

each. All tooth surfaces, excluding 1 mm outside the sealant margin, were coated twice with nail varnish to prevent unnecessary dye penetration into spaces other than the sealant areas, and were then stored in 2% methylene blue dye solution for 24 h. Following immersion, teeth were washed under running water to remove the remaining dye and were then embedded in epoxy resin.

Samples were sectioned in the buccolingual direction with an Isomet low-speed diamond wheel saw (Model 650, South Bay Technology, USA) to expose the vertical section of the fissure, and were then polished with 1000, 1200, 2400, and 4000 grit silicon carbide paper under water cooling. The penetration depth and microleakage of the exposed section were observed using a stereomicroscope (Olympus SZ61®, Japan) at 40 × magnification.

The penetration depth and microleakage were evaluated according to the criteria proposed by Hevinga *et al.*[15] (Fig. 2).

- 0 : No penetration;
- 1 : Penetration down to half of the fissure;
- 2 : Penetration extending beyond half of the fissure;
- 3 : Penetration into the base of the fissure.

4. Evaluation of adaptation

Samples were dried using a vacuum desiccator and plated using an ion sputter with a voltage of 2 kV, current of 20 mA,

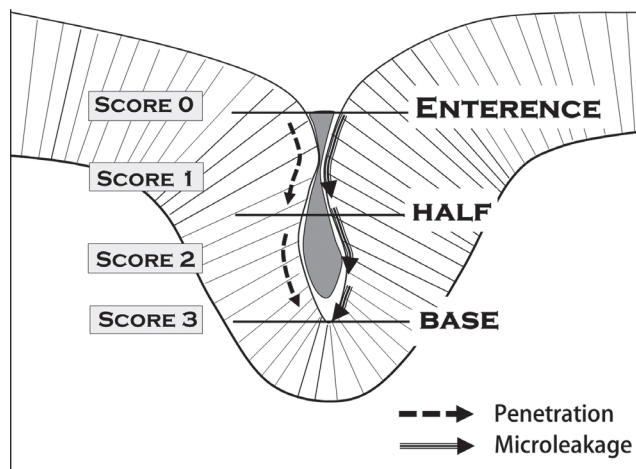


Fig. 2. Schematic diagram of cross-sectioned specimen for measuring the penetration and the microleakage.

and a vacuum status of 4×10^{-2} bar/pa, after which the flowable resin and fissure enamel interface was examined by scanning electron microscopy (JOELJSM-840A, JOEL Co., Japan).

5. Statistical analysis

SPSS (ver. 23.0) was used for data analysis. Statistical significance was set at 95% ($p = 0.05$). Fisher's exact test was used to verify the significance of penetration depth and microleakage among groups, as well as between each group, and the Mann-Whitney test was performed to verify the significance between the types of flowable resin.

III. Results

1. Assessment of penetration depth and microleakage

For the penetration score, control group samples (group I and VI) were mostly distributed at scores of 1 and 2. However, experimental groups were distributed at scores of 2 and 3. The difference in sample distribution between the control and experimental groups showed statistical significance ($p < 0.05$) (Fig. 3).

For Unifil®Flow flowable resin, group V showed deeper penetration than group III and IV ($p < 0.05$). However, there was no significant difference in penetration depth between groups

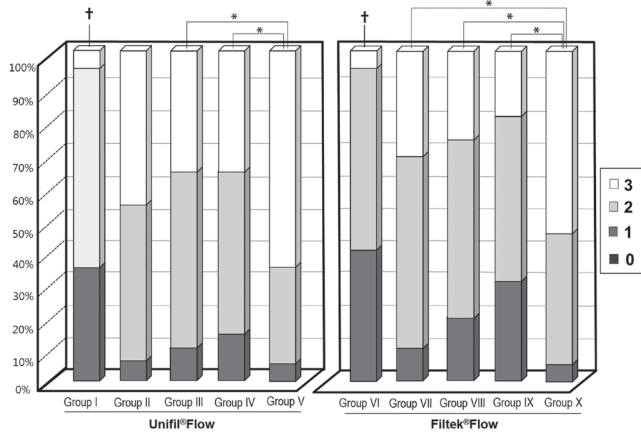


Fig. 3. Comparison of the penetration scores according to fissurotomy methods in each flowable resin.

† : $p < 0.05$ (Fisher's exact test) between control group (I) and each experimental group (II, III, IV, V) in Unifil®Flow; between control group (VI) and each experimental group (VII, VIII, IX, X) in Filtek®Flow.

* : $p < 0.05$ (Fisher's exact test) between experimental group.

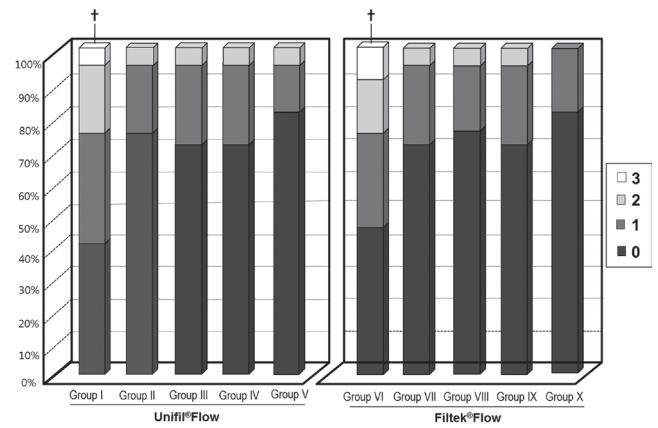


Fig. 4. Comparison of microleakage according to fissurotomy methods in each flowable resin.

† : $p < 0.05$ (Fisher's exact test) between control group (I) and each experimental group (II, III, IV, V) in Unifil®Flow; between control group (VI) and each experimental group (VII, VIII, IX, X) in Filtek®Flow.

Table 2. Comparison of the penetration scores between the Unifil®Flow and Filtek® Flow flowable resin

Flowable resin	N	Mean ± SD	p value
Unifil®Flow	125	2.67 ± 0.67	0.0235*
Filtek®Flow	125	2.04 ± 0.32	

Mann-Whitney test (* : $p < 0.05$)

Table 3. Comparison of microleakage between Unifil® Flow and Filtek® Flow flowable resin

Flowable resin	N	Mean ± SD	p value
Unifil®Flow	125	0.55 ± 0.17	0.5317
Filtek®Flow	125	0.49 ± 0.45	

p value from Mann-Whitney test

V and II. For Filtek®Flow flowable resin, group X showed the highest penetration depth among the experimental groups ($p < 0.05$) (Fig. 3).

For the penetration depth according to the type of flowable resin, the mean score of the Unifil®Flow flowable resin was 2.67 ± 0.67 , which was greater than that of the Filtek®Flow flowable resin with 2.04 ± 0.32 ($p < 0.05$) (Table 2).

For the microleakage, control group samples were evenly distributed at all scores (0 - 3); however, experimental group samples were distributed at a score of 0 and not a score of 3. Experimental groups showed lower microleakage scores than the control group ($p < 0.05$) and there were no significant differences in microleakage scores among experimental groups (Fig. 4). For the microleakage according to flowable resin types, there were no significant differences between groups (Table 3).

2. Assessment of the adaptation

Many samples in the control group showed incomplete penetration of flowable resin into the fissure, particularly samples with long and narrow fissures. Experimental groups generally showed better penetration and closer contact with the fissure wall than the control group; however, there were some differences according to the shape of the fissure prepared by the various burs (Fig. 5 - Fig. 7).

In the control group, loose adaptation of flowable resin to the fissure wall was observed in some samples and the degree of penetration was affected by the shape of the fissure (Fig. 5A, Fig. 7A).

Dentin adhesive was observed between flowable resin and the fissure base, as well as between flowable resin and the fissure wall, which compensated for insufficient penetration and adaptation of flowable resin (Fig. 6, Fig. 7B).

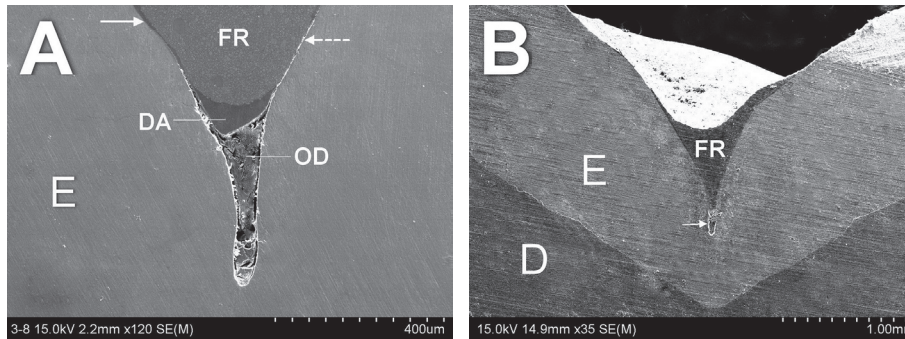


Fig. 5. SEM image of a fissure. A. Control group sample showing incomplete penetration of flowable resin into the fissure. Dentin adhesive penetrated more deeply into the fissure and filled the gap between flowable resin and the fissure wall (solid arrow). Loose adaptation between flowable resin and fissure enamel was observed, which can lead to microleakage (dotted arrow) (scale interval 40 μ m). B. Sample of fissurotomy with a taped diamond bur showing incomplete penetration of flowable resin into the fissure base. Initial carious enamel was not completely removed (arrow) (scale interval 100 μ m). E : Enamel, D : Dentin, FR : Flowable resin, DA : Dentin adhesive, OD : Organic debris

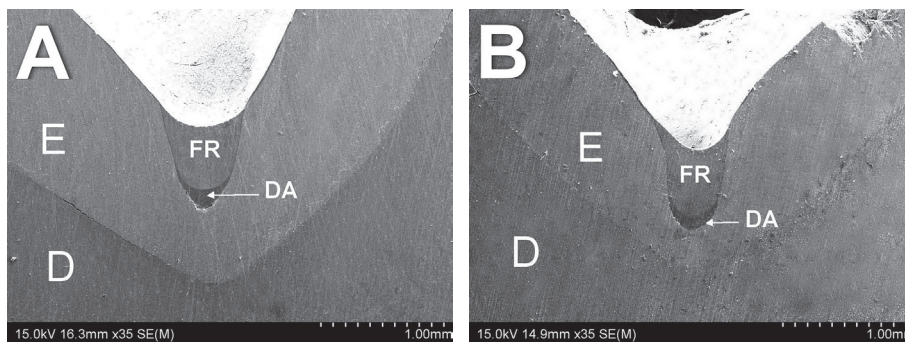


Fig. 6. SEM image of a fissure prepared using Fissurotomy[®] Original Bur (A) and 1/2 round carbide bur (B) with a U-shape and proper penetration of flowable resin (scale interval 100 μ m). Dentin adhesive was flowed into the base of the fissure (arrow). E : Enamel, D : Dentin, FR : Flowable resin, DA : Dentin adhesive

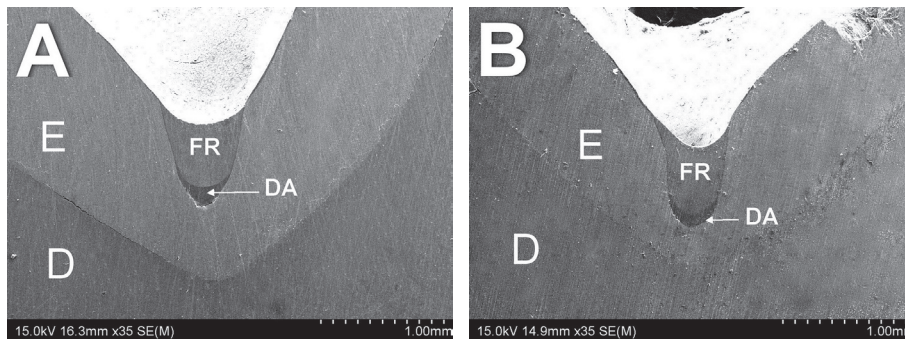


Fig. 7. SEM image of the fissure walls showing (A) poor adaptation of flowable resin to carious fissure enamel (arrow) in the control group and (B) tight adaptation of flowable resin to fissure enamel in the fissurotomy groups (scale interval 5 μ m). A thin layer of dentin adhesive is present, leading to proper adaptation between the fissure enamel and flowable resin (B). E : Enamel, FR : Flowable resin, DA : Dentin adhesive

IV. Discussion

As the flowable resin has become more popular, its range of use is expanded from restorative material for cavity to sealing material for occlusal fissure. Recently, flowable resin tends to be used for sealing the occlusal carious fissure in conjunction with non-invasive preparation.

This study was performed to evaluate the effect of fissurotomy on the penetration and microleakage of flowable resins for carious fissures. In the present study, the penetration score was higher in groups with fissurotomy than in groups without it for both Unifil®Flow and Filtek®Flow flowable resins. This suggests that mechanical preparation of the fissure is more favorable for increasing the penetration of flowable resin by achieving widening and smoothening of the fissure wall, as well as removing organic materials from the fissure[16,17].

In the present study, fissurotomy with a 1/2 round carbide bur showed higher penetration depth compared with other burs in both Unifil®Flow and Filtek®Flow flowable resin. This result indicated that a U-shape fissure formed by a 1/2 round carbide bur is more favorable for flowable resin to flow into the fissure than the V-shape fissure formed by other fissurotomy burs or a tapered diamond bur. However, there were no differences between the preparation burs regarding microleakage. This suggests that penetration does not necessarily affect microleakage. Unlike some studies on conventional sealant in healthy fissures, it is possible that the shape of the bur affects the penetration of flowable resin in carious fissures[18]. When comparison was done between Unifil®Flow and Filtek®Flow, the former showed higher penetration score. According to the technical product files provided by the manufacturers, viscosities at 40 gf for 90 seconds are 33.5 mm for Unifil®Flow and 26.4 mm for Filtek®Flow. This indicated that the flow of Unifil®Flow is better than that of Filtek®Flow when used as a fissure sealant, and this difference in flowability is reflected in our results. Several reports[19,20] demonstrated significant correlation between retention of sealant and its viscosity.

When comparing microleakage, the fissurotomy groups showed less microleakage than the control group. This decrease in microleakage in the fissurotomy groups can be explained by removing the porous component of early carious lesions and debris that increased the micromechanical bonding of the flowable resin to fissure enamel. Another reason for better microleakage of flowable resin placed on the enlarged fissures by fissurotomy could be explained that removal of

prismless enamel from the outmost layer of the fissure enamel enhanced the etching effect[21,22].

It was observed in SEM findings that a few samples of control group showed loose adaptation of the flowable resin to fissure wall. This is considered to be a lack of micromechanical bonding due to the increased porosity of carious enamel and organic materials in the fissure wall[23]. We observed that dentin adhesive responsible for filling the gap between flowable resin and fissure wall or fissure base. Further study is needed as to whether the dentin adhesive can play a role in enhancing adhesion in carious fissures.

In this study, fissurotomy clearly affects the penetration and microleakage of flowable resin, but in clinical practice, technical sensitivity of fissurotomy may not show the consistent result depending on the dentists. If the fissurotomy is performed too shallow then the materials cannot penetrate as intended. In contrast, if the fissurotomy is performed too deep or wide, healthy structures may be removed and the quantity of materials would increase, resulting in increasing polymerized shrinkage and microleakage.

The limitation of this study is considered to be difficulty for standardization of samples because of the variety in fissure shape of natural teeth.

V. Conclusions

Based on this in vitro comparative study, fissurotomy can increase the penetration depth of flowable resin and decrease the microleakage in carious fissures. Fissure preparation with a 1/2 round bur showed the deepest penetration of flowable resin into the carious fissure, but fissure preparation methods did not show any difference in microleakage. There was a significant difference in penetration depth between the two flowable resins (Unifil®Flow and Filtek®Flow), but there was no significant difference in microleakage.

References

1. Frencken JE, Peters MC, Eden E, *et al.* : Minimal intervention dentistry for managing dental caries - a review : report of a FDI task group. *Int Dent J*, 62:223-243, 2012.
2. Holmgren C, Gaucher C, Decerle N, Doméjean S : Minimal intervention dentistry II: part 3. Management of non-cavitated (initial) occlusal caries lesions--non-invasive approaches through remineralisation and therapeutic sealants.

- Br Dent J*, 216:237-243, 2014.
3. Nagano T : The form of pit and fissure and the primary lesion of caries. *Dent Abstract*, 6:426, 1960.
 4. Feldens EG, Feldens CA, de Araujo FB, *et al.* : Invasive technique of pit and fissure sealants in primary molars: a SEM study. *J Clin Pediatr Dent*, 18:187-190, 1994.
 5. Khanna R, Pandey RK, Singh N, Agarwal A : A comparison of enameloplasty sealant technique with conventional sealant technique: a scanning electron microscope study. *J Indian Soc Pedod Prev Dent*, 27:158-163, 2009.
 6. Bagherian A, Akbari M, Rezaeian M, Ansari G : Microleakage assessment of fissure sealant following fissurotomy bur or pumice prophylaxis use before etching. *Dent Res J (Isfahan)*, 10:643-646, 2013.
 7. Chaitra TR, Subba RV, Devarasa GM, Ravishankar TL : Flowable resin used as a sealant in molars using conventional, enameloplasty and fissurotomy techniques: an in vitro study. *J Indian Soc Pedod Prev Dent*, 28:145-150, 2010.
 8. Nahid A, Zahra BG, Yasaman R : Evaluation of the effect of enamel preparation on retention rate of fissure sealant. *Contemp Clin Dent*, 3:380-382, 2012.
 9. Beauchamp J, Caufield PW, Crall JJ, *et al.* : Evidence-based clinical recommendations for the use of pit-and-fissure sealants: a report of the American Dental Association Council on Scientific Affairs. *J Am Dent Assoc*, 139:257-268, 2008.
 10. Borges BC, de Souza Borges J, Braz R, *et al.* : Arrest of non-cavitated dentinal occlusal caries by sealing pits and fissures: a 36-month, randomised controlled clinical trial. *Int Dent J*, 62:251-255, 2012.
 11. Zhang Z, Zheng K, Li E, *et al.* : Mechanical benefits of conservative restoration for dental fissure caries. *J Mech Behav Biomed Mater*, 53:11-20, 2016.
 12. Celiberti P, Lussi A : Penetration ability and microleakage of a fissure sealant applied on artificial and natural enamel fissure caries. *J Dent*, 35:59-67, 2007.
 13. Hesse D, Bonifácio CC, Mendes FM, *et al.* : Sealing versus partial caries removal in primary molars: a randomized clinical trial. *BMC Oral Health*, 28:14-58, 2014.
 14. Lowe RA : Fissurotomy and flowable composite resin: a new standard for the restoration of pit and fissure decay. *Dent Today*, 20:66-71, 2001.
 15. Hevinga MA, Opdam NJ, Frencken JE, *et al.* : Microleakage and sealant penetration in contaminated carious fissures. *J Dent*, 35:909-914, 2007.
 16. Loyola-Rodriguez JP, Mendoza-Razo V, Rodriguez-Juarez F, Campos-Cambranis R : Flowable resin used as a sealant in molars affected by dental fluorosis: a comparative study. *J Clin Pediatr Dent*, 30:39-43, 2005.
 17. Chaitra TR, Subba RV, Devarasa GM, Ravishankar TL : Microleakage and SEM analysis of flowable resin used as a sealant following three fissure preparation techniques--an in vitro study. *J Clin Pediatr Dent*, 35:277-282, 2011.
 18. Zervou C, Kugel G, Leone C, *et al.* : Enameloplasty effects on microleakage of pit and fissure sealants under load: an in vitro study. *J Clin Pediatr Dent*, 24:279-285, 2000.
 19. Sridhar LP, Moses J, Rangeeth BN, Sivakumar S : Comparative evaluation of the marginal sealing ability of two commercially available pit and fissure sealants. *J Clin Diagn Res*, 10:ZC01-ZC04, 2016.
 20. Mehrabkhani M, Mazhari F, Sadeghi S, Ebrahimi M : Effects of sealant, viscosity, and bonding agents on microleakage of fissure sealants: An in vitro study. *Eur J Dent*, 9 : 558-563, 2015.
 21. Burrow MF, Burrow JF, Makinson OF : Pits and fissures: Etch resistance in prismless enamel walls. *Aust Dent J*, 46:258-262, 2001.
 22. Cho TS, Lee SH, Yoon JH, Kim SG : Ultra-structure and etching characteristics of occlusal fissure enamel. *J Korean Acad Pediatr Dent*, 32:321-331, 2005.
 23. Michalaki MG, Oulis CJ, Lagouvardos P : Microleakage of three different sealants on sound and questionable occlusal surfaces of permanent molars: an in vitro study. *Eur Arch Paediatr Dent*, 11:26-31, 2010.

국문초록

교합면 우식열구에서 열구성형술 방법에 따른 유동성 레진의 침투도와 미세누출 평가

권세옥¹ · 이상호¹ · 이난영¹ · 지명관¹ · 윤영미²

¹조선대학교 치의학전문대학원 소아치과학교실

²조선대학교 대학원 치의학과

본 연구의 목적은 교합면 우식열구에서 열구성형술이 유동성 레진의 침투와 미세누출에 미치는 영향을 평가하는데 있다. 교합면 우식증이 있는 발거된 소구치 250개를 대상으로 열구 성형술을 시행하지 않는 군을 대조군(n = 50), 열구성형술을 시행한 군을 실험군으로 하였으며, 실험군은 Fissurotomy® original bur (n = 50), Fissurotomy® Miro NTF bur (n = 50), SF104R tapered diamond bur (n = 50), 1/2 round carbide bur (n = 50) 등 4가지 유형의 bur를 이용하여 열구성형술을 시행한 후 2가지 종류의 유동성 레진(UniFil®Flow, Filtek®Flow)을 적용하고 침투도와 미세누출의 평가를 통하여 전색효과를 비교하였다. 열구성형술을 시행한 군이 시행하지 않은 대조군에 비해 침투도가 컸으며 미세누출은 적었다. 1/2 round bur를 사용하여 열구성형술을 시행한 군이 다른 bur를 사용한 군에 비해 유동성 레진의 열구내로의 침투도는 높았으나 미세누출은 차이가 없었다. 유동성 레진의 종류(UniFil®Flow와 Filtek®Flow)에 따른 침투도의 차이는 있었으나 미세누출은 차이가 없었다.