



Technical Note

Removal of cobalt ions from aqueous solution using chitosan grafted with maleic acid by gamma radiationShuting Zhuang ^a, Yanan Yin ^a, Jianlong Wang ^{a, b,*}^a Collaborative Innovation Center for Advanced Nuclear Energy Technology, INET, Tsinghua University, Beijing 100084, PR China^b Beijing Key Laboratory of Radioactive Waste Treatment, INET, Tsinghua University, Beijing 100084, PR China**ARTICLE INFO****Article history:**

Received 5 February 2017

Received in revised form

30 October 2017

Accepted 17 November 2017

Available online 8 December 2017

Keywords:

Adsorption

Biosorbent

Chitosan

Cobalt

Gamma Radiation

Grafting

ABSTRACT

Chitosan was modified by gamma radiation-induced grafting with maleic acid and then used for the removal of cobalt ions from aqueous solutions. Chitosan-g-maleic acid was characterized by Fourier Transform infrared spectroscopy (FT-IR). The effect of the dose (1–5 kGy) and monomer concentration (0.3–1.3%, m/v) on the grafting ratio was examined. The adsorption kinetics and isotherms were also investigated. The results showed that the optimal dose for grafting was 2 kGy. When monomer concentration was within the range of 0.3–1.3% (m/v), the grafting ratio increased almost linearly. For the adsorption of cobalt ions by chitosan-g-maleic acid beads, the pseudo second-order kinetic model ($R^2 = 0.99$) and Temkin isotherm model ($R^2 = 0.96$) were able to fit the experimental data reasonably well. The equilibrium adsorption capacity of cobalt ions increased from 2.00 mg/g to 2.78 mg/g after chitosan modification.

© 2018 Korean Nuclear Society, Published by Elsevier Korea LLC. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

^{60}Co is a typical radioisotope that is common in the wastewater of nuclear power plants. Because of its radioactivity and long half-life, it can do prolonged damage to the ecosystem. Various methods have been studied to remove cobalt ions from wastewater [1–5]. Adsorption is commonly used to remove it from aqueous solutions [6,7]. With their great biocompatibility, nontoxicity, and availability abundance, natural biopolymers have been received increasing attention in recent years [8–10].

Chitosan is the deacetylation product of chitin, which is the second most abundant natural biopolymer. With large amounts of amino and hydroxyl functional groups, chitosan is a good adsorbent for heavy metal ions [11]. In addition, modifying chitosan is an important way to improve its properties and increase its adsorption capacity [12–14].

Although there are many ways to modify chitosan, grafting is one of the most important methods. Various materials have been studied for the purpose of increasing chitosan's adsorption capacity of heavy metal ions [10,15]. When grafting was achieved, new

functional groups were incorporated into the backbone of chitosan; this not only changed the pH range for the adsorption of metal ions but also added more adsorption sites. Different functional groups, including carboxylate, hydroxyl, sulfate, phosphate, amide, and amino, in the polymeric materials are responsible for metal adsorption via coordination or electrostatic attraction [6,16–18]. So far, our group has by various methods successfully modified chitosan to increase its adsorption capacity for removal of heavy metals and radioisotopes from aqueous solutions [15,18–22].

Compared with conventional chemical routines, the radiation method, in which neither chemical initiators nor cross-linkers are needed, has several advantages. For example, the products are free of toxic additives. The radiation-induced modification of chitosan through grafting with either vinyl or acrylate monomers has been investigated [23–26]. Considering that chitosan is already rich in amino groups, it is interesting to incorporate carboxyl groups into chitosan [27–29]. Chitosan modification via grafting with maleic acid has not been studied yet; maleic acid, which is rich in carboxyl groups, may be useful to improve the adsorption of heavy metal ions.

The objective of this study was to explore the feasibility of using gamma radiation to graft maleic acid onto chitosan and to evaluate the performance of the resulting material for cobalt ion adsorption.

* Corresponding author.

E-mail address: wangjl@tsinghua.edu.cn (J. Wang).

2. Materials and methods

2.1. Chemicals

Chitosan (molecular weight: 130 kDa, degree of deacetylation: 90%), acetic acid, and sodium hydroxide were purchased from Sinopharm Chemical Reagent Co. Ltd (China). Maleic acid and cobalt chloride were purchased from Aladdin (China). All chemicals were used as received without further purification.

2.2. Radiation grafting

Chitosan powder and maleic acid were dissolved in 1% acetic acid solution (v/v) and irradiated under a certain dose rate (31.98 Gy/min) for a given time at the Institute of Nuclear and New Energy Technology (INET), Tsinghua University, Beijing, China. After irradiation, the pH of the grafted solution was adjusted to 10–12 by adding 15% NaOH solution (m/v). The precipitate was separated by filtration and washed with distilled water several times to remove unreacted monomers and homopolymer. Then, it was dried in an air oven at 50°C to a constant weight. The percentage of grafting was calculated by the following equation:

$$\text{grafting ratio}(\%) = (W_2 - W_1)/W_1 \quad (1)$$

where W_1 and W_2 are the weights of chitosan and grafted chitosan, respectively.

2.3. Preparation of chitosan beads

Grafted chitosan (1 kGy and 1% m/v monomer concentration) was dissolved in 6% acetic acid (v/v) to form a mixed solution (5%, w/v) and stirred for 3 hours. After bubbles arising from the agitation had disappeared, the mixed solution was injected into 15% NaOH solution (m/v). The chitosan-g-maleic acid beads were washed with distilled water to eliminate any remaining sodium hydroxide. Then they were dried in an air oven at 50°C to a constant weight.

The preparation of chitosan beads was similar, except that the grafted chitosan was replaced with chitosan.

2.4. Co^{2+} adsorption experiments

Co^{2+} adsorption experiments were carried out by adding chitosan-g-maleic acid or chitosan beads to CoCl_2 solution at 26°C; solution was then shaken at a rate of 150 rpm for a given time. The adsorption capacity (q_t) and equilibrium adsorption capacity (q_e) can be calculated by the following equations:

$$q_t = (C_0 - C_t)V/m \quad (2)$$

$$q_e = (C_0 - C_e)V/m \quad (3)$$

where C_0 , C_e , and C_t are the initial concentration, equilibrium concentration, and concentration of cobalt ions at time t , respectively; V is the volume of the solution; m is the mass of the dry adsorbents.

2.5. Analytical methods

To study the structure of the grafted polymer, FT-IR spectra were obtained by a VERTEX 70 FT-IR (Bruker). The concentration of cobalt ions was measured using a ZA3000 Polarized Zeeman Atomic Absorption Spectrophotometer (HITACHI, Japan).

3. Results and discussion

3.1. FT-IR analysis

The FT-IR spectra are shown in Fig. 1. The main characteristic bands of chitosan were $3,413\text{ cm}^{-1}$, $2,877\text{ cm}^{-1}$, and $1,659\text{ cm}^{-1}$, which were assigned to O-H stretching vibration, polymer backbone C-H stretching vibration, and N-H bending vibration, respectively [24,30,31]. In addition to the characteristic bands of chitosan, the spectrum of chitosan-g-maleic acid exhibited newly added bands at $1,572\text{ cm}^{-1}$ and $1,432\text{ cm}^{-1}$, which may be due to the COO asymmetrical stretch vibration and COH in-plane bending vibration in carboxyl groups, respectively. Besides this, the disappeared band at $1,659\text{ cm}^{-1}$ in the chitosan-g-maleic acid spectrum indicated that maleic acid might be connected to the amino group [27].

3.2. Effect of dose

The effect of the dose on grafting is depicted in Fig. 2. The concentrations of maleic acid and chitosan were both 1% (m/v). With increasing of the dose from 1 kGy to 2 kGy, the grafting percentage increased at the same time. With further increases of the dose, an obvious decrease in the grafting ratio was observed. As is well-known, graft polymerization is initiated by radicals produced by irradiation and radical reactions [32]. Thus, the grafting yield depended on the number of radicals formed in the system. With the increase of the absorbed dose, the radicals formed in the system increased, which resulted in the increase of the grafting yield. At lower doses, the increase of the grafting percentage may be due to the increasing concentration of free radicals formed in the polymeric solution. It has been reported that the grafting process and the polymerization reaction take place at the same time during irradiation [33]. Beyond a certain dose value (2 kGy), the rate of homopolymerization may exceed that of the grafting reaction, resulting in a decrease in the grafting percentage. A similar trend was observed by Casimiro et al. [34].

3.3. Effect of monomer concentration

The effect of the monomer concentration on the grafting ratio was studied at 2 kGy and 1% chitosan (m/v); the results are presented in Fig. 3. It can be seen that the grafting percentage

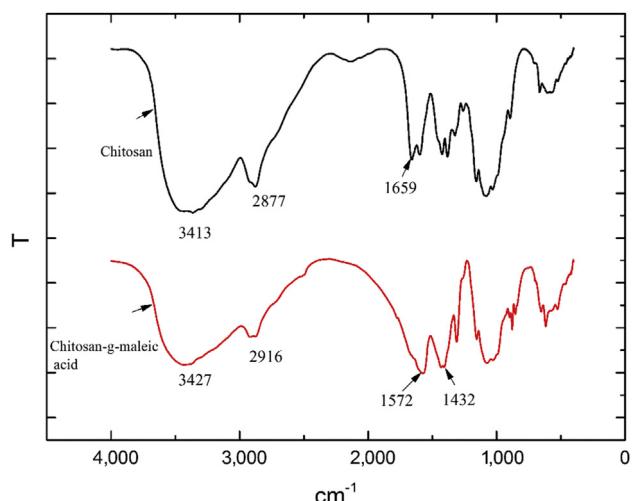


Fig. 1. FT-IR spectra of chitosan and chitosan-g-maleic acid.

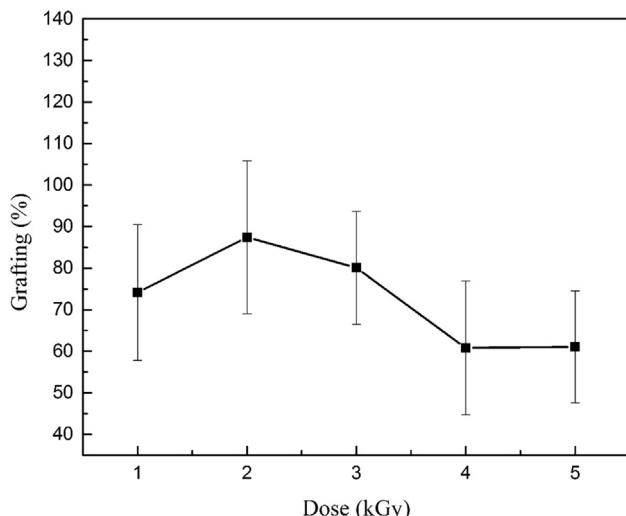


Fig. 2. Effect of dose on grafting ratio.

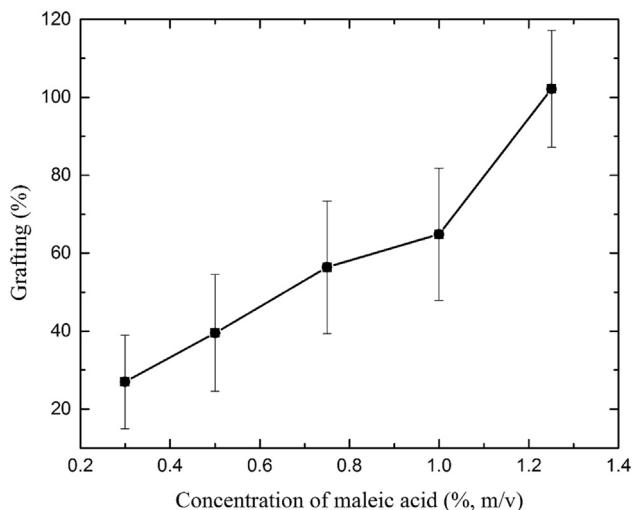


Fig. 3. Effect of monomer concentration on grafting ratio.

increased with the increase of concentration of maleic acid from 0.3–1.3% (m/v). A similar trend was observed for the other grafting systems [32,35,36]. In this study, the amount of maleic acid in contact with the chitosan backbones increased when the dosage of the monomer increased; eventually, the grafting yield increased. That is to say, the effect of the grafting of a monomer onto chitosan depends on the availability of maleic acid in the vicinity of the polymers. The increase of monomer concentration will lead to an increase of grafting percentage.

3.4. Adsorption kinetics

The adsorption of cobalt ions by chitosan-g-maleic acid beads and chitosan beads is presented in Fig. 4. After exposure to the solution for 30 minutes, both materials reached adsorption equilibrium. Modified chitosan showed higher adsorption capacity for cobalt ions than that of chitosan beads.

Adsorption kinetics is important in the illustration of the mechanism of the adsorption processes. Various researchers have found that the pseudo second-order model can better describe the adsorption process of metal ions by chitosan [14,18]. There has been an assumption regarding the second-order dependence of the

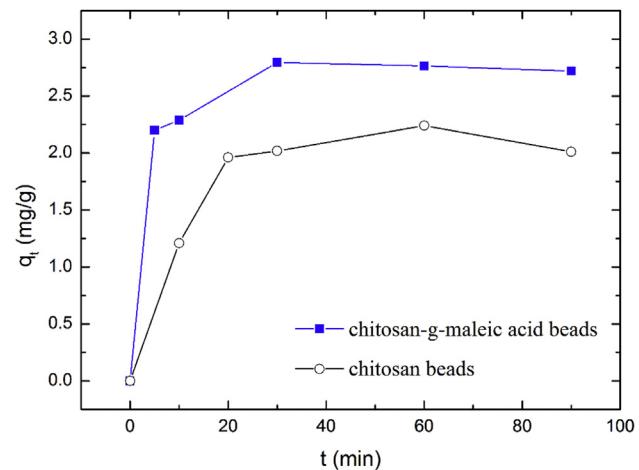


Fig. 4. Effect of contact time on Co²⁺ adsorption.

sorption rate on the available sites; the linearized form of the pseudo second-order model is shown as follows:

$$\frac{t}{q} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e} \quad (4)$$

where k_2 is the pseudo second-order constant (g/mg/min); q_t and q_e refer to the amount of Co²⁺ adsorbed (mg/g) at any time t (min) and equilibrium.

As shown in Table 1, the experimental data can be well-fitted with the pseudo second-order model for chitosan beads with ($R^2 = 0.97$) and chitosan-g-maleic acid beads ($R^2 = 0.99$), suggesting that chemical sorption plays an important role in the rate-limiting step of adsorption. The coordination between carboxyl groups and heavy metal ions has been reported widely (Pepo et al. 2011) [37]. With the modification of maleic acid, the equilibrium adsorption capacity (q_e) of cobalt ions on modified chitosan increased from 2.00 mg/g to 2.78 mg/g, which may be due to the combination of carboxyl groups induced by irradiation. However, the obtained q_e for similar adsorption conditions was lower than in our previous study on carboxyl grafted chitosan (7.97 mg cobalt ions/EDTA modified chitosan beads) [38] synthesized via chemical method rather than irradiation. This implies that to improve the adsorption capacity, grafting is an effective method. However, more adsorption sites mean more than just more functional groups; they also indicate a proper structure that makes the adsorption sites available. There is a lot of room for improvement of the adsorption capacity of grafting chitosan via irradiation. This research offers us insights that can be used in future research.

3.5. Adsorption isotherms

The commonly used adsorption isotherms, including the Langmuir, the Freundlich, and the Temkin models, were used to study the adsorption isotherms of chitosan beads; their linearized forms can be expressed as follows:

$$\ln q_e = \frac{1}{n} \ln C_e + \ln K_F \quad (5)$$

$$\frac{C_e}{q_e} = \frac{1}{q_m K_L} + \frac{C_e}{q_m} \quad (6)$$

$$q_e = A + B \ln C_e \quad (7)$$

Table 1Adsorption kinetic parameters for Co^{2+} adsorption

| Model | Linearized forms | Parameters | Chitosan-g-maleic acid beads | Chitosan beads |
|---------------------------|---|--------------------------------|------------------------------|----------------------|
| Pseudo second-order model | $\frac{t}{q} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e}$ | k_2 q_e (mg/g) R^2 | 0.32 2.78 0.99 | 0.13 2.00 0.97 |

Table 2Adsorption isotherm parameters for Co^{2+} adsorption.

| Models | Linearized forms | Parameters | Values |
|------------|---|--------------------------|----------------|
| Temkin | $q_e = A + B \ln C_e$ | A (L/g) B (J/mol) | -28.31 9.23 |
| Freundlich | $\ln q_e = \frac{1}{n} \ln C_e + \ln K_F$ | K_F (L/mg) n | 0.60 0.01 |
| Langmuir | $\frac{C_e}{q_e} = \frac{1}{q_m K_L} + \frac{C_e}{q_m}$ | K_L q_m (mg/g) | 0.01 — |
| | | R^2 | 0.36 |

where K_F (L/mg) is the Freundlich constant, describing the sorption capacity; and n is the Freundlich constant, an indicator of the heterogeneity of the sorbent surface; q_m (mg/g) and K_L (L/mg) are the maximum monolayer capacity of the adsorbent and the affinity constant, respectively; A (L/g) is the Temkin equilibrium binding constant and B (J/mol) is Temkin constant related to the heat of sorption.

As shown in Table 2, the Temkin model had the best fit for all the results ($R^2 = 0.96$), indicating that the multilayer adsorption of cobalt ions on adsorption sites had different energies at every different layer. Besides this, the Freundlich model proved to be the second best one ($R^2 = 0.90$), while the Langmuir model was not good for fitting the data ($R^2 = 0.36$). Results showed that the multilayer adsorption model was preferred over the single-layer adsorption model to explain this adsorption process. Due to the rather poor fitting coefficient, the fitting results for Langmuir parameter have no meaning.

4. Conclusions

Gamma radiation-induced grafting can be used to modify chitosan to increase its adsorption capability. Chitosan-g-maleic acid was prepared and characterized by FT-IR analysis. The effects of the dose and monomer concentration on grafting were examined. The pseudo second-order kinetic model ($R^2 = 0.99$) and the Temkin isotherm model ($R^2 = 0.96$) can be used to describe the adsorption of cobalt ions onto chitosan-g-maleic acid beads. After modification, the adsorption capacity of Co^{2+} by the grafted chitosan beads increased from 2.00 mg/g to 2.78 mg/g.

Conflict of interest

There is no conflict of interest.

Acknowledgments

The research was supported by the National Natural Science Foundation of China (51578307), the National Key Research and Development Program (2016YFC1402507), the Program for Changjiang Scholars and Innovative Research Team in University (IRT-13026), and the National S&T Major Project (2013ZX06002001).

References

- C.L. Chen, D. Xu, X.L. Tan, X.K. Wang, Sorption behavior of Co(II) on gamma-Al₂O₃ in the presence of humic acid, *J. Radioanal. Nucl. Chem.* 273 (2007) 227–233.
- C. Cojocaru, G. Zakrzewska-Trznadel, A. Miskiewicz, Removal of cobalt ions from aqueous solutions by polymer assisted ultrafiltration using experimental design approach Part 2: optimization of hydrodynamic conditions for a crossflow ultrafiltration module with rotating part, *J. Hazard. Mater.* 169 (2009) 610–620.
- T. Missana, M. Garcia-Gutierrez, Adsorption of bivalent ions (Ca(II), Sr(II) and Co(II)) onto FEBEX bentonite, *Phys. Chem. Earth* 32 (2007) 559–567.
- M. Xing, J.L. Wang, Nanoscaled zero valent iron/graphene composite as an efficient adsorbent for Co(II) removal from aqueous solution, *J. Colloid Interface Sci.* 474 (2016) 119–128.
- G. Zakrzewska-Trznadel, Advances in membrane technologies for the treatment of liquid radioactive waste, *Desalination* 321 (2013) 119–130.
- J.L. Wang, C. Chen, Biosorbents for heavy metals removal and their future, *Biotechnol. Adv.* 27 (2009) 195–226.
- M. Xing, J.L. Xu, J.L. Wang, Mechanism of Co(II) adsorption by zero valent iron/graphene nanocomposite, *J. Hazard. Mater.* 301 (2016) 286–296.
- B. An, H. Lee, S. Lee, S.H. Lee, J.W. Choi, Determining the selectivity of divalent metal cations for the carboxyl group of alginate hydrogel beads during competitive sorption, *J. Hazard. Mater.* 298 (2015) 11–18.
- A.D. Augst, H.J. Kong, D.J. Mooney, Alginate hydrogels as biomaterials, *Macromol. Biosci.* 6 (2006) 623–633.
- J.L. Wang, C. Chen, Chitosan-based biosorbents: modification and application for biosorption of heavy metals and radionuclides, *Bioresour. Technol.* 160 (2014) 129–141.
- Y.H. Zhu, J. Hu, J.L. Wang, Removal of Co^{2+} from radioactive wastewater by polyvinyl alcohol (PVA)/chitosan magnetic composite, *Prog. Nucl. Energy* 71 (2014) 172–178.
- Y.H. Gad, Preparation and characterization of poly (2-acrylamido-2-methylpropane-sulfonic acid)/chitosan hydrogel using gamma irradiation and its application in wastewater treatment, *Radiat. Phys. Chem.* 77 (2008) 1101–1107.
- T.B. Mostafa, H.F. Naguib, M.W. Sabaa, S.M. Mokhtar, Graft copolymerization of itaconic acid onto chitin and its properties, *Polym. Int.* 54 (2005) 221–225.
- H.H. Sokker, N.M. El-Sawy, M.A. Hassan, B.E. El-Anadouli, Adsorption of crude oil from aqueous solution by hydrogel of chitosan based polyacrylamide prepared by radiation induced graft polymerization, *J. Hazard. Mater.* 190 (2011) 359–365.
- Y.W. Chen, J.L. Wang, Removal of radionuclide Sr^{2+} ions from aqueous solution using synthesized magnetic chitosan beads, *Nucl. Eng. Des.* 242 (2012) 445–451.
- V.A. Izvozchikova, N.V. Pastukhova, S.A. Ryabov, Y.D. Semchikov, L.A. Smirnova, A.E. Mochalova, Flocculation power of chitosan and its derivatives in mixtures with anionic flocculants, *Russ. J. Appl. Chem.* 76 (2003) 1784–1786.
- T. Kume, N. Nagasawa, F. Yoshi, Utilization of carbohydrates by radiation processing, *Radiat. Phys. Chem.* 63 (2002) 625–627.
- Y.H. Zhu, J.L. Wang, Competitive adsorption of Pb(II), Cu(II) and Zn(II) onto xanthate-modified magnetic chitosan, *J. Hazard. Mater.* 221 (2012) 155–161.
- Y.W. Chen, J.L. Wang, Preparation and characterization of magnetic chitosan nanoparticles and its application for Cu(II) removal, *J. Chem. Eng.* 168 (2011) 286–292.
- Y.W. Chen, J.L. Wang, The characteristics and mechanism of Co(II) removal from aqueous solution by a novel xanthate-modified magnetic chitosan, *Nucl. Eng. Des.* 242 (2012) 452–457.
- F. Jia, J.F. Li, J.L. Wang, Y.L. Sun, Removal of cesium from simulated radioactive wastewater using a novel disc tubular reverse osmosis system, *Nucl. Technol.* 197 (2017) 219–224.
- F. Jia, J.L. Wang, Separation of cesium ions from aqueous solution by vacuum membrane distillation process, *Prog. Nucl. Energy* 98 (2017) 293–300.
- T.T. Hanh, H.T. Huy, N.Q. Hien, Pre-irradiation grafting of acrylonitrile onto chitin for adsorption of arsenic in water, *Radiat. Phys. Chem.* 106 (2015) 235–241.
- A. Khan, T. Huq, R.A. Khan, D. Dussault, S. Salmieri, M. Lacroix, Effect of gamma radiation on the mechanical and barrier properties of HEMA grafted chitosan-based films, *Radiat. Phys. Chem.* 81 (2012) 941–944.
- P.F. Liu, M.L. Zhai, J.L. Wu, Study on radiation-induced grafting of styrene onto chitin and chitosan, *Radiat. Phys. Chem.* 61 (2001) 149–153.
- M.P. Pérez-Calixto, A. Ortega, L. García-Uriostegui, G. Burillo, Synthesis and characterization of N-vinylcaprolactam/N,N-dimethylacrylamide grafted onto chitosan networks by gamma radiation, *Radiat. Phys. Chem.* 119 (2016) 228–235.
- H.C. Ge, T.T. Hua, Synthesis and characterization of poly(maleic acid)-grafted crosslinked chitosan nanomaterial with high uptake and selectivity for Hg(II) sorption, *Carbohydr. Polym.* 153 (2016) 246–252.
- K. Jantanaskulwong, N. Lekwasdi, P. Seuriyachan, S. Wongsuriyasak, C. Techapun, T. Ougizawa, Reactive blending of thermoplastic starch and polyethylene-graft-maleic anhydride with chitosan as compatibilizer, *Carbohydr. Polym.* 153 (2016) 89–95.

- [29] X.C. Shen, L.Y. Zhang, X.Q. Jiang, Y. Hu, J. Guo, Reversible surface switching of nanogel triggered by external stimuli, *Angew. Chem. Int. Ed.* 46 (2007) 7104–7107.
- [30] V. Singh, D.N. Tripathi, A. Tiwari, R. Sanghi, Microwave synthesized chitosan-graft-poly(methylmethacrylate): an efficient Zn²⁺ ion binder, *Carbohydr. Polym.* 65 (2006) 35–41.
- [31] H.L. Wang, H.Q. Tang, Z.T. Liu, X. Zhang, Z.P. Hao, Z.W. Liu, Removal of cobalt(II) ion from aqueous solution by chitosan–montmorillonite, *J. Environ. Sci.* 26 (2014) 1879–1884.
- [32] J. Dong, J. Hu, J.L. Wang, Radiation-induced grafting of sweet sorghum stalk for copper(II) removal from aqueous solution, *J. Hazard. Mater.* 262 (2013) 845–852.
- [33] J.P. Wang, Y.Z. Chen, S.J. Zhang, H.Q. Yu, A chitosan-based flocculant prepared with gamma-irradiation-induced grafting, *Bioresour. Technol.* 99 (2008) 3397–3402.
- [34] M.H. Casimiro, M.L. Botelho, J.P. Leal, M.H. Gil, Study on chemical, UV and gamma radiation-induced grafting of 2-hydroxyethyl methacrylate onto chitosan, *Radiat. Phys. Chem.* 72 (2005) 731–735.
- [35] H.I. Melendez-Ortiz, C. Alvarez-Lorenzo, A. Concheiro, V.M. imenez-Paez, E. Bucio, Modification of medical grade PVC with N-vinylimidazole to obtain bactericidal surface, *Radiat. Phys. Chem.* 119 (2015) 37–43.
- [36] D.K. Singh, A.R. Ray, Radiation-induced grafting of N,N'-Dimethylaminooethylmethacrylate onto chitosan films, *J. Appl. Polym. Sci.* 66 (1997) 869–877.
- [37] E. Repo, L. Malinen, R. Koivula, R. Harjula, M. Sillanpaa, Capture of Co(II) from its aqueous EDTA-chelate by DTPA-modified silica gel and chitosan, *J. Hazard. Mater.* 187 (2011) 122–132.
- [38] S.T. Zhuang, Y.N. Yin, J.L. Wang, Simultaneous detection and removal of cobalt ions from aqueous solution by modified chitosan beads, *Int. J. Environ. Sci. Technol.* (2017), <https://doi.org/10.1007/s13762-017-1388-x>.