

The Measurement of Physical Properties of Outdoor Exposed Members¹

Gwang-Chul Kim¹ · Jun-Ho Kim²

ABSTRACT

The number of newly constructed traditional Korean houses, i.e., *Hanoks*, and light-frame buildings is increasing. However, related research is limited owing to the lack of awareness regarding safety evaluations. Therefore, this study conducted an outdoor exposure test to accurately evaluate wooden constructions. Spruce, pine, and fir (SPF) material was monitored for a year, wherein the SPF material was artificially dried under 18% moisture content, and its physical properties and color differences were measured once a month. Large differences were observed in the material's weight and moisture content, which are indexes sensitive to daily range and rainfall; however, no significant difference was found for other basic properties in the pre and post test results. Herein, L^* , a^* , and b^* values represent color differences; these values exhibited a general decrease after the test. Such differences were attributed to the loss of lignin in the wood. The color difference value was high between the months of May and July, when the daily range and rainfall significantly fluctuated. Multiple regression analysis was performed on the a^* value (redness indicator), daily range, rainfall, and ultraviolet index. The results indicated that the daily range influenced redness the most. According to the estimated regression equation, the daily range and redness are positively correlated. Based on the results, the types and influence of independent variables on color difference are expected to change as the wood's duration of outdoor exposure and the amount of data obtained both increase.

Keywords: Hanok, light frame construction, outdoor exposure test, physical property, color difference

1. INTRODUCTION

In Korea, there are many wooden cultural heritages that use timbers. Among them, *Hanok*, means a construction made with traditional methods in Korea. More modern *Hanok* construction is expected as large-scale *Hanok* district promotion projects.

According to statistics of 2016 provided by the National *Hanok* Center, an average of 1,533 *Hanok* was built annually, with steady demand. The area with

the most *Hanoks* built from 2007 to 2010 was *Jeolla Namdo (Southern Jeolla)* with 1,549 new houses, followed by Seoul city with 486 houses. During the 3 years the survey had been conducted, about 3,000 new *Hanoks* were built, and roughly the same number of *Hanoks* had gone through maintenance. Modern *Hanok* and wooden cultural heritage, unlike general wooden construction, require consistent maintenance, management and repair, as they use structural size members (Kim *et al.*, 2015; Kim, 2012b). Statistics

¹ Date Received March 15, 2019, Date Accepted May 13, 2019

² Department of Housing Environmental Design, Chonbuk National University, Jeonju 54896, Republic of Korea

† Corresponding author: Gwang-Chul Kim (e-mail: gckim@jbnu.ac.kr, ORCID: 0000-0002-9774-0309)

Table 1. Numbers of wooden construction begin in Korea. (Statistics Korea)

year	2011	2012	2013	2014	2015	2016
Wooden construction	10,037	10,369	10,339	11,493	13,595	14,945

provided from the National *Hanok* Center indeed shows the necessity of systematic maintenance, management and repair. Moreover, as innovative cities being built across different provinces and districts actively attract residential population, trend shows that consumers clearly prefer wooden houses especially in single residential sites, as interest for eco-friendly living has increased. This led to an increased number of constructions of light frame buildings.

This study aims to build a database through an outdoor exposure test for a more accurate safety evaluation of wooden construction (Kim, 2017a; Kim, 2017b). A 3-year outdoor exposure test of small wooden test pieces is underway, in which basic physical properties are measured monthly by test piece samples (Kim, 2012a). This study was conducted to evaluate the test pieces that have completed on year test. Utilizing the database on remaining life acquired from this study will interact with local characteristics and bring beneficial insights including management of structural size members in the traditional point of view, and increase of demand of wooden houses by securing safety of wooden houses in the modern point of view (Kim and Park, 2015a).

2. MATERIALS and METHODS

The official tree species used in this study is an SPF (Spruce-*Picea jezoensis*, Pine-*Pinus densiflora*, and Fir-*Abies holophylla*) artificially dried under 18 percent moisture content, those is used frequently in Korean wooden constructions. The test pieces were prepared in the size of 38 × 38 × 300 mm with a miter saw. Although wooden cultural heritage and heavy timber construction employs members of structural size, the complete absence of related research data required this study to establish the concept first, thus the samples processed as small test pieces. The number of test pieces was a total of 120 units, which are ten units per month for a period of twelve month. Among these, the collecting 10 specimens tested per month. And the control group (20 specimens) was tested separately. The physical properties of the specimen were measured monthly before and after the test (Kim *et al.*, 2009; Kim and Matsumura, 2013).

$$W.L(\%) = \left(1 - \frac{A.W}{B.W}\right) \times 100 \dots\dots\dots (1)$$

The weight loss was obtained by equation 1. A.W (After weight) is the test group’s weight, and B.W

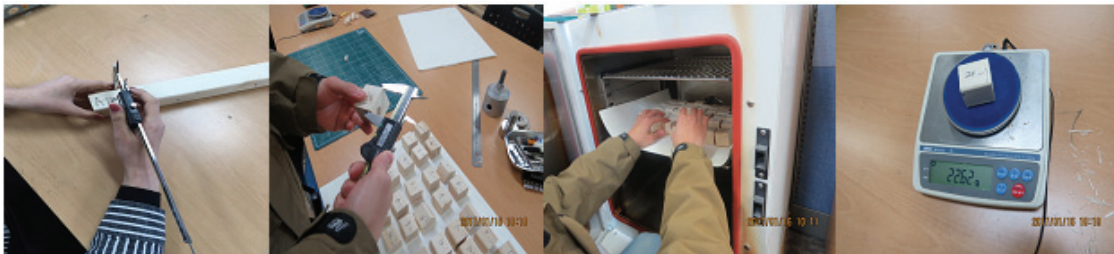


Fig. 1. The measurement of physical properties.

Table 2. Specimen information

Month	Count	Specimen number
1	10	1-1 ~ 1-10
2	10	2-1 ~ 2-10
3	10	3-1 ~ 3-10
4	10	4-1 ~ 4-10
5	10	5-1 ~ 5-10
6	10	6-1 ~ 6-10
7	10	7-1 ~ 7-10
8	10	8-1 ~ 8-10
9	10	9-1 ~ 9-10
10	10	10-1 ~ 10-10
11	10	11-1 ~ 11-10
12	10	12-1 ~ 12-10

(Before Weight) is a control group’s weight. The weight loss was analyzed for comparison of physical properties. The weight of cutting specimens for moisture content’s test was used.

The outdoor exposure test was conducted on the rooftop of the Chonbuk National University, College of Human Ecology located in *Deogjin-dong, Jeonju city, Northern Jeolla province*. 10 test pieces were collected per month to measure physical properties. Daily weather indexes including the highest and lowest temperatures, humidity and ultraviolet ray amount were collected through the K-weather web-site, the online National Weather Service. In order to enhance confidence, an on-site measurement took place once every day at 2:00 PM. The testing bench for the outdoor exposure experiment consulted the Weathering Testing Guidebook published by the US company Atlas Electric Devices Company, and was tilted at -5 degrees from level, in order to maximize reception of solar radiation through reflection and direct rays at the testing (rooftop) environment with waterproof flooring (ASTM G 90, 2005; Raberg *et al.*, 2005). In order to ensure all sides of the test pieces was evenly exposed to ultraviolet rays, all sides were turned over at a designated time once a week (ASTM G7/G7M-13, 2013).

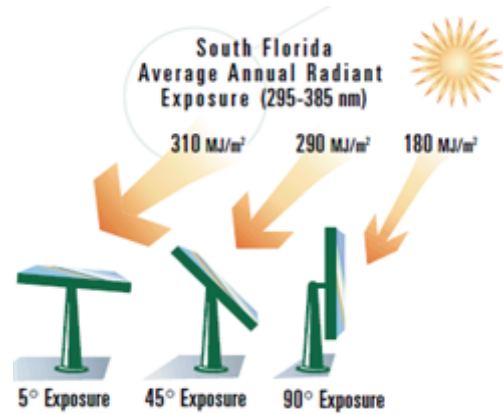


Fig. 2. South Florida Radiant (McGreer, 2003).



Fig. 3. Test desks for the outdoor exposure.



Fig. 4. Field record.



Fig. 5. Details for the color difference test.

Fig. 2 shows the angle at which solar radiation exposure could be maximized, according to the Weathering Testing Guidebook, and used the average radiant quantities of *South Florida* as the standard. Latitude

is necessary when examining the difference between temperature and sun radiant quantities. However, the radiant quantities were not adapted because of little difference between the latitudes of Florida (31°) and Jeonju (35°).

For the color difference test, 3 parts per test piece before and after outdoor exposure tests were measured using the color difference measurement device (model: CR-400). The color difference was observed for changes, categorized by L^* , a^* and b^* and the degree of color change was obtained by solving for color difference value ΔE (Kim, 2012a; Lee *et al.*, 2009).

3. RESULTS and DISCUSSION

3.1. Changes in physical properties

Table 3 shows the physical properties of test pieces exposed to outdoor in one year. The length, thickness, weight, moisture content and density were measured and the averages data of test pieces per test groups were recorded (Park and Kim, 2014). The length, width and thickness of all test pieces showed almost no difference before and after the test. Alike other physical property indexes, density also showed little difference among test groups with an average of 0.42g/cm³(±0.04).

Table 3. The changes of basic physical properties

	Length(mm)		Width(mm)		Thickness(mm)		Weight(g)		M.C.(%)	Density (g/cm ³)
	Before	After	Before	After	Before	After	Before	After		
C.G									10.86(±0.23)	0.43 (±0.07)
1M	300.45	300.40	37.53	37.62	37.59	37.78	205.33	209.20	14.29(±1.61)	0.45 (±0.05)
2M	300.45	300.45	37.40	36.91	37.56	37.29	203.31	202.36	13.26(±0.50)	0.42 (±0.03)
3M	300.45	300.20	37.51	37.80	37.35	37.82	195.21	193.37	12.78(±0.65)	0.41 (±0.05)
4M	300.30	300.10	37.74	37.58	37.67	37.35	199.92	193.31	10.37(±0.47)	0.42 (±0.03)
5M	300.55	299.85	37.64	37.14	37.45	36.85	184.28	173.43	8.59(±0.31)	0.39 (±0.04)
6M	300.60	299.85	37.58	38.00	37.64	38.09	180.69	188.54	20.72(±2.04)	0.39 (±0.03)
7M	300.55	300.30	37.56	38.02	37.59	38.08	194.77	211.76	19.69(±1.62)	0.42 (±0.05)
8M	300.70	300.00	37.55	37.44	37.52	37.54	189.50	186.71	12.20(±0.78)	0.40 (±0.05)
9M	300.50	299.85	37.45	37.33	37.39	37.36	206.45	206.27	18.18(±2.82)	0.45 ((±0.06)
10M	300.60	299.42	37.44	37.12	37.37	37.09	203.56	195.54	11.48(±1.57)	0.44 (±0.05)
11M	300.55	299.57	37.47	37.61	37.38	37.53	193.90	177.96	13.72(±1.62)	0.43 (±0.02)
12M	300.35	299.85	37.53	37.49	37.52	37.43	191.18	196.42	12.76(±0.90)	0.42 (±0.06)

M.C : Moisture Content, C.G : Control Group, M : Month

Table 4. The comparison of weight loss

	Weight(g)	W.L(%)
C.G	24.71	-
1M	27.83	-12.62
2M	26.47	-7.12
3M	25.57	-3.48
4M	25.98	-5.13
5M	22.54	8.78
6M	24.94	-0.93
7M	27.14	-9.83
8M	24.11	2.42
9M	27.02	-9.34
10M	25.70	-4.00
11M	24.08	2.54
12M	24.72	-0.04

W.L : Weight Loss

Weight and moisture content showed large difference among test groups, and this is thought to be caused by the sensitivity to changes in daily range and rainfall (Feist and Hon, 1984; Feist, 1989). The average post-test moisture content of all test pieces was 14.00%(±3.70), which increased approximately 30% from the moisture content of the control group of 10.86%(±0.23). The months that showed the most difference in moisture

content were May (8.59 %(±0.31)), and June (20.72%(±2.04)).

Table 4 shows the weight loss of test groups. May which shows the greatest weight loss, was measured the lowest moisture content. This is assumed to be the reason the dry atmosphere caused by the low rainfall, and the highest daily range led to the moisture of the wood to escape easily. Except for the beginning of an experiment, moisture content was the second highest in July when the weight loss was the lowest. (In June and July, there is not a large difference in moisture content by about 1%) In contrast to May, this is thought the wet atmosphere caused by the highest rainfall, and the lowest daily range made it difficult to move moisture inside the wood. As a result, it can be said that the weight loss and the moisture content are inversely proportional.

3.2. Comparison of color difference

3.2.1. Change of color difference

Fig. 6 shows the change in the appearance of test pieces according to outdoor exposure time, and Table 5 shows the average value of L^* , a^* , and b^* values

Table 5. Average of color values

	L^*	a^*	b^*
1M	77.94(±1.00)	4.03(±0.61)	29.1(±1.05)
2M	72.67(±5.47)	4.23(±5.47)	26.5(±2.83)
3M	69.87(±1.81)	6.03(±0.40)	26.6(±1.39)
4M	66.86(±1.70)	5.39(±0.66)	21.58(±2.04)
5M	65.26(±2.04)	5.09(±0.99)	19.71(±2.02)
6M	60.47(±3.90)	4.06(±1.62)	14.84(±3.07)
7M	57.84(±1.97)	2.72(±0.53)	11.58(±1.06)
8M	61.85(±2.66)	3.27(±0.53)	9.74(±1.17)
9M	59.14(±4.78)	3.30(±0.58)	10.75(±2.89)
10M	57.89(±2.38)	3.12(±0.59)	9.80(±1.20)
11M	58.31(±5.08)	2.67(±0.63)	8.14(±1.53)
12M	58.81(±3.81)	2.41(±0.53)	7.63(±1.32)

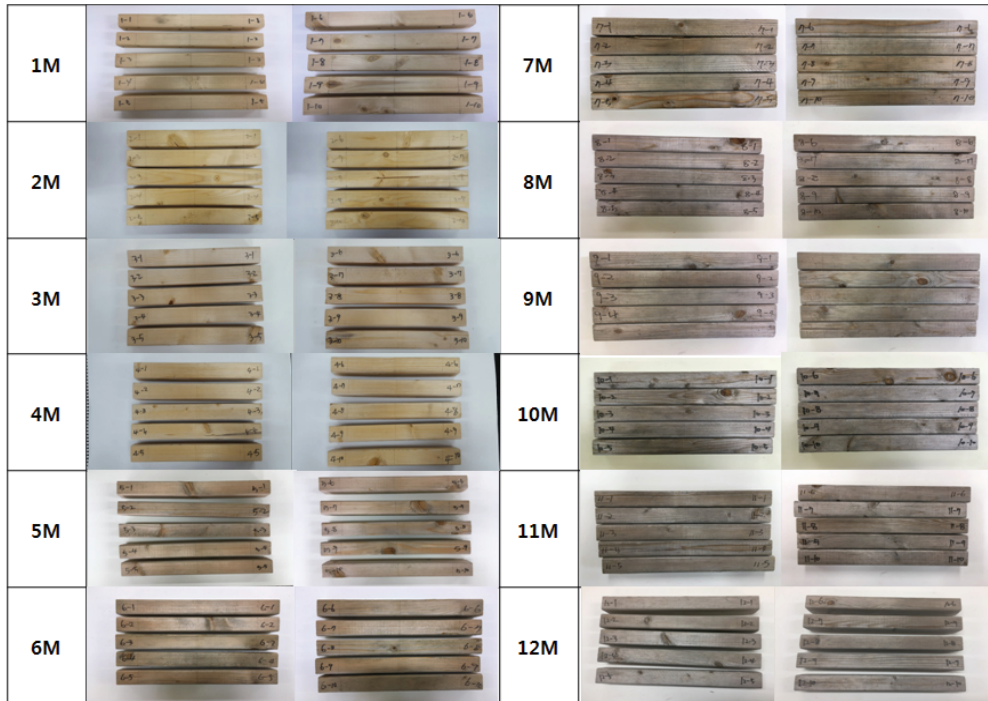


Fig. 6. Details for the color difference test.

according to outdoor exposure time. In terms of appearance change, the original brown color of the test piece lightened into a greyish white after a year-long exposure (Chang *et al.*, 2000). This change is likely due to the constant breakdown of lignin, a brown colored wood component, by ultraviolet ray exposure (Park *et al.*, 2016; Derbyshire and Miller, 1981; Evans, 1989). The L^* value that represents whiteness decreased by 25% post-test, and the a^* , and b^* values that represent redness and yellowness decreased by respectively 40% and 70%, causing the general color of the test piece to darken (Hidayat *et al.*, 2017). The degree of decrease in the L^* and b^* values actually diminished with time (Hon and Minemura, 1991). This can be attributed to the diminished amount of lignin being broken down (Evans *et al.*, 2000), compared to the initial stages, and is expected to decrease even more with more exposure time (Evans *et al.*, 2008).

3.2.2. ΔE computation

The color difference value was obtained by equation (2) using the difference of whiteness, redness, and yellowness measured pre and post outdoor exposure test.

$$\Delta E = \sqrt{(L^*1 - L^*2)^2 + (a^*1 - a^*2)^2 + (b^*1 - b^*2)^2} \quad \dots (2)$$

L^*1 , a^*1 and b^*1 are initial values before the test, and L^*2 , a^*2 and b^*2 are values that had changed after the tests. All color difference values showed a general increase with the progression of the test, as shown in Table 6. According to the N.B.S (National Bureau of Standard) that show the degree of perception according to color difference value, only the value measured during the first month into the test, 10.85, was included in the categorized item and showed considerable color change (Hon *et al.*, 1986). Measurements taken after

Table 6. Average of ΔE .

	ΔE
1M	10.85(± 1.70)
2M	14.89(± 5.07)
3M	17.54(± 1.82)
4M	17.27(± 1.94)
5M	18.77(± 2.75)
6M	25.3(± 4.27)
7M	27.23(± 2.35)
8M	25.21(± 2.18)
9M	26.7(± 5.51)
10M	24(± 9.48)
11M	22.81(± 10.29)
12M	29.43(± 9.60)

Table 7. Sensitive expression of color difference by N.B.S Unit 6.0

	Sensitive expression of color difference
0.0 ~ 0.5	Trace
0.5 ~ 1.5	Slight
1.5 ~ 3.5	Noticeable
3.0 ~ 6.0	Appreciable
6.0 ~ 12.0	Much
12.0 ~ d	Very much

the initial month were no less than 12; they were not categorized but one could see that very much color change took place. In terms of the degree of monthly

difference in color difference value, the two months between May and July were measured around 9, which mean the degree of change was larger than that of other months. We explored the cause through virtual data analysis.

Fig. 7 is a graph that shows the average daily range and rainfall during the year of the experiment (Son *et al.*, 2016; Ra, 2018). It can be seen that during the two months with the most color difference value difference, the line graph fluctuates drastically, with rapid increase and decreases. Months between May and July are summer in the Korean peninsula, and a period where many weather characteristics such as monsoons and tropical nights take place. The daily range graph shows that July is the month with the least daily range throughout the year. July is also the hottest month of the year, the average temperature being 27.1°C. In other words, it was hot all day and all night, steadily maintaining high temperature across hours. Exposure to higher temperatures can lead to degradation and change of hemicelluloses, and even cellulose, that affect (mainly deleteriously) the properties of the cell wall and the wood (Hills, 1984). And the lignin is mainly degraded due to its capacity to absorb light in short wavelength with a peak at 280 nm (Cogulet *et al.*, 2016). It is therefore inferred that the high temperature activated molecular activity of the wood and the long daytime

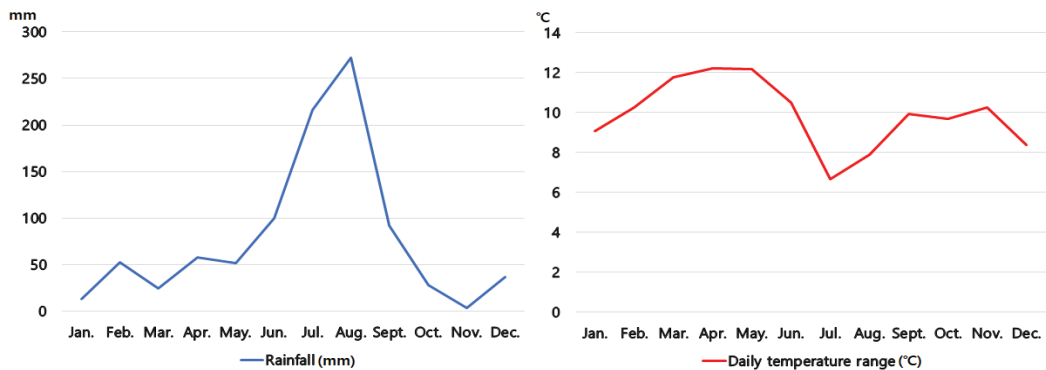


Fig. 7. The daily temperature range and rainfall in 2017.

Table 8. ANOVA table for the ΔE

Summary						
Groups	Count	Sum	Average	Variance		
1M	10	108.81	10.88	2.90		
2M	10	152.53	15.25	25.72		
3M	10	175.90	17.59	3.34		
4M	10	173.90	17.39	3.80		
5M	10	188.68	18.86	7.56		
6M	10	254.42	25.44	18.25		
7M	10	273.23	27.32	5.54		
8M	10	253.31	25.33	4.76		
9M	10	268.51	26.85	30.36		
10M	10	283.20	28.32	9.37		
11M	10	286.83	28.68	24.14		
12M	10	289.62	28.96	8.68		

ANOVA						
Source of variation	SS	df	MS	F	P-value	F critical
Between groups	4235.73	11	385.06	31.98	4.85E-29	1.87
Within groups	1300.22	108	12.03			
	5535.96	119				

hours resulted in longer exposure to ultra violet rays, accelerating the speed of lignin breakdown (Miniutti, 1967; Evans *et al.*, 1993; Evans *et al.*, 1996). Moreover, the loss of decomposed lignin on the surface is accelerated during the rainy season, contributing to even larger differences of color difference value.

3.3. Verifying significance

An F-test was conducted in order to verify the significance of the measured color difference value (Kim and Park, 2015a; Kim and Park, 2015b). As there were a total of 12 test pieces tested, an analysis of variance was conducted in order to compare the averages of more than two groups (Kim and Kim, 2016).

A significant verification took place, in order to verify change among 12 test groups tested in the same location but with different outdoor exposure time.

Results revealed a significant change, as the F value exceeded its critical, rejecting null hypothesis and the P value was considerably smaller than 0.05. This indicates that the experiment was appropriate, as changes existed among test groups of different exposure time. In other words, outdoor exposure time has a great impact on the color difference value of each test group.

3.4. Regression analysis

The factor that was thought to have deteriorated from weather and have a big influence on the color difference value of the outdoor exposure test was the lignin in the wood. As lignin is a brownish substance in wood, this study assumed a relationship with the a^* value that shows redness, and conducted a multiple regression analysis between a^* value, daily range, rainfall and ultraviolet index.

Table 9. Multiple regression analysis

REGRESSION ANALYSIS STATISTIC

MCC	0.83
R ²	0.69
M.R ²	0.57
SE	0.75
COUNT	12

ANOVA

	df	SS	MS	F	Significant F
Regression	3	10.26	33.42	6.03	0.01
Within groups	8	4.53	0.56		
	11	14.79			

	C	SE	t	P-value	Low rank 95%	High rank 95%	Low rank 95.0%	High rank 95.0%
Y (<i>a</i> *)	-2.75	2.03	-1.35	0.21	-7.43	1.93	-7.43	1.93
Daily temperature range (°C)	0.61	0.22	2.73	0.02	0.09	1.12	0.09	1.12
Rainfall (mm)	0.002	0.005	0.54	0.6	-0.009	0.015	-0.009	0.015
Ultraviolet Index	0.06	0.19	0.33	0.74	-0.37	0.50	-0.37	0.50

Table 9 shows the result of the multiple regression analysis. The M.R² was 0.57, producing a regression model with a fair amount of explanation power. The significant F was 0.01, smaller than 0.05, indicating that among various independent variables including daily range, rainfall and ultraviolet index, there exists a variable that affects the *a** value, the dependent variable. Table 9 shows that among the three independent variables, only the P value of daily range is smaller than 0.05, having a significant impact on the dependent variable, the *a** value. In other words, daily range has a statistically greater effect on *a** value that shows redness, compared to other weather factors. After the multiple regression analysis, a simple regression analysis was carried out between the significant independent variable of daily range and the dependent variable of *a** value.

Table 10 shows the result of the simple regression

analysis, in which the M.R² is 0.58, indicating a fair amount of explanation power like the multiple regression analysis. The P value is smaller than when other independent variables are present, which shows a greater influence on the dependent variable. Estimation of the regression equation through simple regression analysis is as the following.

$$y = 0.536048x - 1.4453 \dots\dots\dots (3)$$

In the estimated regression equation, the *x* value represents daily range, the independent variable. According to regression equation 3, the value, the dependent variable and *x*, the independent variable, are in a proportionate relationship, which means the *a** value also increases as the *x* value increases. In other words, the larger the daily range, the larger the redness. As the months between March and June shows

Table 10. Simple regression analysis

REGRESSION ANALYSIS STATISTIC

MCC	0.79
R ²	0.62
M.R ²	0.58
SE	0.74
COUNT	12

ANOVA

	df	SS	MS	F	Significant F
Regression	1	9.26	9.26	16.77	0.002
Within groups	10	5.52	0.55		
	11	14.79			

	C	SE	t	P-value	Low rank 95%	High rank 95%	Low rank 95.0%	High rank 95.0%
Y (<i>a</i> *)	-1.44	1.31	-1.10	0.29	-4.37	1.48	-4.37	1.48
Daily temperature range (°C)	0.53	0.13	4.09	0.002	0.24	0.82	0.24	0.82

the greatest daily range throughout the year, the *a** value in the same period is much as three times higher than in other months (Ra *et al.*, 2012). When compared with the estimated regression equation, it is thought that the breakdown of lignin accelerates during this period, causing the inner lignin to migrate to the surface and affect the *a** value of redness.

Whereas this study was only able to take a year-length outdoor exposure test for statistical analysis, changes are expected in types and influence of independent variables as longer outdoor exposure time amasses more data and the total lignin amount in the wood decrease.

4. CONCLUSION

This study derives its importance in securing a database on the little-studied remaining life of outdoor exposure wood, for the maintenance of full size wooden members in the traditional sense and for the increase

in wooden constructions demand by securing safety in the modern sense.

This study presents the following conclusions.

1. The length, width and thickness of all test pieces showed insignificant changes pre and post-test, but the weight and moisture content, affected by daily range and rainfall, showed large differences across different test groups. Also, it can be showed that the weight loss and the moisture content are inversely proportional.
2. *L**, *a**, and *b** values that represent color difference generally decreased post-test. The degree of decrease in *L** and *b** values tended to diminish with time, which is likely due to the decrease in total lignin amount compared to the initial stages of the test.
3. Color difference value was greatest between May and July. This period is when daily range and

rainfall fluctuates the most. July is also the month with monsoon and the highest monthly average temperature, which accelerated the cycle of lignin breakdown and loss in the wood, causing the greatest color difference value.

4. A significance verification showed that outdoor exposure time and color difference value showed a statistically significant difference.
5. A multiple regression analysis between a value, a redness indicator that gauges the degree of the brownish lignin, daily range, rainfall and ultraviolet index showed that daily range had the biggest influence on redness. The daily range and redness in the estimated regression equation were in a proportionate relationship, confirming that the increase in daily range also meant an increase in redness value.
6. Changes are expected in types and influence of independent variables on color difference, as longer outdoor exposure time amasses more data and the total lignin amount in the wood decrease.

ACKNOWLEDGMENT

This research was supported by Basic Science Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education (NRF-2016R1D1A3B03932199).

REFERENCES

- ASTM G7/G7M-13. 2013. Standard practice for atmospheric environmental exposure testing of nonmetallic materials. American Society for Testing and Materials (ASTM), West Conshohocken.
- ASTM G 90. 2005. Standard practice for performing accelerated outdoor weathering of nonmetallic materials using concentrated natural sunlight. American Society for Testing and Materials (ASTM), West Conshohocken.
- Chang, S.T., Wang, S.Y., Cheng, S.S. 2000. Environmental effects on the color of sugi (*Cryptomeria japonica* D. Don) heartwood. *Journal of Wood Science* 46(5): 390-394.
- Cogulet, A., Blanche, P., Landry, V. 2016. Wood degradation under UV irradiation: A lignin characterization. *Journal of Photochemistry & Photobiology* 158(2016): 184-191.
- Derbyshire, H., Miller, E.R. 1981. The photo degradation of wood during solar irradiation. Part 1. Effects on the structural integrity of thin wood strips. *Holz Roh-Werkst* 39(8): 341-350.
- Evans, P.D. 1989. Structural changes in *Pinus radiata* during weathering. *Journal of the Institute of Wood Science* 11(5): 172-181.
- Evans, P.D., Schmalzl, K.J., Michell, A.J. 1993. Rapid loss of lignin at wood surfaces during natural weathering. In: Kennedy JF, Phillips GO, Williams PA (eds) *Cellulose: pulp, fiber and environmental aspects*, chap 51. Ellis Horwood, Chichester, pp. 335-340.
- Evans, P.D., Thay, P.D., Schmalzl, K.J. 1996. Degradation of wood surfaces during natural weathering- Effects on lignin and cellulose and on the adhesion of acrylic latex primers. *Journal of Wood Science* 30(6): 411-422.
- Evans, P.D., Wallis, A.F.A., Owen, N.L. 2000. Weathering of chemically modified wood surfaces. *Journal of Wood Science* 34(2): 151-165.
- Evans, P.D., Urban, K., Chowdhury, M.J.A. 2008. Surface checking of wood is increased by photo degradation caused by ultraviolet and visible light. *Journal of Wood Science* 42(3): 251-265.
- Feist, W.C., Hon, D.N.S. 1984. Chemistry of weathering and protection. In: Rowell RM (ed) *Chemistry of*

- solid wood, chap 11. ACS, Washington DC, pp. 401-454.
- Feist, W.C. 1989. Outdoor wood weathering and protection. Forest Products Laboratory, Madison WI 53705-2398.
- Hidayat, W., Qi, Y., Jang, J.H., Park, B.H., Banuwa, I.S., Febrianto, F., Kim, N.H. 2017. Color Change and Consumer Preferences towards Color of Heat-Treated Korean White Pine and Royal Paulownia Woods. *Journal of the Korean Wood Science and Technology* 45(2): 213-222.
- Hillis, W.E. 1984. High temperature and chemical effects on wood stability. *Wood Science and Technology* 18: 281-293.
- Hon, D.N.S., Clemson, S.C., Feist, W.C. 1986. Weathering characteristics of hardwood surfaces. *Journal of Wood Science* 20(2): 169-183.
- Hon, D.N.S., Minemura, N. 1991. Color and discoloration. In: Hon DNS, Shiraish N (eds) *Wood and cellulosic chemistry*. Marcel Dekker, New York, pp. 395-454.
- Kim, G.C., Kang, C.W., Matsumura, J. 2009. Performance assessment of existing Korean school building (I) - Mechanical and physical properties of the rafter members. *Journal of the Faculty of Agriculture, Kyushu University* 54(2): 439-444.
- Kim, G.C. 2012a. Study on the Color Changing of Pine by Accelerated Weathering Test. *Korea Furniture Society* 23(2): 152-162.
- Kim, G.C. 2012b. Study on the Change of Physical and Anatomical Properties in the Pine Wood by Accelerated Weathering Test. *Korea Furniture Society* 23(3): 324-331.
- Kim, G.C., Matsumura, J. 2013. Study on the change of bending performance for wood member by accelerated weathering test. *Journal of the Faculty of Agriculture, Kyushu University* 58(2): 351-357.
- Kim, G.C., Park, C.Y. 2015a. Mechanical Properties of Zelkova Serrata Makino in Accelerated Weathering Test. *Korea Furniture Society* 26(4): 392-397.
- Kim, G.C., Park, C.Y. 2015b. Analysis of Surface Color Characteristics of Wood in Accelerated Weathering Test. *Korea Furniture Society* 26(3): 262-266.
- Kim, G.C., Kim, J.H. 2016. Performance Comparison of Korean Tongue and Groove Joint between Hand-made and Pre-cut. *Journal of the Korean Wood Science and Technology* 44(5): 664-676.
- Kim, M.J., Shin, H.K., Choi, Y.S., Kim, G.C., Kim, G.H. 2015. Predicting Influence of Changes in Indoor Air Temperature and Humidity of Wooden Cultural Heritages by Door Opening on Their Conservation Environment. *Journal of the Korean Wood Science and Technology* 43(6): 798-803.
- Kim, Y.S. 2017a. Current Researches on The Weathering of Wood. *Journal of the Korean Wood Science and Technology* 45(5): 483-494.
- Kim, Y.S. 2017b. Current Researches on the Protection of Exterior Wood from Weathering. *Journal of the Korean Wood Science and Technology* 46(5): 449-470.
- Lee, G.H., Cha, M.Y., Chung, W.Y., Bae, H.J., Kim, Y.S. 2009. Chemical and morphological change and discoloration of cedar wood stored indoor. *Journal of the Korean Wood Science and Technology* 37(6): 566-577.
- McGreer, M. 2003. *Weathering Testing Guidebook*. Chicago, USA: Atlas Electric Devices Company.
- Miniutti, V.P. 1967. Microscopic observations of ultraviolet irradiated and weathered softwood surfaces and clear coatings. *USDA Forest Service Research Paper FPL, vol 74*, pp. 1-32.
- Park, C.Y., Kim, G.C. 2014. Evaluation of Modulus of Elasticity of Wood Exposed to Accelerated Weathering Test by Measuring Ultrasonic Transmission Time. *Journal of the Korean Wood Science and Technology* 42(3): 275-281.
- Park, S.H., Jang, J.H., Hwang, W.J., Kim, N.H. 2016.

- Color change of major wood species planted in Indonesia by ultraviolet radiation. *Journal of the Korean Wood Science and Technology* 44(1): 9-18.
- Raberg, U., Edlund, M.L., Terziev, N., Land, C.J. 2005. Testing and evaluation of natural durability of wood in above ground conditions in Europe-an overview. *Journal of Wood Science* 51(5): 429-440.
- Ra, J.B., Kim, K.B., Leem, K.H. 2012. Effect of Heat Treatment Conditions on Color Change and Termite Resistance of Heat-Treated Wood. *Journal of the Korean Wood Science and Technology* 40(6): 370-377.
- Ra, J.B. 2018. Determination of Driving Rain Index by Using Hourly Weather Data for Developing a Good Design of Wooden Buildings. *Journal of the Korean Wood Science and Technology* 46(6): 627-636.
- Son, D.W., Hong, J.O., Park, J.H., Lee, H.S., Chung, Y.J., Han, G.S. 2016. Effect of Short-Term Weathering on Flame Retardant Performance of Korean Red Pine Wood Coated with Dancheong. *Journal of the Korean Wood Science and Technology* 44(5): 785-808.