

Effect of [EMIM]Ac Recycling on *Salix gracilistyla* Miq. Pretreatment for Enzymatic Saccharification¹

Song-Yi HAN² · Chan-Woo PARK^{2,3} · Gu-Joong KWON^{2,4} · Jong-Ho KIM^{2,3} ·
Nam-Hun KIM^{2,3} · Seung-Hwan LEE^{2,3,5,†}

ABSTRACT

Recycling of ionic liquid (1-ethyl-3-methylimidazolium acetate, [EMIM]Ac) after the pretreatment of *Salix gracilistyla* Miq. was conducted and the effect of the recycling number on the enzymatic saccharification yield was investigated. Enzymatic saccharification was performed using an enzyme cocktail (Acremonium cellulase and Optimash BG) at 50 °C for 72 h. All recycled [EMIM]Ac samples showed a lower amount of water soluble fraction than pure [EMIM]Ac. On increasing the recycling number from 1 to 4, the amount of water soluble fraction decreased from 18% to 15%. The X-ray diffraction pattern of the products pretreated with recycled [EMIM]Ac showed cellulose I crystalline polymorph. The crystallinity of the product pretreated with recycled [EMIM]Ac was 47-49%, which was lower than 33% of that with pure [EMIM]Ac. The yields of glucose and xylose decreased in the pretreatment with recycled [EMIM]Ac compared to that with pure [EMIM]Ac.

Keywords: ionic liquid, recycling, pretreatment, enzymatic saccharification, *Salix gracilistyla* Miq.

1. INTRODUCTION

Pretreatment is an essential process to improve the enzymatic saccharification efficiency of lignocellulosic biomass because of its recalcitrance characteristics (Wu *et al.*, 2013). Moreover, pretreatment is the most expensive process, which reportedly costs approximately 20% of the total cost for ethanol production from lignocellulosic biomass (Yang and Wyman 2008). In this context, many studies have attempted to develop a novel pretreatment process to improve the economic feasi-

bility of the biorefinery process from lignocellulosic biomass (Jung *et al.*, 2017; Yanti *et al.*, 2019). Among them, the pretreatment using ionic liquids (ILs) has attracted attention as an environment-friendly process because of their various advantages such as low volatility, high thermal and chemical stability, excellent solubility, non-flammability, and recovery. IL pretreatments are also known effective as the biological and chemical conversion of lignocellulosic biomass into a wide range of biomaterials and bioenergy (Park *et al.*, 2015; Dutta *et al.*, 2016; Han *et al.*, 2020c). The IL

¹ Date Received February 17, 2020, Date Accepted May 1, 2020

² Institute of Forest Science, Kangwon National University, Chuncheon 24341, Republic of Korea

³ Department of Forest Biomaterials and Engineering, College of Forest and Environmental Sciences, Kangwon National University, Chuncheon 24341, Republic of Korea

⁴ Kangwon Institute of Inclusive Technology, Kangwon National University, Chuncheon 24341, Republic of Korea

⁵ Institute of Fermentation and Brewing, Kangwon National University, Chuncheon 24341, Republic of Korea

† Corresponding author: Seung-Hwan LEE (e-mail: lshyhk@kangwon.ac.kr, ORCID: 0000-0002-9988-2749)

pretreatment is known to be more environment-friendly and facile but less economical than other organic-solvent-based processes (Kim *et al.*, 2012; George *et al.*, 2015). Therefore, it is recommended to recover and reuse the ILs for industrial applications (Elgharbawy *et al.*, 2016). Sangian *et al.* (2015) investigated the effect of recycling an IL (methylmethylimidazolium dimethyl phosphate, [MMIM]DMP) after pretreatment of coconut coir for enzymatic saccharification. The used IL was recycled twice to re-employ for pretreatment. The yields of sugar after the pretreatment using fresh IL and IL recycled once and twice were 0.19, 0.15, and 0.15 g per gram of polysaccharide (cellulose+hemicellulose), respectively. Ding *et al.* (2016) pretreated corn stover using dilute NaOH (1 wt% solution) followed by pretreatment with fresh and recycled IL (1-butyl-3-methylimidazolium chloride, [BMIM]Cl). The glucose concentration from the product pretreated with the IL recycled 10 times was 18.7 g/L after 12 h of enzymatic hydrolysis, which was 5.5 g/L lower than that with fresh IL. Cheenkachorn *et al.* (2016) reported that the pretreatment of rice straw with [EMIM]Ac could afford the glucose yield of 90% compared to untreated products. The recycling of [EMIM]Ac using methanol as an anti-solvent reportedly retains more than 90% efficiency without any modification in the pretreatment process despite 5 recycles. Xu *et al.* (2017) investigated the effect of recycling 1-allyl-3-methylimidazolium chloride ([AMIM]Cl) and 1-butyl-3-methylimidazolium acetate ([BMIM]Ac) on the pretreatment of eucalyptus for enzymatic hydrolysis. The glucose yield by ILs recycled 4 times was 54.3% for [AMIM]Cl and 72.8% for [BMIM]Ac, which was 5.0- and 6.7-folds higher than that of untreated eucalyptus. The pretreatment effect of the recycled ILs deteriorated after 4 times, showing relatively lower sugar conversion and lignin removal.

In this study, the effect of the number of recycling of [EMIM]Ac on the enzymatic saccharification was investigated to improve the economic feasibility of the

pretreatment. The higher solid loading of 15 wt% was adapted, which is higher than about 5% in the general studies described above. *Salix gracilistyla* Miq. is a native species in Korea and known as one of the rapidly growing wood species for bioenergy production (Lee *et al.*, 2018).

2. MATERIALS and METHODS

2.1. Materials

Salix gracilistyla Miq. wood powder (40 mesh) was extracted at 85 °C for 5 h with an ethanol/benzene mixed solution (1:2, v/v) and used as the lignocellulose material. The chemical composition of *Salix gracilistyla* Miq. was 47.2, 26.4, 25.1, and 5.6 wt% α -cellulose, hemicellulose, klason lignin, and extractives, respectively and these results have been reported previously (Han *et al.*, 2017a). [EMIM]Ac was purchased from IoLiTec (Heilbronn, Germany), and other chemicals used in this study were obtained from Daejung Chemicals & Metals (Gyeonggi, Korea). Acremonium cellulase and Optimash BG were purchased from Meiji Seika Co. (Tokyo, Japan) and Genencor International, Inc. (Palo Alto, CA, USA).

2.2. Pretreatment and IL re-usage

The *Salix gracilistyla* Miq. wood powder was pretreated using [EMIM]Ac with 15 wt% solid loading at 120 °C for 2 h (Han *et al.*, 2017b; Han *et al.*, 2020a). The pretreated product was regenerated using 500 mL distilled water at room temperature for 1 h. The regenerated *Salix gracilistyla* Miq. was collected by filtration under vacuum and washed with distilled water (500 mL) to remove the residual IL and water soluble fraction. The fractionated residue was freeze-dried using FDB-5503 (Operon Co., Ltd., Korea) and subjected to crystallinity analysis and enzymatic saccharification. The filtrate was collected from recycling the IL with an evaporator (Rotavapor, R-3000; Buchi Analytical Inc., USA)

at 45 °C under a pressure of 700 mmHg and stored at 40 °C for 3 days, which was sufficient to remove almost all the water from the IL. [EMIM]Ac was recycled for 1-4 times. Then, the recycled IL was used as the raw material, and the treatment procedure was the same as mentioned above.

2.3. Acid hydrolysis

The compositional measurement of the monosaccharides before and after pretreatment was conducted using the Laboratory Analytical Procedure (LAP) by NREL (Sluiter *et al.* 2008). The raw material and pretreated samples (100 mg) were added to 1.5 mL Eppendorf tubes with 72% sulfuric acid solution (1 mL). For hydrolysis, the tubes were kept in a shaking incubator (Shaking incubator, VS-101Si, vision scientific Co., Korea) at 30 °C for 1 h. The hydrolysates were diluted to 4% using deionized water (19.8 mL) and further hydrolyzed at 120 °C for 1 h. Next, it was separated from the acid slurry for the measurement of acid-insoluble lignin to determine the acid-soluble monosaccharide. Calcium carbonate was used to neutralize the sample to a pH of 5-6. The supernatant was passed through a 0.2 µm filter into an autosampler vial before monosaccharide analysis by HPLC. The yields of glucose and xylose were measured by HPLC (YL9100, Younglin Co., Anyang, Korea) with a carbohydrate analysis column (Aminex HPX-87P, 300×7.8 mm, hydrogen form, 8% cross-linkage, Bio-Rad Laboratories, Inc., CA, USA) at a flow rate 0.6 mL/min at 85 °C. For acid-insoluble lignin measurement, the acid slurry was filtrated through the Whatman filter paper by adding distilled water until neutralized, dried at 100 °C, and weighed.

2.4. Enzymatic saccharification

Enzymatic hydrolysis was conducted using an enzyme cocktail of Acremonium cellulase (15 FPU per gram of substrate) and Optimash BG (0.2%, v/v) as

a supplement to β-xylosidase (Han *et al.*, 2020b). The pretreated substrates (250 mg) were added to the enzyme cocktail at a solid loading of 2.5% in a sodium acetate buffer solution (50 mM, pH 5). Hydrolysis was performed in a shaking incubator at 50 °C for 72 h (150 rpm). Hydrolysates of 1 mL were sampled at 3, 6, 12, 24, 48, and 72 h intervals. The enzyme inactivation was conducted by heating at 95 °C for 15 min in a heating block (HB-48-Set, Wisd; Daihan Scientific Co., Ltd., Wonju, Korea) and stored at 4 °C. The enzymatic hydrolysate was centrifuged at 7000 rpm for 15 min and filtered through a syringe filter (0.2 µm).

2.5. Analysis

X-ray diffraction analysis was conducted for the crystallization evaluation of the pretreated sample. For this analysis, the specimen was prepared by substituting the suspension with t-butyl alcohol and freeze-drying. X-ray diffraction analysis was performed at a rate of 2 ° per minute using an X-ray diffractometer (Rigaku RINT-TTR III, Tokyo, Japan) at a range of $2\theta = 2-60^\circ$. The crystallinity index (CrI) was determined by the Segal method (Segal *et al.*, 1959).

The monosaccharide analysis was conducted with an HPLC system (YL9100; Young Lin Instrument Co., Ltd., Anyang, Korea) equipped with an Aminex HPX-87P column (Bio-Rad Laboratories, Inc., Hercules, CA, USA). The mobile phase was deionized water, and the flow rate was 0.6 mL/min at 85 °C. The glucose and xylose yields in the enzymatic hydrolysate were calculated using equation 1 and 2:

$$\begin{aligned} & \text{Glucose or xylose yield (\%)} \\ & = \frac{\text{Mass of glucose or xylose in enzymatic hydrolysates (g)} \times \text{conversion factors}}{\text{Mass of glucan or xylan in the pretreated wood (g)}} \times 100 \end{aligned} \quad (1)$$

$$\begin{aligned} & \text{Glucose or xylose yield (\%)} \\ & = \frac{\text{Mass of glucose or xylose in enzymatic hydrolysates (g)}}{\text{Mass of raw material (g)}} \times 100 \end{aligned} \quad (2)$$

where 0.9 and 0.88 are conversion factors for glucose and xylose to glucon and xylan, respectively.

3. RESULTS and DISCUSSION

Fig. 1 shows the effect of the recycling number of [EMIM]Ac on the amount of water soluble fraction. Compared to the 21% fraction obtained by pure [EMIM]Ac, all samples pretreated with recycled [EMIM]Ac showed lower values. On increasing the recycling number from 1 to 4, the amount of water soluble fraction decreased from 18% to 15%. The water soluble fraction may contain low molecules of hemicellulose and lignin degraded by [EMIM]Ac, which can act as a physical barrier to block enzyme accessibility to cellulose (Shi *et al.*, 2014; Kumagai *et al.*, 2016). After extracting the water soluble fraction, the residual substrate will be cellulose-rich and very porous, which will increase the surface area of cellulose. Lee *et al.* (2010) reported that the nanospace could be generated between cellulose microfibrils by extracting hemicellulose by the hot-compressed water treatment. Moreover, delignification can increase the surface area of polysaccharides, i.e., cellulose and hemicellulose.

The main aim of pretreatment is to disrupt the cell wall structure of the lignocellulosic biomass by partial or complete removal of hemicellulose or lignin, resulting in the increase in the surface area and porosity of the substrates, and to decrease cellulose crystallinity (Kucharska *et al.*, 2018). Fig. 2 shows the XRD patterns of the products pretreated with pure and recycled [EMIM]Ac for different recycling numbers, and their CrI are summarized in Table 1. The raw material

and the product pretreated with pure and recycled [EMIM]Ac displayed a strong peak at around 22.8° (2 θ), corresponding to the (002) crystal plane of cellulose, as well as composite peaks at 15° and 15.5°, corresponding to the (101) and (10) crystal planes. This pattern represents the cellulose I polymorph. In the sample pretreated with pure [EMIM]Ac, however, the

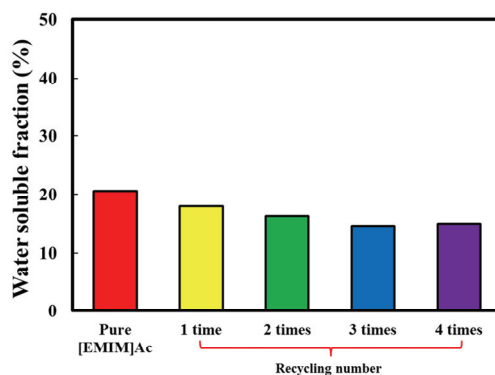


Fig. 1. Effect of the recycling number of [EMIM]Ac on water soluble fraction from *Salix gracilistyla* Miq.

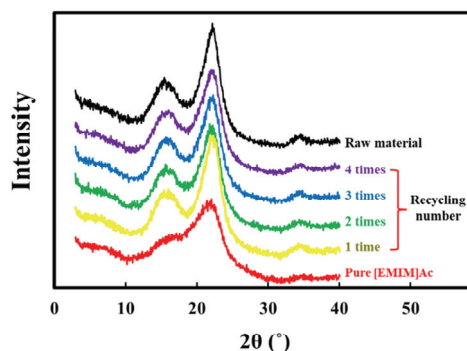


Fig. 2. XRD patterns of the products pretreated with pure and recycled [EMIM]Ac for different recycling numbers.

Table 1. Recycling numbers of [EMIM]Ac and CrI of the pretreated products

	Raw material	Pure [EMIM]Ac	Number of the recycling			
			1	2	3	4
CrI (%)	55	33	49	47	47	47

intensity of the (002) plane dramatically decreased and no distinct peak for the (101) and (10) planes were observed. This indicates that the crystallinity of cellulose is significantly disrupted by partial dissolution and distension of the cellulose crystal (Zhang *et al.*, 2014). The increase in the amorphous portion of cellulose will improve its enzyme accessibility (Ling *et al.*, 2017). This disruption ability was diminished by [EMIM]Ac recycling, regardless of the recycling numbers.

The CrI of the raw material was 55%, which decreased to 33% by pretreatment with pure [EMIM]Ac. However, the CrI of the product pretreated with recycled [EMIM]Ac ranged from 47 to 49%, which was higher than that with pure [EMIM]Ac. This indicates that the pretreatment effect of lowering the CrI is deteriorated by recycling. Hamidah *et al.* (2018) reported the pretreatment of softwood (*Cryptomeria japonica*) with a recycled [EMIM]Ac without the dissolution of cellulose and lignin. It was reported that CrI (34.0%) of the product pretreated with [EMIM]Ac recycled for 3 times were similar with 30.7% of the products with pure [EMIM]Ac, and glucose yields were also not significantly different between the products pretreated with recycled and pure [EMIM]Ac. Although lignin dissolved in [EMIM]Ac continued to accumulate after [EMIM]Ac recycling, the pretreatment was found

to be effective for three consecutive cycles without the need for the removal of dissolved materials.

Fig. 3 shows the glucose and xylose yields of the product pretreated with pure and recycled [EMIM]Ac depending on enzymatic saccharification time. The glucose and xylose yields were evaluated from the original masses of glucan and xylan, which were obtained by acid hydrolysis. With increasing enzymatic saccharification time, the glucose and xylose yield increased in all products. The product pretreated with pure [EMIM]Ac showed the highest glucose and xylose yields, which were more than 80% for 72 h saccharification. On the other hand, the raw material exhibited the lowest yields, i.e., approximately 20% and 10% for glucose and xylose, respectively. With recycled [EMIM]Ac, both yields decreased compared to pure [EMIM]Ac. There was no significant difference in both yields among the products pretreated with recycled [EMIM]Ac yields of 66-69% for glucose and 55-63% for xylose for 72 h saccharification.

The glucose and xylose yields of the product pretreated with pure and recycled [EMIM]Ac after enzymatic saccharification are calculated using equation 2 and summarized in Table 2. These values are calculated on the basis of the original mass and the glucan (xylan) after acid hydrolysis (equation 1) in paren

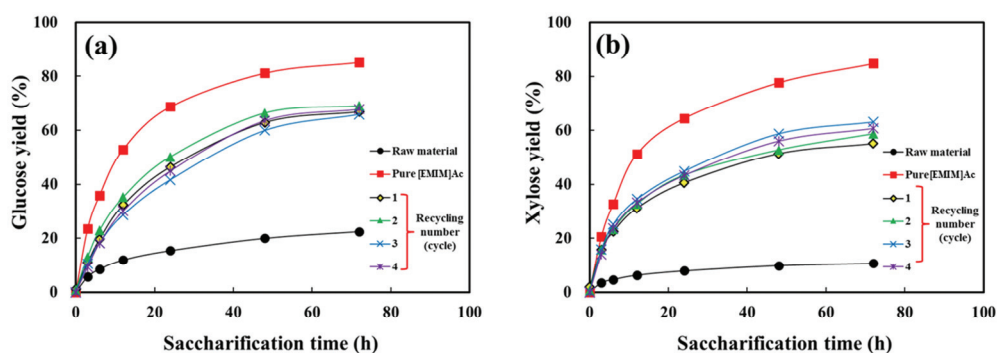


Fig. 3. Yields of glucose (a) and xylose (b) for raw material and product pretreated with pure and recycled [EMIM]Ac on the basis of glucan and xylan obtained by acid hydrolysis.

Table 2. Yields of glucose and xylose for pretreated products on the basis of the original mass after enzymatic saccharification for 72 h

	Yield of enzymatic saccharification	
	Glucose (%)	Xylose (%)
Raw material	14 (22)	3 (11)
Pure IL	42 (85)	13 (85)
Recycling number	1	34 (67)
	2	32 (69)
	3	34 (66)
	4	34 (68)

Notes: The values in parenthesis are calculated on the basis of the mass of glucan and xylan after enzymatic saccharification for 72 h.

thesis as well. The glucose and xylose yields of the product pretreated with pure [EMIM]Ac were 42% and 13%, respectively. These values decreased with the pretreatment with recycled [EMIM]Ac. Regardless of the recycling number, the glucose yield on enzymatic saccharification was 34-36%, which was lower than that with pure [EMIM]Ac. However, the xylose yield (9-12%) was not significantly different from that with pure [EMIM]Ac (13%). This result is attributed to the extraction amount of the water soluble fraction because the value was calculated by compensating the amount of water soluble fraction. This also indirectly indicates that the water soluble fraction contains hemicellulose components degraded by [EMIM]Ac.

In general, there is a correlation between the saccharification yield and the CrI of the cellulose (Cui *et al.*, 2014). It is also known that the initial rate of the cellulase-catalyzed hydrolysis of cellulose is linearly proportional to the crystallinity index of cellulose. In this study, the CrI of the product pretreated with pure [EMIM]Ac was 33%, showing the highest saccharification yield. On the other hand, the CrI values (47-49%) increased for the product pretreated with recycled [EMIM]Ac, showing the lower saccharifi-

cation yield than that with pure [EMIM]Ac. Hall *et al.* (2010) reported that the CrI of cellulose is a key predictor of the enzymatic saccharification efficiency and rate. They stated that the initial enzymatic rate continued to increase with a decreasing crystallinity index, even though the bound enzyme concentration stayed constant. They insisted that their finding supports the determinant role of crystallinity rather than adsorption on the enzymatic rate. Hou *et al.* (2012) reported that [Ch]Lys showed excellent reusability over five successive batches in the pretreatment of rice straw. Lignin continued to accumulate in [Ch]Lys during recycling, and delignification efficiency decreased slightly from 59% to 53% over the five recycling batches for rice straw. Glucose yields (84-87%) and initial glucose release rates (2.4-2.5 mg/mL/h) remained almost constant after the IL was reused for five batches.

4. CONCLUSION

Pretreatment with recycled [EMIM]Ac of *Salix gracilistyla* Miq. was successfully conducted to achieve more than 80% yield of glucose and xylose by enzymatic saccharification. Compared to the product pretreated with pure [EMIM]Ac, the product pretreated with recycled [EMIM]Ac showed a lower amount of water soluble fraction, cellulose I polymorph, and higher CrI, and lower yields of glucose and xylose. However, there was no significant difference in these properties among the product pretreated with recycled [EMIM]Ac. It is concluded that the pretreatment effect of recycled [EMIM]Ac was declined, compared to pure [EMIM]Ac, but more than 60% enzymatic saccharification yield was able to be achieved by the pretreatment using [EMIM]Ac recycled for 4 times.

ACKNOWLEDGMENT

This study was funded by the Basic Science Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education (Grant No. 2018R1A6A1A03025582).

REFERENCES

- Cheenkachorn, K., Douzou, T., Roddecha, S., Tantayotai, P., Tantayotai, P., Sriariyanun, M. 2016. Enzymatic saccharification of rice straw under influence of recycled ionic liquid pretreatments. *Energy Procedia* 100: 160-165.
- Cui, T., Li, J., Yan, Z., Yu, M., Li, S. 2014. The correlation between the enzymatic saccharification and the multidimensional structure of cellulose changed by different pretreatments. *Biotechnology for Biofuels* 7: 134.
- Ding, J.C., Xu, G.C., Han, R.Z., Ni, Y. 2016. Biobutanol production from corn stover hydrolysate pretreated with recycled ionic liquid by *Clostridium saccharobutylicum* DSM 13864. *Bioresource Technology* 199: 228-234.
- Dutta, T., Shi, J., Sun, J., Zhang, X., Cheng, G., Simmons, B.A., Singh, S. 2016. Ionic liquid pretreatment of lignocellulosic biomass for biofuels and chemicals. In: *Ionic liquids in the biorefinery concept: challenges and perspectives*. RSC Green Chemistry Ser. 36, Ed. by Bogel-Lukasik, R., Royal Society of Chemistry, Cambridge, UK.
- Elgharbawy, A.A., Alam, M.Z., Moniruzzaman, M., Goto, M. 2016. Ionic liquid pretreatment as emerging approaches for enhanced enzymatic hydrolysis of lignocellulosic biomass. *Biochemical Engineering Journal* 109: 252-267.
- George, A., Brandt, A., Tran, K., Zahari, S.M.S.N.S., Klein-Marcuschamer, D., Sun, N., Sathitsuksanoh, N., Shi, J., Stavila, V., Parthasarathi, R., Singh, S., Holmes, B.M., Welton, T., Simmons, B.A., Hallett, J.P. 2015. Design of low-cost ionic liquids for lignocellulosic biomass pretreatment. *Green Chemistry* 17(3): 1728-1734.
- Hall, M., Bansal, P., Lee, J.H., Realff, M.J., Bommarius A.S. 2010. Cellulose crystallinity-a key predictor of the enzymatic hydrolysis rate. *The FEBS Journal* 277(6): 1571-1582.
- Hamidah, U., Arakawa, T., H'ng, Y.Y., Nakagawazumi, A., Kishino, M. 2018. Recycled ionic liquid 1-ethyl-3-methylimidazolium acetate pretreatment for enhancing enzymatic saccharification of softwood without cellulose regeneration. *Journal of Wood Science* 64(2): 149-156.
- Han, S.Y., Park, C.W., Kim, N.H., Lee, S.H. 2017a. Co-solvent system of [EMIM]Ac and DMF to improve the enzymatic saccharification of pussy willow (*Salix gracilistyla* Miq.). *Holzforchung* 71(1): 43-50.
- Han, S.Y., Park, C.W., Lee, S.H. 2017b. Preparation of lignocellulose nanofiber by mechanical defibrillation after pretreatment using cosolvent of ionic liquid and DMF. *Journal of the Korean Wood Science and Technology* 45(3):268-277.
- Han, S.Y., Park, C.W., Febrianto, F., Kim, N.H., Lee, S.H. 2020a. Pretreatment with [EMIM]Ac/DMAc Co-solvent to Improve Enzymatic Saccharification of Pussy Willow (*Salix gracilistyla* Miq.). *Bio-Resources* 15(1): 187-198.
- Han, S.Y., Park, C.W., Endo, T., Febrianto, F., Kim, N.H., Lee, S.H. 2020b. Extrusion process to enhance the pretreatment effect of ionic liquid for improving enzymatic hydrolysis of lignocellulosic biomass. *Wood Science and Technology*.
- Han, S.Y., Park, C.W., Park, J.B., Ha, S.J., Kim, N.H., Lee, S.H. 2020c. Ethanol fermentation of the enzymatic hydrolysates from the products pretreated using [EMIM]Ac and its co-solvents with DMF. *Journal of Forest and Environmental Science* 36(1):

- 62-66.
- Hou, X.D., Smith, T.J., Li, N., Zong, M.H. 2012. Novel renewable ionic liquids as highly effective solvents for pretreatment of rice straw biomass by selective removal of lignin. *Biotechnology and Bioengineering* 109(10): 2484-2493.
- Jung, J.Y., Ha, S.Y., Park, J.H., Yang, J.-K. 2017. Optimization of alkali pretreatment from steam exploded barley husk to enhance glucose fraction using response surface methodology. *Journal of the Korean Wood Science and Technology* 45(2): 182-194.
- Kim, J.-Y., Kim, T.-S., Hwang, H., Oh, S., Choi, J.W. 2012. Chemical · Structural characterization of lignin extracted from Pitch Pine with Ionic Liquid (1-ethyl-3-methylimidazolium acetate). *Journal of the Korean Wood Science and Technology* 40(3): 194-203
- Kucharska, K., Rybarczyk, P., Holowacz, I., Glinka, M., Kaminski, M. 2018. Pretreatment of lignocellulosic materials as substrates for fermentation processes. *Molecules* 23(11): 2937.
- Kumagai, A., Lee, S.H., Endo, T. 2016. Evaluation of the effect of hot-compressed water treatment on enzymatic hydrolysis of lignocellulosic nanofibrils with different lignin content using a quartz crystal microbalance. *Biotechnology and Bioengineering* 113(7): 1441-1447.
- Lee, S.H., Chang, F., Inoue, S., Endo, T. 2010. Increase in enzyme accessibility by generation of nanospace in cell wall supramolecular structure. *Bioresource Technology* 101(19): 7218-7223.
- Lee, H.S., An, C.H., Kang, J.W., Lee, W.Y., Yi, J.-S. 2018. Investigation of Growth Characteristics of *Salix gracilistyla* Clones. *Journal of Korean Society of Forest Science* 107(1): 16-24.
- Ling, Z., Chen, S., Zhang, X., Takabe, K., Xu, F. 2017. Unraveling variations of crystalline cellulose induced by ionic liquid and their effects on enzymatic hydrolysis. *Scientific Reports* 7: 10230.
- Park, S.Y., Hwang, H., Jang, S., Choi, I.G., Choi, J. 2015. study on pretreatment of giant miscanthus using ionic liquid and structural change of lignin. *Journal of the Korean Wood Science and Technology* 43(3): 344-354.
- Sangian, H., Kristian, J., Rahma, S., Dewi, H.K., Puspasari, D.A., Agnesty, S.Y., Gunawan, S., Widjaja, A. 2015. Preparation of reducing sugar hydrolyzed from high-lignin coconut coir dust pretreated by the recycled ionic liquid [mmim][dmp] and combination with alkaline. *Bulletin of Chemical Reaction Engineering & Catalysis* 10(1): 8-22.
- Segal, L., Creely, J.J., Martin Jr, A.E., Conrad, C.M. 1959. An empirical method for estimating the degree of crystallinity of native cellulose using the X-ray diffractometer. *Textile Research Journals* 29(10): 786-794.
- Shi, J., Balamurugan, K., Parthasarathi, R., Sathitsuksanoh, N., Zhang, S., Stavila, V., Zhang, S., Stavila, V., Subramanian, V., Simmons, B.A., Singh, S. 2014. Understanding the role of water during ionic liquid pretreatment of lignocellulose: Co-solvent or anti-solvent. *Green Chemistry* 16(8): 3830-3840.
- Sluiter, A., Crocker, D., Hames, B., Ruiz, R., Scarlata, C., Sluiter, J., Templeton, D. 2008. Determination of structural carbohydrates and lignin in biomass," NREL/TP-510-42618.
- Wu, L., Lee, S.H., Endo, T. 2013. Effect of dimethyl sulfoxide on ionic liquid 1-ethyl-3-methylimidazolium acetate pretreatment of eucalyptus wood for enzymatic hydrolysis. *Bioresource Technology* 140: 90-96.
- Xu, J., Liu, B., Hou, H., Hu, J. 2017. Pretreatment of eucalyptus with recycled ionic liquids for low-cost biorefinery. *Bioresource Technology* 234: 406-414.

- Yang, B., Wyman, C.E. 2008. Pretreatment: the key to unlocking low-cost cellulosic ethanol. *Biofuels, Bioproducts and Biorefining* 2(1): 26-40.
- Yanti, H., Syafii, W., Wistara, N.J., Febrianto, F., Kim, N.H. 2019. Effect of Biological and Liquid Hot Water Pretreatments on Ethanol Yield from Mengkuang (*Pandanus artocarpus* Griff). *Journal of the Korean Wood Science and Technology* 47(2): 145-162.
- Zhang, J., Wang, Y., Zhang, L., Zhang, R., Liu, G., Cheng, G. 2014. Understanding changes in cellulose crystalline structure of lignocellulosic biomass during ionic liquid pretreatment by XRD. *Bioresource Technology* 151: 402-405.