



Natural Dye Extraction from Merbau (*Intsia bijuga*) Sawdust: Optimization of Solid–Solvent Ratio and Temperature

Aswati MINDARYANI^{1,2,†} · Ali SULTON¹ · Felix Arie SETIAWAN³ · Edia RAHAYUNINGSIH^{1,2}

ABSTRACT

The ecofriendly lifestyle has attracted considerable support for sustainable development. Natural dyes, as sustainable products, have become a research focus and development area for many scientists. Ecofriendly processing also supports circular sustainable development. This study effectively obtained tannins as a natural dye from merbau (*Intsia bijuga*) sawdust using water as an ecofriendly solvent. Merbau sawdust is an underutilized industrial waste. Temperature and solid–solvent ratio variations were performed to extract tannins from merbau sawdust. Temperature and solid–solvent ratio positively affected solution yield and tannin concentration. The optimal condition was identified using response surface methodology and experimental observations. A yield of 0.2217 g tannins/g merbau was obtained under the conditions of 333.15 K and 0.125 solid–solvent ratio. Extraction was controlled by convective mass transfer at the interface of solid particles.

Keywords: natural dye, ecofriendly solvent, tannins, merbau, solid–liquid extraction

1. INTRODUCTION

The back-to-nature style of using natural instead of synthetic dyes has made great contributions to sustainability and consumer habits. The food industry prefers natural over synthetic dyes. However, the textile industry does not follow this behavior due to the price aspect. Even restrictions cannot hinder the application of synthetic dyes in the textile industry (Kiumarsi *et al.*, 2017; Parvinzadeh Gashti *et al.*, 2014). Therefore, scientists

and researchers should consider competitively priced natural dyes to maintain ecofriendliness and sustainability.

Processing waste into products decreases the prices because raw materials are inexpensive. Additionally, this approach improves the circular economy and sustainability of products. Although tannins are compounds commonly used as adhesive materials, their use as natural dyes is often ignored (Hendrik *et al.*, 2019; Trisatya *et al.*, 2023); they are sustainable and ecofriendly al-

Date Received August 18, 2023, Date Revised September 14, 2023, Date Accepted October 13, 2023

¹ Department of Chemical Engineering, Faculty of Engineering, Universitas Gadjah Mada, Yogyakarta 55281, Indonesia

² Indonesia Natural Dye Institute (INDI), Grup Riset Interdisipliner Institut Pewarna Alami Indonesia, Laboratorium Penelitian dan Pengujian Terpadu (LPPT), Universitas Gadjah Mada, Yogyakarta 55281, Indonesia

³ Department of Chemical Engineering, Faculty of Engineering, University of Jember, Jawa Timur 68121, Indonesia

[†] Corresponding author: Aswati MINDARYANI (e-mail: amindaryani@ugm.ac.id, <https://orcid.org/0000-0003-3617-2341>)

© Copyright 2023 The Korean Society of Wood Science & Technology. This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/4.0/>) which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

ternatives to synthetic dyes and provide the opportunity to blend the beauty of natural colors with improved environmental values across various industries.

Another advantage of natural dyes developed from waste or by-products is their abundant resources. Natural dyes can be derived from different plant, animal, and fungal parts and minerals (Haji *et al.*, 2016; Ju and Roh, 2020; Rahayuningsih *et al.*, 2019; Roh and Jo, 2022). Indonesia has great potential natural resources for generating natural dyes. Merbau (*Intsia bijuga*), an unexplored resource, can be utilized as a natural-dye source, with a brown color, produced by tannins (Malik *et al.*, 2016). Further, tannins are not limited to natural dyes but have broad applications as coagulants, superplasticizers, floating agents, and adhesives (Fraga-Corral *et al.*, 2020). The structures of several forms of tannins are shown in Fig. 1.

Merbau is primarily used as hardwood for furniture, musical instruments, and construction. The wood processing industry emits 60% of underdeveloped or underutilized wastes or residues (Prasetya *et al.*, 2021). However, the extraction of tannins from merbau has obstacles, such as low resource access and research interest, that impede development. Wood waste or residue is primarily processed into firewood without any other processing steps. Hence, its value does not increase. Rahayuningsih *et al.* (2011) compared mahogany (*Swietenia mahagoni*) and merbau sawdusts as prospective

raw materials for natural dyes and found that the durability, quality, and extraction of merbau were superior to mahogany (Rahayuningsih *et al.*, 2011). Malik *et al.* (2016) successfully extracted tannins from merbau wood using water, ethanol, and ethyl acetate with yields of 1.34%, 12.45%, and 12.56%, respectively (Malik *et al.*, 2016). Polar solvents provide high yields in tannin extraction. However, their use increases the carbon footprint of the natural-dye product. Ease and safety issues are other reasons for using water as an extraction solvent. Mun *et al.* (2020, 2021) investigated the extraction of *Pinus radiata* bark with 0.8% NaHCO₃ aqueous solution and prepared a neutral extract that was used as a natural dyestuff for cotton and silk fabrics (Mun *et al.*, 2020, 2021). Jung *et al.* (2017) extracted phenolic compounds from oak wood (*Quercus mongolica*) through steam explosion. They identified the optimal extraction conditions using response surface methodology (RSM; Jung *et al.*, 2017). Jung and Yang (2018) employed RSM to optimize a two-stage extraction process that consisted of steam explosion and water extraction (Jung and Yang, 2018). The study conducted by Um *et al.* (2020) aimed to investigate the optimization of ascorbic acid extraction from *Rugosa rose* (*Rosa rugosa* Thunb.) fruit by the utilization of RSM (Um *et al.*, 2020). RSM was used to optimize mycelial growth and cordycepin content in the submerged culture of *Paecilomyces japonica* (Ha *et al.*, 2020).

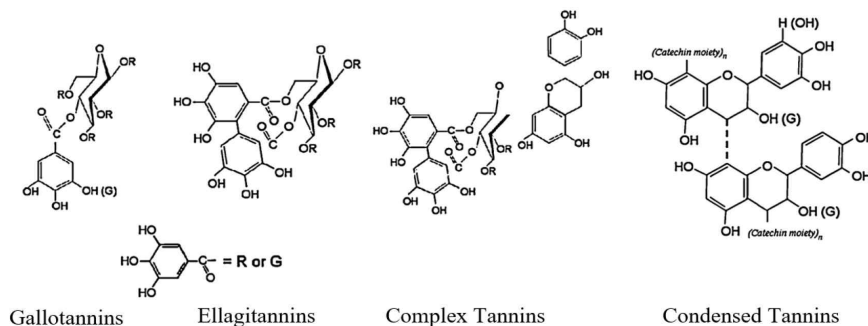


Fig. 1. Chemical structures of tannins. Adapted from Aguilar *et al.* (2007) with permission of Springer Nature.

Solid-solvent extraction depends on solvent type, particle size, solid-solvent ratio, and temperature. This study aims to identify the optimal extraction condition that provides the highest tannin concentration in extracts. In this study, water was chosen as the solvent. Meanwhile, particle size was defined in accordance with the available sawdust, and solid-solvent ratio (merbau sawdust-water) and temperature were varied to identify the optimal extraction condition. The optimal condition and design parameters for upscaling extraction were used as response parameters. This study also performed a simple examination of the extraction mechanism.

2. MATERIALS and METHODS

2.1. Materials

Merbau sawdust was obtained from the Indonesia Natural Dye Institute Research Center, Universitas Gadjah Mada. Distilled water was used as a solvent for extraction process, and ethanol was utilized as a solvent for total tannin content analysis (Soxhlet method). The reagents used for tannin analysis were sulfuric acid, potassium permanganate (KMnO₄), and indigo carmine (C₁₆H₈N₂Na₂O₈S₂), procured from Sigma-Aldrich (St. Louis, MO, USA).

2.2. Sample preparation

Merbau sawdust was preliminarily dried in an oven at 110°C to a constant weight at which the sample had the minimum water content necessary to generate the optimal conditions for extraction. Merbau sawdust was sieved with a 45/60 mesh to obtain homogenous particle sizes.

2.3. Extraction

Merbau sawdust was extracted through Soxhlet and shaking water bath methods. The Soxhlet method was used to obtain the total tannin content of the sawdust.

A total of 3 g of sawdust was covered with filter paper and soaked in 500 cm³ of ethanol (96 wt%) until a clear solvent was obtained. Meanwhile, the shaking water bath method was implemented for 3 h using water and various independent variables (Table 1). Both solutions were analyzed through the volumetric method to obtain tannin concentrations.

2.4. Tannin analysis

The tannin extract solution (50 cm³) was added to 50 cm³ distilled water and boiled until its volume decreased to 50 cm³. A total of 5 mL solution was mixed with 20 cm³ indigo carmine solution in 200 cm³ volumetric flask, with distilled water and titrated with 0.1 N KMnO₄ standard solution. Volumetric analysis was conducted twice on every sample. Meanwhile, a blank solution, without any sample, was prepared and titrated correspondingly from the indigo carmine solution. Tannin yield was calculated using Equation (1).

$$C = \frac{(V_s - V_b) \times 0.004157 \times DF}{m_s}, \quad (1)$$

Where *C* is the tannin content (g/g sawdust); *V_s* is the titrated volume of the sample; *V_b* is the titrated volume of the blank; DF is the Dilution factor; *m_s* is the weight of merbau sawdust.

Indigo carmine solution was prepared by dissolving 3 g of indigo carmine (analytical grade, Sigma-Aldrich) in 100 mL of distilled water with continuous heating. The boiled solution was cooled and mixed with water and 25 cm³ sulfuric acid in a 500 cm³ volumetric flask.

Table 1. Independent variables in this research

Independent variable	Range of level				
	-1	-δ	0	1	2
Temperature, °C (<i>X</i> ₁)	30	-	45	60	-
Solid: solvent ratio, (<i>X</i> ₂)	0.083	0.130	0.167	0.250	0.333

2.4.1. Response surface methodology

The independent variables used to identify the optimal extraction conditions are shown in Table 1. The response variables (dependent variables) in volumetric analysis were analyzed using RSM with Minitab® 19.

2.4.2. Extraction mechanism

Tannin extraction is microscopically regarded as the mass transfer of tannins from inside sawdust solids into solvents. The mechanism of mass transfer is theoretically described as the diffusion of tannin molecules in sawdust solids to the interface of solid particles, transfer of tannin molecules from the particle surface to the liquid film at the particle surface, and convective mass transfer of tannins from the liquid film into the bulk liquid solvent. This study proposed two mass transfer models.

2.4.2.1. Model 1: Control by diffusion in solid particles

This model proposes that the diffusion rate in solid particles and convective mass transfer at the particle surface control extraction. Mass transfer is based on Fick's law of diffusion and convection:

$$N_A = -D_e \frac{dC_A}{dr} \quad (2)$$

$$N_{A_f} = -k_c a (C_{A_f}^* - C_{A_f}) \quad (3)$$

This model is based on several assumptions: sawdust particles are spherical solids; the process is isothermal; volume is fixed throughout the experiment; a concentration gradient does not exist in the bulk solvent. Equation (4) was obtained on the basis of the mass balance analysis of the solid volume element:

$$\frac{\partial^2 C_A}{\partial r^2} + \frac{2}{r} \frac{\partial C_A}{\partial r} = \frac{1}{D_e} \frac{\partial C_A}{\partial t} \quad (4)$$

This equation can be solved numerically by using the

initial and boundary conditions specified below:

$$C_{A(r,0)} = C_{A0} \quad (5)$$

$$C_{A(0,t)} = \text{finite} \quad (6)$$

$$-D_e \frac{dC_A}{dr}(R,t) = k_c (C_{A_f}^* - C_{A_f}) \quad (7)$$

The value of C_{A_f} was generated by compiling the mass balance of solutes in the solid and liquid phases:

$$C_{A_f} = C_{A_{f0}} + \frac{V_s}{V} \left[C_{A_0} - \frac{1}{R} \int_0^R C_A dr \right] \quad (8)$$

In this case, D_e is the diffusivity coefficient of the solid (cm^2/min), C_A is the tannin concentration (g/cm^3) in sawdust at time t (min), C_{A_0} is the tannin concentration in sawdust at $t = 0$, (g/cm^3), C_{A_f} is the tannin concentration (g/cm^3) in the solvent at time t , $C_{A_f}^*$ is the tannin concentration (g/cm^3) in the solvent phase that is in equilibrium with the tannin concentration at the solid particle surface, $C_{A_{f0}}$ is the tannin concentration (g/cm^3) in the solvent phase at $t = 0$, k_c is the mass transfer coefficient (cm/min), $k_c a$ is the volumetric mass transfer coefficient, $1/\text{min}$, a is the mass transfer specific surface (area/volume) of sawdust (cm^2/cm^3), V_s is the solid volume (cm^3), V is the solvent volume (cm^3), r is the radial position in the sawdust particle from the center (cm) and R is the sawdust radius (0.009 cm).

The equilibrium between solid and liquid concentrations at the solid-liquid interface is expressed as

$$C_{A_f}^* = k_H C_A, \quad (9)$$

where k_H is the equilibrium constant. In this case, k_H is considered constant across various tannin concentrations.

2.4.2.2. Model 2: Control by convective mass transfer

The second model assumes that the diffusion rate inside sawdust particles is faster than that of particle surfaces. This assumption is based on the fact that saw-

dust particles are tiny, with a radius of only 0.009 cm, the extraction time to reach equilibrium is < 3 h, and sawdust wood is microscopically porous with 0.833 g/cm³ density. This assumption accounts for the rapid diffusion rate in the solid phase. Therefore, the second model assumes that the tannin concentration inside sawdust particles is always homogeneous regardless of position and that mass transfer at particle surfaces controls extraction.

The equilibrium equation is then estimated with

$$C_{Af}^* = K_{Hs} X_A, \tag{10}$$

where C_{Af}^* is the tannin concentration in the solution (in equilibrium with tannins in the solid, g/mL), X_A is the tannin concentration in sawdust solid particles (g tannin/g solid), and K_{Hs} is the equilibrium constant. The correlation of K_{Hs} in Equation (10) with the equilibrium k_H of Model 1 in Equation (9) is given by $K_{Hs} = \frac{\rho_s}{k_H}$ with ρ_s = wood density (0.83 g/cm³).

The mass transfer of tannins in the solution is formulated as

$$V \frac{dC_{Af}}{dt} = k_c A_s (C_{Af}^* - C_{Af}), \tag{11}$$

$$V \frac{dC_{Af}}{dt} = k_c A_s (K_{Hs} X_A - C_{Af}), \tag{12}$$

where A_s is the total surface area of sawdust particles in the solution. During extraction time $t = t_0$, the concentration of tannins in the solid and solution are X_{A0} and C_{Af0} . The overall mass balance of tannins in the extraction mixture yields the following equation:

$$M_s (X_{A0} - X_A) = V (C_{Af} - C_{Af0}), \tag{13}$$

where M_s is the total mass of sawdust solids. The solution and integration of Equations (12) and (13) result in

$$\ln \left[\frac{X_{Ain} - K_1 C_{Af}}{X_{Ain} - K_1 C_{Af0}} \right] = -K_2 (t - t_0), \tag{14}$$

where $K_1 = \frac{V}{M_s} + \frac{1}{K_{Hs}}$ and $K_2 = k_c A_s \left(\frac{K_{Hs}}{M_s} + \frac{1}{V} \right)$. In this case, X_{Ain} is the tannin concentration in sawdust at the beginning of extraction ($t = 0$). Equation (14) is written in another form for evaluation:

$$C_{Af} = \frac{1}{K_1} [X_{Ain} - (X_{Ain} - K_1 C_{Af0}) \cdot \exp(-K_2(t - t_0))]. \tag{15}$$

K_{Hs} and k_c are evaluated through the minimization of the sum of squares of errors (SSEs).

The parameters of mass transfer in both models are evaluated through the minimization of SSE, in which error is defined as the difference between the experimental data and model prediction of C_{Af} :

$$SSE = \sum (C_{Af,calc} - C_{Af,data})^2. \tag{16}$$

The Van't Hoff equation describes the correlation of the solid-liquid equilibrium constant k_H described in Equation (17) with the extraction temperature in isothermal processes.

$$\ln(k_H) = -\frac{\Delta H}{R} \frac{1}{T} + \frac{\Delta S}{R}, \tag{17}$$

where H is the enthalpy (kJ), S is the entropy (kJ/K), R is the gas constant (J/mol·K), and T is the temperature (K).

3. RESULTS and DISCUSSION

3.1. Effect of solid-solvent ratio and temperature on tannin yield and concentration

The total tannin content of merbau sawdust was determined through the Soxhlet method, and a tannin

content of 0.3472 g tannins/g merbau was obtained. Volumetric analysis was performed to identify the value of equivalent tannins and all tannin components, such as (-)-robidanol, robinetin, catechin, naringenin, dihydro-myricetin, piceatannol, quercetin, and fustin (Sari *et al.*, 2021).

In Fig. 2, tannin concentration and yield are presented as a function of solid-solvent ratio. Solid-solvent ratio had a considerable effect on tannin concentration but not on yield. This result was reasonable because tannin concentration, which increased with variables, was calculated as the amount of extracted tannins divided by the total amount of solvent, which was a fixed value. Meanwhile, yield was divided by the solid amount, which increased with variables.

Temperature significantly affected both parameters. The increase in extraction temperature accelerated tannin extraction from merbau sawdust. It was primarily affected by the mass transfer coefficient, which was a function of temperature.

3.2. Determining optimum condition for tannin yield and concentration

Experimental results were analyzed using Minitab[®]

19 to investigate the effects of temperature and solid-solvent ratio on extracted tannin concentration. Table 2 shows constants and *F*- and *p*-values. The constants describe the magnitude of values in the nonlinear polynomial equation of RSM results (Bezerra *et al.*, 2008; Mansour *et al.*, 2017; Montgomery, 2017). *F*- and

Table 2. Analysis of variance of RSM

Source	Tannin concentration (g/g)		
	Constants	<i>F</i> -value	<i>p</i> -value
Model		307.09	0.000
Linear	-14.52	615.88	0.000
X_1	0.08926	1,096.98	0.000
X_2	-1.426	134.78	0.000
Square		70.96	0.000
X_1^2	-0.00014	115.35	0.000
X_2^2	-1.071	26.58	0.000
Two-way interaction		27.56	0.000
$X_1 \times X_2$	0.00636	27.56	0.000
R-square		0.9884	

RSM: response surface methodology.

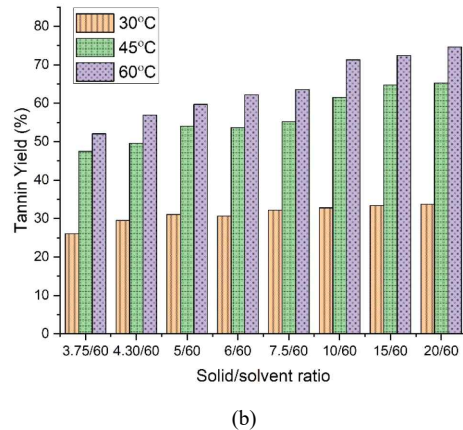
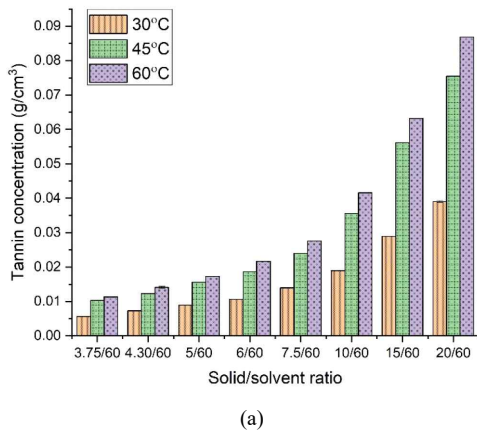


Fig. 2. Tannin extraction from merbau sawdust. (a) Tannin concentration in solution and (b) tannin yield.

p-values can describe model fitness (Rahayuningsih *et al.*, 2021). A higher *F*-value than *F*-statistic indicates an acceptable model. Meanwhile, *p*-value of the model (0.000) should be < 0.05 to be statistically significant. R-square of the model was 0.9884.

Further analysis showed that residual values increased with increasing model accuracy [Fig. 3(a); Agarry and Ogunleye, 2012; Mohajeri *et al.*, 2010]. Data were normally distributed. The plot of the experimental and modeled concentrations are shown in Fig. 3(b) with gradient and R-square values ~1.00.

The effect of independent variables is illustrated in Fig. 4. Temperature and solid-solvent ratio positively affected tannin concentration [Fig. 4(a)]. Increasing temperature led to the softening and expansion of solid substances along with an increase in diffusivity and solubility of tannins (Sun *et al.*, 2011). However, both parameters stabilized at some point with the further increase in tannin concentration. Meanwhile, the combination of temperature and solid-solvent ratio resulted in a high positive value of tannin concentration [Fig. 4(b)].

A final analysis was conducted using RSM to identify the optimal extraction condition. The optimal condition was identified as a temperature of 333.15 K and solid-solvent ratio of 0.3224 and yielded 0.2639 g tannins/g merbau. However, the experiment showed that yield decreased when the solid-solvent ratio further increased

because the solution was absorbed and trapped in solid pores. This phenomenon affected the optimal extraction condition. The optimal solid-solvent ratio of 0.125 resulted in a yield of 0.2217 g tannins/g merbau. Nevertheless, the optimal modeling condition can still be implemented in industrial processes because the solid (merbau sawdust) and solution can be separated using a filter press machine.

3.3. Extraction mechanism model

The equilibrium constant at various temperatures was calculated using Equations (9) and (17). Fig. 5(a) and (b) shows that k_H values at 303.15, 318.15, and 333.15 K were 0.4254, 0.9129, and 1.6908 (cm³/cm³), respectively. The equilibrium constant was obtained based on the slope under each condition. Consistent with the findings of previous research, the results of this work showed that high temperatures were associated with high equilibrium constants. Next, the obtained equilibrium constant was utilized in Equation (9) to generate a temperature function. The values of ΔH and ΔS were generated in accordance with Equation (17) by recalculating the linear regression and were 38.7 kJ and 120.53 kJ/K, respectively. Therefore, spontaneous and endothermic processes occurred during the solid-liquid extraction of merbau sawdust.

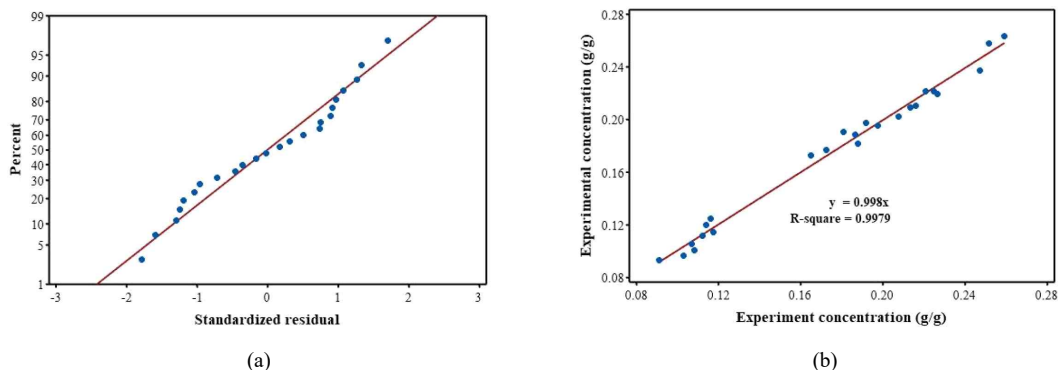


Fig. 3. Standardized residual (a) and linear response plots (b) of experimental results.

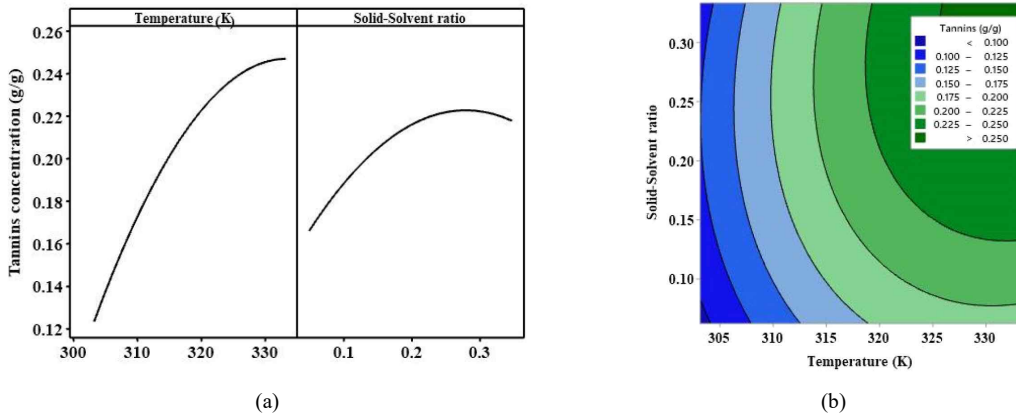


Fig. 4. Factorial plot of effect of independent variables on responses. (a) Linear and (b) two-way interaction.

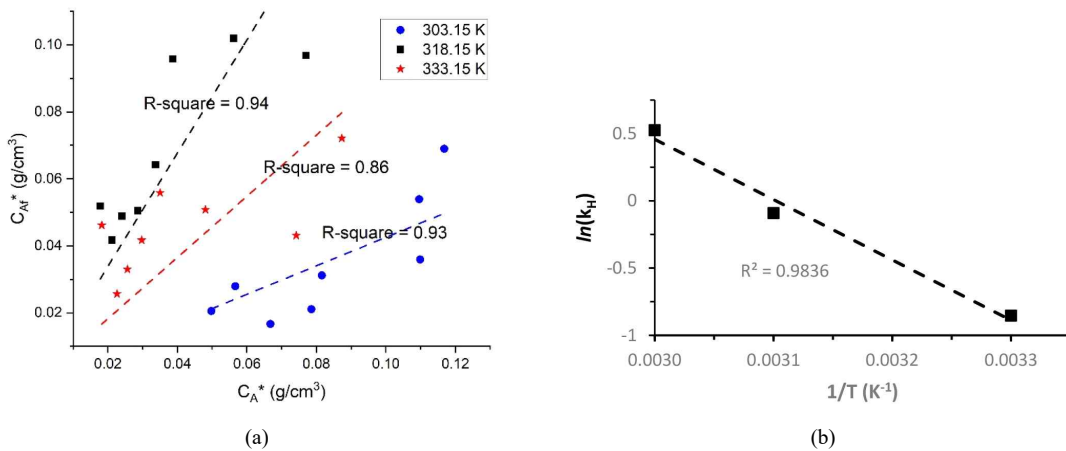


Fig. 5. Calculation of equilibrium constants (a) from experimentally determined values and (b) as a function of temperature.

Models 1 and 2 were evaluated based on the tannin concentration obtained at 60°C as a function of time. The mass transfer coefficient ($k_c a$) and diffusivity (D_e) in Model 1 were evaluated using Equations (4), (5), (6), (7), and (8) by applying the finite difference approximation method.

The concentration profile is presented in Fig. 6. The model and experimental C_{Af} profiles are compared in Fig. 6(a), which confirms that the presence of strong driving forces at the early stage of extraction resulted in


rapid diffusion. Meanwhile, Fig. 6(b) presents the tannin concentration around merbau sawdust particles. These findings will help scholars develop a green tannin extraction process. However, stabilizing tannin content, structure, and activity remains a challenge in tannin extraction (Cuong *et al.*, 2020).

Moreover, tannin amount decreased with prolongation of the handling time of raw materials (Cuong *et al.*, 2020). Thus, the local raw material plant is considered the best option for tannin production. Meanwhile, pro-

cess ease and solvent availability are other factors to be examined.

The initial values of mass transfer coefficient (k_c) and diffusivity (D_e) were estimated and subsequently computed by using the Hooke-Jeeves technique until their minimum SSEs were obtained. The results are presented in Fig. 6. The value of D_e is 3.71×10^{-7} cm²/min and k_c is 0.681 cm/min respectively, with SSE of 2.317×10^{-4} . The diffusivity coefficient obtained in this work was lower than previously reported values of 1.69×10^{-6} – 1.86×10^{-6} (Tasheva *et al.*, 2019) and 1.23×10^{-5} cm²/min (Stefanova *et al.*, 2017) because this experiment used water as the solvent in contrast to other studies that used ethanol. However, the effective diffusion coefficient was greater than 6.24×10^{-8} – 2.22×10^{-7} cm²/min (Simeonov and Koleva, 2012). Raw material properties (tannin content, structure, and activity; particle size; porosity; water content) and extraction process parameters (method, temperature, and time) accounted for differences in the effective diffusion and mass transfer coefficients.

For Model 2, calculation with Equation (15) and SSE minimization resulted in $K_{Hs} = 1.16$ (equivalent to $k_{H} = 0.718$), $k_c = 2.15 \times 10^{-5}$ cm/min, and SSE = 1.2×10^{-6} .

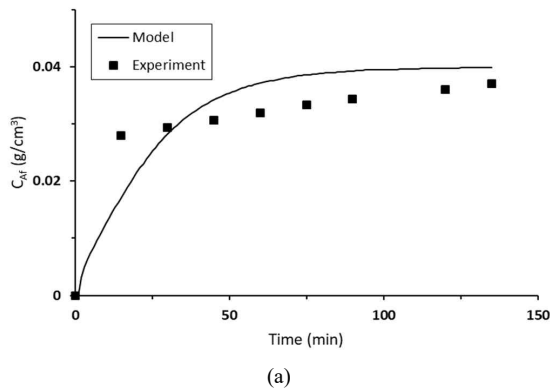

The mass transfer coefficient of Model 2 was very small. Fig. 7 shows C_{Af} as a function of time. In this figure, the calculated C_{Af} was in line with experimental C_{Af} . It is clear that the calculated values of C_{Af} were close to experimental values. Furthermore, SSE of Model 2 was smaller than that of Model 1.

Therefore, the mass transfer rate was controlled by the transfer of tannins at the interface of sawdust particles, and diffusion in solid particles was rapid due to the porosity of solid sawdust.

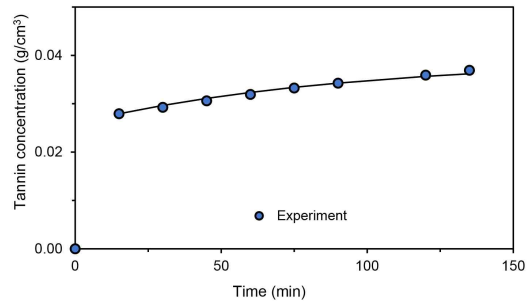


Fig. 7. Tannin concentration profile based on Model 2.

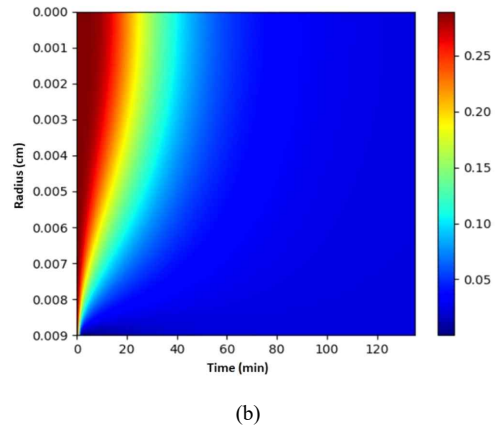


Fig. 6. Tannin concentration based on Model 1. (a) Comparison of model and experimental results and (b) profile of merbau sawdust particles.

4. CONCLUSIONS

Merbau sawdust can be processed and utilized as a natural brown-colored dye. The ecofriendly extraction of natural dye from merbau sawdust was successfully conducted with water as the solvent instead of an organic solvent. The yield of 0.2217 g tannins/g merbau was obtained under the optimal conditions of 333.15 K and solid-solvent ratio (merbau sawdust-water ratio) of 0.125. Temperature and solid-solvent ratio had a positive effect on tannin yield. Extraction was controlled by convective mass transfer at the interface of solid particles. The obtained parameters can be implemented to design the industrial extraction of natural dyes with water as an ecofriendly solvent.

CONFLICT of INTEREST

No potential conflict of interest relevant to this article was reported.

ACKNOWLEDGMENT

The authors acknowledge the support of the Chemical Engineering Department, Universitas Gadjah Mada, for the laboratory facilities provided in this research. This research is supported by the Research Funding Scheme of Penelitian Pengembangan Unggulan Perguruan Tinggi 2020-2022 under the contract number 1699/UNI/DITLIT/Dit-Lit/PT.01.03/2022 from the Directorate General of Higher Education.

REFERENCES

- Agarry, S.E., Ogunleye, O.O. 2012. Factorial designs application to study enhanced bioremediation of soil artificially contaminated with weathered bonny light crude oil through biostimulation and bioaugmentation strategy. *Journal of Environmental Protection* 3(8): 748-759.
- Aguilar, C.N., Rodríguez, R., Gutiérrez-Sánchez, G., Augur, C., Favela-Torres, E., Prado-Barragan, L.A., Ramírez-Coronel, A., Contreras-Esquivel, J.C. 2007. Microbial tannases: Advances and perspectives. *Applied Microbiology and Biotechnology* 76(1): 47-59.
- Bezerra, M.A., Santelli, R.E., Oliveira, E.P., Villar, L.S., Escaleira, L.A. 2008. Response surface methodology (RSM) as a tool for optimization in analytical chemistry. *Talanta* 76(5): 965-977.
- Cuong, X.D., Hoan, N.X., Dong, D.H., Thuy, L.T.M., Thanh, N.V., Ha, H.T., Tuyen, D.T.T., Chinh, D.X. 2020. Tannins: Extraction from Plants. In: *Tannins: Structural Properties, Biological Properties and Current Knowledge*, Ed. by Aires, A. IntechOpen, London, UK.
- Fraga-Corral, M., García-Oliveira, P., Pereira, A.G., Lourenço-Lopes, C., Jimenez-Lopez, C., Prieto, M.A., Simal-Gandara, J. 2020. Technological application of tannin-based extracts. *Molecules* 25(3): 614.
- Ha, S.Y., Jung, J.Y., Yang, J.K. 2020. Effect of light-emitting diodes on cordycepin production in submerged culture of *Paecilomyces japonica*. *Journal of the Korean Wood Science and Technology* 48(4): 548-561.
- Haji, A., Mehrizi, M.K., Sharifzadeh, J. 2016. Dyeing of wool with aqueous extract of cotton pods improved by plasma treatment and chitosan: Optimization using response surface methodology. *Fibers and Polymers* 17: 1480-1488.
- Hendrik, J., Hadi, Y.S., Massijaya, M.Y., Santoso, A., Pizzi, A. 2019. Properties of glued laminated timber made from fast-growing species with mangium tannin and phenol resorcinol formaldehyde adhesives. *Journal of the Korean Wood Science and Technology* 47(3): 253-264.
- Ju, S.G., Roh, J. 2020. Manufacturing regenerated woody

- dyed fiber from waste MDF using natural dyes. *Journal of the Korean Wood Science and Technology* 48(2): 154-165.
- Jung, J.Y., Ha, S.Y., Yang, J.K. 2017. Response surface optimization of phenolic compounds extraction from steam exploded oak wood (*Quercus mongolica*). *Journal of the Korean Wood Science and Technology* 45(6): 809-827.
- Jung, J.Y., Yang, J.K. 2018. A two-stage process for increasing the yield of prebiotic-rich extract from *Pinus densiflora*. *Journal of the Korean Wood Science and Technology* 46(4): 380-392.
- Kiumarsi, A., Parvinzadeh Gashti, M., Salehi, P., Dayeni, M. 2017. Extraction of dyes from *Delphinium Zalil* flowers and dyeing silk yarns. *The Journal of the Textile Institute* 108(1): 66-70.
- Malik, J., Santoso, M., Mulyana, Y., Ozarska, B. 2016. Characterization of merbau extractives as a potential wood-impregnating material. *BioResources* 11(3): 7737-7753.
- Mansour, R., Ezzili, B., Farouk, M. 2017. The use of response surface method to optimize the extraction of natural dye from winery waste in textile dyeing. *The Journal of the Textile Institute* 108(4): 528-537.
- Mohajeri, L., Aziz, H.A., Isa, M.H., Zahed, M.A. 2010. A statistical experiment design approach for optimizing biodegradation of weathered crude oil in coastal sediments. *Bioresource Technology* 101(3): 893-900.
- Montgomery, D.C. 2017. *Design and Analysis of Experiments*. John Wiley & Sons, Hoboken, NJ, USA.
- Mun, J.S., Kim, H.C., Mun, S.P. 2020. Chemical characterization of neutral extracts prepared by treating *Pinus radiata* bark with sodium bicarbonate. *Journal of the Korean Wood Science and Technology* 48(6): 878-887.
- Mun, J.S., Kim, H.C., Mun, S.P. 2021. Potential of neutral extract prepared by treating *Pinus radiata* bark with NaHCO₃ as a dyestuff. *Journal of the Korean Wood Science and Technology* 49(2): 134-141.
- Parvinzadeh Gashti, M., Katozian, B., Shaver, M., Kiumarsi, A. 2014. Clay nanoadsorbent as an environmentally friendly substitute for mordants in the natural dyeing of carpet piles. *Coloration Technology* 130(1): 54-61.
- Prasetya, A., Siagian, H., Setiawan, F.A., Petrus, H.T.B.M. 2021. Densification process of Merbau (*Intsia bijuga*) and Matoa (*Pometia pinnata* J.R. Forster & J.G. Forster) sawdust waste for biomass based solid fuel source in West Papua Indonesia: Optimization using response surface methodology (RSM). *Jurnal Rekayasa Proses* 15(1): 116-130.
- Rahayuningsih, E., Rahayu, S.S., Raharjo, T.J. 2011. The potential of sawdust as raw material for the production of natural dye. In: Sydney, Australia, Proceedings of Chemeca 2011: Engineering a Better World: Sydney Hilton Hotel, NSW, Australia, 18-21 September 2011, pp. 2065-2074.
- Rahayuningsih, E., Setiawan, F.A., Ayanie, C.J., Antoko, A.A., Ayuningtyas, Y.I., Petrus, H.B. 2019. Optimization model on the effect of clove oil, formaldehyde, and chitosan added to batik fabric colored with gambier (*Uncaria gambir* Roxb): Antifungal properties and stability. *Indonesian Journal of Chemistry* 20(1): 210-222.
- Rahayuningsih, E., Setiawan, F.A., Rahman, A.B.K., Siahaan, T., Petrus, H.T.B.M. 2021. Microencapsulation of betacyanin from red dragon fruit (*Hylocereus polyrhizus*) peels using pectin by simple coacervation to enhance stability. *Journal of Food Science and Technology* 58(9): 3379-3387.
- Roh, J., Jo, H.J. 2022. Dyeing and color fastness properties of natural dyed actual size hanji. *Journal of the Korean Wood Science and Technology* 50(1): 31-45.
- Sari, R.K., Prayogo, Y.H., Sari, R.A.L., Asidah, N., Rafi, M., Wientarsih, I., Darmawan, W. 2021. *Intsia bijuga* heartwood extract and its phytosome as tyrosinase inhibitor, antioxidant, and sun protector. *Forests*

- 12(12): 1792.
- Simeonov, E., Koleva, V. 2012. Solid-liquid extraction of tannins from *Geranium sanguineum* L.: Experimental kinetics and modelling. *Chemical and Biochemical Engineering Quarterly* 26(3): 249-255.
- Stefanova, G.L., Tasheva, S.T., Damyanova, S.T., Stoyanova, A.S. 2017. Coefficient of diffusion of tannins in extracts from laurel leaves (*Laurus nobilis* L.). *Scientific Works of University of Food Technologies* 64(1):75-79.
- Sun, Y., Liu, D., Chen, J., Ye, X., Yu, D. 2011. Effects of different factors of ultrasound treatment on the extraction yield of the all-trans- β -carotene from citrus peels. *Ultrasonics Sonochemistry* 18(1): 243-249.
- Tasheva, S.T., Ivanova, T.A., Popova, V.T., Iliev, I.Z., Stankov, S.S., Fidan, H.N., Mazova, N.N., Stoyanova, A.S. 2019. Coefficient of diffusion of tannins in extracts from physalis leaves (*Physalis peruviana* L.). *Bulgarian Chemical Communications* 51(D): 209-213.
- Trisatya, D.R., Santoso, A., Abdurrachman, A., Prastiwi, D.A. 2023. Performance of six-layered cross laminated timber of fast-growing species glued with tannin resorcinol formaldehyde. *Journal of the Korean Wood Science and Technology* 51(2): 81-97.
- Um, M., Kim, J.W., Lee, J.W. 2020. Optimization of ascorbic acid extraction from rugosa rose (*Rosa rugosa* Thunb.) fruit using response surface methodology and validation of the analytical method. *Journal of the Korean Wood Science and Technology* 48(3): 364-375.